



### **Science Arts & Métiers (SAM)**

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>  
Handle ID: <http://hdl.handle.net/10985/12515>

#### **To cite this version :**

T. SIVARUPAN, Mohamed EL MANSORI, Nicolas CONIGLIO - Investigation of process parameter effect on anisotropic properties of 3D printed sand molds - International Journal of Advanced Manufacturing Technology - Vol. 94, p.2175-2185 - 2018

Any correspondence concerning this service should be sent to the repository

Administrator : [scienceouverte@ensam.eu](mailto:scienceouverte@ensam.eu)



# Investigation of Process Parameters Effect on Anisotropic Properties of 3D Printed Sand Molds

---

Nicolas CONIGLIO\*, Tharmalingam SIVARUPAN, Mohamed EL MANSORI

MSMP Laboratory, EA-7350, Arts et Metiers ParisTech,

2 Cours des Arts et Metiers, 13617 Aix en Provence, France

## ABSTRACT

The development of sand mold three-dimensional printing technologies enables the manufacturing of molds without the use of a physical model. However, the effects of the three-dimensional printing process parameters on the mold permeability and strength are not well known, leading the industries to keep old settings until castings have recurring defects. In the present work, the influence of these parameters was experimentally investigated to understand their effect on the mold strength and permeability. Cylindrical and bar-shaped test specimens were printed to perform respectively permeability and bending strength measurements. Experiments were designed to statistically quantify the individual and combined effect of these process parameters. While the binder quantity only affects the mold strength, increasing the recoater speed leads to both greater permeability and reduced strength due to the reduced sand compaction. Recommendations for optimizing some 3D printer settings are proposed to attain predefined mold properties and minimize the anisotropic behavior of the sand mold in regards to both the orientation and the position in the job box.

**Keywords:** 3D printing; mold properties; casting; additive manufacturing

### *Nomenclature :*

3DP	Three-dimensional printing
3PB	Three-point bending
$P_x$	Permeability along X-direction
$P_y$	Permeability along Y-direction
$P_z$	Permeability along Z-direction

---

\* Corresponding author: nicolas.coniglio@ensam.eu

$\sigma_x$	Stress along X-direction
$\sigma_y$	Stress along Y-direction
$\rho$	Density

## I. INTRODUCTION

The development in additive manufacturing also referred to as three-dimensional (3D) printing technology, provides technological means to fabricate near-net-shaped three-dimensional parts, as indicated in reviews on the subject [1–6]. Particular 3D printers are used to manufacture sand molds for casting, directly from computer models [4–20]. While dimensional accuracy is the main concern due to squashing [11,21–24], other sand mold properties such as density [25], permeability [15], and strength [9,15,25–27] remain difficult to control homogeneously over the volume of the printed parts. Sand mold designs for foundry purposes may include a high permeability for filling enhancement, a sand binder with low volatile content for porosity defect avoidance, an excellent dimensional accuracy for limited post-casting machining, and sufficient strength for easier handling [28].

Permeability refers to the ability of a mold volatiles to escape without being a source of concern and is, therefore, a measure of the ease with which a mold gas can flow through the porous sand mold media [28]. A high mold permeability allows the escape of gases, reducing the outgassing pressure ahead of the molten front, and subsequently improving filling ability. Permeability relies in part on the sand grain compaction, with low compaction resulting in greater intergrain spacing and subsequently high permeability [12]. Therefore, high permeability conditions imply a probability of metal penetration defect due to the large inter-sand grain spacing.

A high mold strength permits good dimensional control of the casting during cooling, by limiting distortion, but may enhance hot tearing, by hindering the free contraction of the solidifying metal [16,17,28]. The sand mold strength depends upon the sand grain compaction and the binder amount [12,26], with greater strength for greater sand grain compactions and binder amounts. However, the excessive use of binder produces too much off-gazing pressure ahead of the molten front during filling, generating poor casting quality [5] and lack of filling [29].

Sand grain compaction is a common parameter that controls both strength and permeability. While numerous compacting methods have been developed [30], there are today issues in homogeneously compacting the sand grains within the same job box. Moreover, as greater compaction simultaneously reduces permeability and increases strength, the dependence of these two properties, upon the same

1 condition, renders rather difficult the control of these two properties simultaneously. Post-printing  
2 solutions have been, therefore, proposed to obtain given mold properties by optimized mold curing  
3 conditions [4,15].  
4  
5

6  
7 Among the various existing binders, foundries commonly use the organic furan binder in 3D printing  
8 machines for the mold manufacturing to cast light alloys [5,11,14,16,17,31]. A 3D printer  
9 manufactures molds by successive layers of deposited sand with the addition of a controlled amount of  
10 resin at the future mold positions. The furan binder poses advantages related to its room-temperature  
11 curing and high mechanical strength [31]. While some studies investigated the process parameter  
12 effects on mold properties[12,26] [11], only one [11] quantified the heterogeneous properties of sand  
13 molds within the same job-box. Moreover, few published on the properties of furan sand molds  
14 printed by ExOne 3D printer [5,14].  
15  
16  
17  
18  
19

20  
21 The present work investigates the influence of print resolution, recoater (also referred to as sand  
22 conveyor) speed, and job-box position on the strength and permeability of sand molds. Experiments  
23 were statistically designed to quantify the individual and combined effect of process parameters on.  
24 Tests were carried out by printing three-point bending and permeability specimens at various positions  
25 in the job box. Statistical analysis was finally applied for selecting the appropriate 3D printer settings.  
26  
27  
28  
29  
30

## 31 32 33 34 35 36 **II. EXPERIMENTAL SETUP**

### 37 38 39 *3D Printing process*

40  
41 The sand mold samples were printed by a binder, furan, jetting printer<sup>†</sup> equipped with an  
42 800×500×400 mm<sup>3</sup> job box. The printing process began by mixing of the sulfonic acid catalyst and  
43 magnesium inhibitor<sup>‡</sup> with 8 kg of sand particles and temporally stored in the mixing chamber. Sand  
44 layers of 280 μm thickness were successively deposited on the job box. Then the platform was  
45 lowered by a distance equal to the layer thickness before spreading the furfuryl alcohol based binder  
46 by the printhead inkjet nozzles on specific area according to each slice (cross section) in the STL file  
47 of the part to be printed. The process continued until the last slice of the samples was printed. The  
48 printed sand parts were cured at room temperature, inside the job box, for an hour before they were  
49  
50  
51  
52  
53  
54  
55  
56

---

57  
58 <sup>†</sup> ExOne S-Print<sup>TM</sup>

59 <sup>‡</sup> In order to imitate the use of the mold for the Mg alloy casting.

1 taken out of the job box and the loose sand particles were removed with a soft brush or compressed  
 2 air.  
 3  
 4  
 5  
 6

### 7 *Printing parameters*

8  
 9 The experimental setup was same as in the previous publication [32]. Briefly, a job-box (Fig 2) was  
 10 designed in a commercial software program, NetFabb™, so as to characterize the sand specimens from  
 11 various job-box positions, indicated as  $X_i Y_j$  with  $i$  and  $j$  the X and Y coordinates, respectively. A total  
 12 of 32 bars and 36 cylinders were printed each time (Table 1), and the respective tests were carried out.  
 13 Printings were performed in a room maintained at a temperature of  $298 \pm 3$  K and relative humidity of  
 14  $40 \pm 10$  %. The print resolution (or furan drop spacing) and the recoater speed were varied (Table 2).  
 15  
 16 Printed specimens may sink during compaction due to squashing if unbound sand particles are present  
 17 underneath the printed specimens [21,22,24]. Therefore, to improve the repeatability by avoiding this  
 18 issue, the specimens were always printed over the first 1.4 mm thick sand layer deposited in the job-  
 19 box bottom, thin enough to neglect compressibility issues and sub-layer displacements [21].  
 20  
 21  
 22  
 23  
 24  
 25  
 26  
 27  
 28

29 **Table 1** : Dimensions, quantity, and orientations of specimens printed in each job box.  
 30

Specimen	Dimensions (mm)	Direction	Number
Bar (for 3PB test)	22.4 x 22.4 x 172	X	18
		Y	14
Cylinder (for permeability test)	Diameter = 50 Height = 50	X	12
		Y	12
		Z	12

31  
 32  
 33  
 34  
 35  
 36  
 37  
 38  
 39 **Table 2** :3D printing process parameters for the sand specimens.  
 40

Average sand grain size	140 $\mu\text{m}$
Activator content	0.18 wt.% <sup>§</sup>
Inhibitor content	0.4 wt. % <sup>**</sup>
Print head voltage	78 V
Layer thickness	280 $\mu\text{m}$
Heating temperature	305 K
Print resolution	120 - 140 $\mu\text{m}$
Recoater speed	130 - 286 $\text{mm}\cdot\text{s}^{-1}$

### 41 *Specimen Characterization*

42  
 43 The three-point bending tests were carried out on the printed sand bars. The test fixture †† (Fig. 3b),  
 44 consisted of two supporting pins at 150 mm distance apart. A third pin applied a load at a rate of 0.1  
 45  
 46  
 47  
 48  
 49  
 50

51  
 52  
 53  
 54  
 55  
 56  
 57  
 58 <sup>§</sup> Of the sand weight.

59 <sup>\*\*</sup> Of the sand weight.  
 60  
 61  
 62  
 63  
 64  
 65

1 MPa.s<sup>-1</sup>, at the mid-length of each specimen, using an electric motor with a maximum load capacity of  
2 12.8 MPa. The reading uncertainty on the pressure gauge was ±0.05 MPa.  
3  
4

5 The mold permeability measurement was performed on the cylindrical specimens using a digital  
6 permeability meter<sup>††</sup> with a measuring range from 0 to 1000 GP with ±1 GP uncertainty. The orifice  
7 standard method was applied as per the recommendations of American Foundry Society (AFS). The  
8 gas permeability<sup>§§</sup>, *GP*, was given by:  
9  
10

$$11 \quad GP = \frac{Q \times h}{S \times p \times t} \quad (1)$$

12 , where *Q* is the air volume in the chamber (2000 cm<sup>3</sup>), *h* is the height (5 cm) of the specimen (Fig.  
13 3a), *S* is the specimen cross sectional area (19.63 cm<sup>2</sup>), and *t* the passage time for the 2000 cm<sup>3</sup> of air  
14 (in minutes).  
15  
16

17 The density was measured on the mold sample with maximum volume, that was the volume of a  
18 cylinder (98.13 cm<sup>3</sup>) to average the sand packing errors from printing process. The porosity was then  
19 evaluated by :  
20  
21

$$22 \quad Porosity(\%) = \left(1 - \frac{\text{apparent density}}{\text{bulk density}}\right) \times 100 \quad (2)$$

23 , where the bulk density was taken as the theoretical density of SiO<sub>2</sub>-quartz (2648 kg·m<sup>-3</sup>), constituting  
24 99.1% of the sand used in the printer.  
25  
26

27 Lost-on-ignitions (LOI) tests were finally performed on smalls cube of 10 mm side printed with the  
28 same parameters than the studied bars and cylinders. Measurements were provided by weighting the  
29 specimens before and after LOI tests performed at 1273 K in a furnace.  
30  
31  
32

### 33 *Statistically Designed Experiments*

34 The permeability, strength, and density values of the printed specimens were implemented into a  
35 statistical model in order to quantify the process parameter effects. A two-level four-parameter  
36 factorial analysis is a good approach to scientifically establish the individual and combined effects of  
37 the two-level factors on the responses. The experiments were designed and carried out using six  
38 responses influenced by four factors, i.e. four process parameters. The six response variables were the  
39 permeabilities along X, Y, and Z, the strength of bars printed along X and Y directions, and the  
40  
41  
42

---

43 †† Simpson® Technologies brand

44 †† Simpson® Technologies brand

45 §§ This is not the standared gas permeability definition according to Darcy law and hence does not have the SI  
46 unit of gas permeability but is used in the foundry industries, recomended by AFS.  
47  
48

1 density of the printed specimens. No bars along the Z-direction were printed to limit the height and  
2 the cost of each printed job-box.  
3

4  
5 The factors were the position X and Y in the job box, the recoater speed (RS), and print resolution  
6 ( $X_R$ ). Only the mold samples at the job box corners were used for the statistical experiments. The  
7 factors were selected to form a two-level L16 orthogonal array experiment (Table 3). The parameter  
8 levels were chosen after a preliminary research in order to expect a linear relationship between the  
9 responses and the experiment variables. The most influential factors were selected to model the  
10 printing process. The effect of the selected process parameters on the responses were calculated using  
11 a statistical approach. The standard error of the responses and the additional measurements to validate  
12 the models were quantified by printing several job-boxes with the parameters of 120  $\mu\text{m}$  ( $X_R$ ) and 234  
13  $\text{mm}\cdot\text{s}^{-1}$  (RS).  
14  
15  
16  
17  
18  
19  
20  
21  
22

23 **Table 3:** Process parameters with their ranges and values at two levels.  
24

Parameter Designation	Process Parameter	Range	Level 1	Level 2
X	X-position in job box (mm)	50 – 750	50	750
Y	Y-position in job box (mm)	50 – 450	50	450
$X_R$	Print Resolution ( $\mu\text{m}$ )	120 – 140	120	140
RS	Recoater Speed ( $\text{mm}\cdot\text{s}^{-1}$ )	130 – 286	130	286

### III. RESULTS

#### *Repeatability*

Job-boxes with the parameters of 120  $\mu\text{m}$  ( $X_R$ ) and 234  $\text{mm}\cdot\text{s}^{-1}$  (RS), which were within the factorial analysis range, were printed to evaluate the repeatability of the measurements and the residual errors of the models. The repeatabilities in the measurements were  $\pm 10 \text{ kg}\cdot\text{m}^{-3}$  (density),  $\pm 4 \text{ GP}$  (permeability), and  $\pm 0.10 \text{ MPa}$  (3PB strength). These values served as a benchmark to identify the influential parameters during the statistically designed experiments.

#### *Process Parameters Effects*

The measured values of the responses, i.e. permeabilities ( $P_X$ ,  $P_Y$ , and  $P_Z$ ), flexural strength ( $\sigma_X$  and  $\sigma_Y$ ), and density ( $\rho$ ), were used to build the mathematical models for the 3D printer\*\*\* characterization and are summarized in the Appendix. The linear regression analysis for each response when considering up to the 1<sup>st</sup> order combined effects were summarized in Table 4. Residual errors were calculated by ignoring the 2<sup>nd</sup> to 4<sup>th</sup> order combined effects. Applying the mathematical model with the coefficients listed in Table 3 to the initial printing conditions lead to maximum residual errors of  $\pm 9 \text{ GP}$ ,  $\pm 0.11 \text{ MPa}$ , and  $\pm 8 \text{ kg}\cdot\text{m}^{-3}$  for permeability, flexural strength, and density, respectively.

**Table 4** : Coefficients of process parameter effects on permeability, flexural stress, and density.

Parameters	Identifiers	$P_X$ (GP <sup>†††</sup> )	$P_Y$ (GP)	$P_Z$ (GP)	$\sigma_X$ (MPa)	$\sigma_Y$ (MPa)	$\rho$ ( $\text{kg}\cdot\text{m}^{-3}$ )
Average	M	115.6	97.1	98.6	1.913	1.969	1311
X	A	-10.3	-9.8	-10.4	0.119	0.106	22
Y	B	-2.8	-1.1	-3.2	0.157	0.069	3
$X_R$	C	0.8	0.5	-0.9	-0.206	-0.238	-2
RS	D	19.9	15	19.8	-0.325	-0.406	-4.8
X-Y	AB	0.6	2.3	0.8	0.038	0.043	3
X- $X_R$	AC	-3.3	-3.8	-1.2	-0.013	0.025	3
X-RS	AD	-5.9	-4.6	-5.9	0.056	0.056	9
Y- $X_R$	BC	-0.1	0	-0.4	-0.075	-0.013	-3
Y-RS	BD	-1.9	-2.5	-3.6	0.069	0.006	3
$X_R$ -RS	CD	-1.3	-2.3	-2.9	0.069	0.038	6
<i>Maximum residual errors</i>		6	9	4	0.11	0.09	8
<i>Minimum</i>		89.7	72.3	71.7	1.175	1.156	1226
<i>Maximum</i>		159.9	134.4	144.7	2.788	2.794	1383

\*\*\* ExOne's S-Print™

††† Commonly used AFS number for gas permeability of sand mold, but does not have the SI or proper scientific unit.



1  
2  
3  
4 The most effective factors affecting the printed sample characteristics were the job box positions X  
5 and Y, and the recoater speed RS. They are believed to impact the density which is a key factor for  
6 the permeability and strength. Nevertheless, the  $X_R$  parameter significantly affected only the strength  
7 of mold samples.  
8  
9

10 While permeability is primarily influenced by the sand grain size and shape, the sand compaction, and  
11 the amount of binder [15], this study revealed that the effect of the binder amount was negligible in  
12 regards to the sand compaction. This may be due to the fact that the binder quantity was varying from  
13 approximately 1.9 to 2.2 wt.% (according to LOI tests), which may be too small to effectively affect  
14 the number of inter-grain cavities filled by the binder. Therefore, the impact of binder amount on  
15 permeability was within the noise of the permeability measurements.  
16  
17  
18  
19  
20  
21  
22  
23  
24

### 25 ***Sand Mold Properties***

26 Sand mold properties (Table 3) varied within the factorial analysis parameters with a wide range of 70  
27 to 160 GP and 1.1 to 2.8 MPa. The density varied from 1226 to 1383  $\text{kg}\cdot\text{m}^{-3}$ , which represented a  
28 porosity variation from 48 to 54 %.  
29  
30

31 The average value of sample densities of 1331  $\text{kg}\cdot\text{m}^{-3}$  agreed with another study [12]. The sand  
32 compaction was mainly controlled by the RS parameter and the position in the jobbox. The observed  
33 heterogeneous compaction of sand grains within a single job box agreed with another work [30]. The  
34 effect of  $X_R$  parameter (value of -2) was negligible. Even though the density of the furfuryl alcohol  
35 (1130  $\text{kg}\cdot\text{m}^{-3}$ ) was not negligible, its small variation in quantity did not play a significant role in the  
36 total weight of the samples. Indeed, lost-on-ignition measurements performed at 1273 K revealed a  
37 furan content variation from 1.9 wt.% ( $X_R = 140\mu\text{m}$ ) to 2.3 wt.% ( $X_R = 120\mu\text{m}$ ), slightly higher than  
38 LOI measurements of other studies [5,33]. Such variation corresponded to a variation of  $\pm 0.002$  wt.%,  
39 in agreement with the -2 value of the  $X_R$  parameter for density modeling.  
40  
41  
42  
43  
44  
45  
46  
47  
48

49 The model for permeabilities had numerous similitudes with the density model, that were strong X and  
50 RS parameters, smaller Y parameter, and negligible  $X_R$  parameter. A strong correlation between  
51 density and permeability was observed (Fig. 4) with a linear dependance of permeability with density  
52 and a saturation of the permeabilities above 1360  $\text{kg}\cdot\text{m}^{-3}$ . Fitting the data lead to Eq. 3 :  
53  
54  
55

$$56 \quad P = -0.429 \cdot \rho + D \quad (R^2=0.83) \quad (\text{Eq.3})$$

57  
58  
59  
60  
61  
62  
63  
64  
65

1 , where  $D$  is a constant that equals 678 for  $P_X$  and 661 for  $P_Y$  and  $P_Z$ . The offset of 17 GP between the  
 2  $P_X$  values on one side and the  $P_Y$  and  $P_Z$  values on the other side remains unclear. The favorable air  
 3 flow along X than Y and Z was surprising. We would have expected a different Z permeability  
 4 because of the layer-by-layer deposition (X-Y plane) manufacturing mode. This is believed to be due  
 5 to the compaction that is performed by an oscillating blade located beneath the recoater. The sand  
 6 compaction could vary in the Y recoating direction according to the sandwave distributed ahead of the  
 7 oscillating compacting blade. The pressure exerted along Y and Z should organize the grains in such a  
 8 heterogeneous way that porosities were more oriented along the X direction, leading to anisotropic  
 9 permeability.  
 10

11 The mold flexural strength did not depend significantly on the printing direction (X or Y) in the  
 12 deposition plane and was greater for high compaction (obtained by small RS values in the 130-182  
 13 mm·s<sup>-1</sup> range), high furan amount (obtained at small  $X_R$  values of 120 μm), and towards the  $X_0Y_0$   
 14 corner. Slowing the recoater speed increased the sand density inducing greater flexural strength, in  
 15 agreement with other works [12]. The flexural strength values varied from 1.12 to 2.76 MPa with  
 16 standard deviation up to 0.24 MPa, in agreement with other publications on ExOne S-Print™ [5] and  
 17 ZCorp printer [9] and greater than traditional furan sand mold samples [33]. Strength heterogeneity in  
 18 the job box was in agreement with another studies [26,34] and was associated to the sand density  
 19 variation, as highlighted by Fig 5 and Eq. 4:  
 20

$$21 \quad \sigma = 0.743 \cdot \rho - 781.1 \quad (R^2=0.72) \quad (\text{Eq. 4})$$

22 The standard deviation around this linear trend was ±0.25 MPa. This was due to the  $X_R$  effect, not  
 23 included in the present graph. Indeed, the ±0.25 MPa was very close to the  $X_R$  effect for stress models,  
 24 that is -0.206 and -0.238 MPa for  $\sigma_x$  and  $\sigma_z$ , respectively. However, the effect of a Y-parameter was  
 25 not clear. Such a dependence of the strength with the binder deposition axis has been related in other  
 26 works to a preferential spreading of the binder towards the printhead movement direction due to the  
 27 impact trajectory of the droplet [34,35]. This may not be the case in the present work because the  
 28 impact trajectory of the droplet is composed of a fast Y-velocity component (Y-direction printhead  
 29 movement). Therefore, it is believed that the Y-variation of the printed sample stress may be related  
 30 to the binder preferential spreading on a less compacted sand (towards  $Y_{500}$  positions).  
 31

32 Finally, a strong correlation existed between the flexural stress and permeability, as indicated in Fig. 6.  
 33 The relationship was given by :

$$34 \quad P = -0.43 \cdot \sigma + 189.6 \quad (R^2=0.53) \quad (\text{Eq. 7})$$

Albeit a small coefficient of determination, the trend given by Eq. 7 was valid up to 2.4 MPa flexural stresses, after which permeability remains unchanged at 95 and 76 GP along X and Y, respectively. This was directly due to the saturation effect observed in Fig. 3.

### ***Heterogeneity of Properties***

The sample properties depended upon their position in the job box, in agreement with previous works [11,24,36]. The heterogeneity in a job box was quantified by analyzing statistically the measured properties of the printed specimens in each job box (Fig. 2). The equations for the standard deviation of permeability ( $S_p$ ), flexural strength ( $S_\sigma$ ) and density ( $S_\rho$ ) were given by:

$$S_p = 10.6 + 1.8FDS + 4.7RS + 2.64(FDS - RS) \quad (\text{Eq. 4})$$

$$S_\sigma = 0.203 + 0.003FDS + 0.021RS + 0.021(FDS - RS) \quad (\text{Eq. 5})$$

$$S_\rho = 23.8 + 2.8FDS + 9.3RS + 8.3(FDS - RS) \quad (\text{Eq. 6})$$

The homogeneity in properties in the same job box was strongly affected by the RS parameter, meaning that slow recoater speeds, i.e. slow sand layer deposition, enabled the manufacturing of a job box with homogeneous sample characteristics. The measured sand specimen properties were most homogeneous in the Y-building direction rather than the X-direction, the reason being possibly related to the observed RS-X combined effect induced by the printer design. Indeed, the sand compaction depended on the X position in the job-box, the recoater speed, and the interaction of these two parameters. The sand was deposited by a recoater movement from  $Y_{500}$  to  $Y_0$ . The screw conveyor in the recoater transported the sand from the sand container ( $X_{800}$ ) to the recoater extremity ( $X_0$ ). This X-dependence upon sand compaction cannot be related to the distribution of the sand by the screw conveyor as the sand height in the conveyor was continuously controlled and maintained constant. Therefore the outwards sand flow variations along the X-direction was believed to be due to a variation of the front-blade spacing of the conveyor. Therefore, the present results justified a slight modification in the front-blade spacing adjustment by enlarging this spacing near the  $X_0$  position to increase the local flow of the sand deposition.

## **IV. DISCUSSION**

Printing sand molds using the ExOne's S-Print™ was performed in order to validate permeability and strength requirements. A minimum nominal strength is required for an easy manipulation of the mold and good dimensional accuracy of the casting. This rigidity should be obtained with a minimum

binder resolution ( $X_R = 140 \mu\text{m}$ ), that means small Loss-On-Ignition values, to reduce the off-gassing that hinders the filling of the sand mold cavity [5,13,14,29].

The volume of gas evolved is proportional in part to the amount of binder present in the printed mold [28]. Sufficient permeability is necessary to allow the escape of gases produced when the molten metal heats the internal surface of the mold cavity. Therefore a balance must be found between strength and permeability as an increase of the sand density simultaneously increases the mold strength and reduced the mold permeability (Table 3) and was in agreement with another similar study [35].

Various 3D machine settings exist regarding print resolution, recoater speed, and mold position which will give optimised sand mold properties in terms of a particular permeability-strength combination. The algorithm for setting the printer parameter values is an iterative procedure that determines first if the permeability and strength requirements for the sand mold are simultaneously achievable, followed by a minimization of the furan content.

In the present work the aim is to obtain a minimum sand mold strength of 1.8 MPa with the greatest permeability and smallest furan content. By fixing the  $X_R$  parameter to +1 (140  $\mu\text{m}$ ), the lower flexural stress value of 1.80 MPa in  $X_0Y_0$  corner ( $X=Y=-1$ ) is reached for both X- and Y-stresses at recoater speed values slower than  $158 \text{ mm}\cdot\text{s}^{-1}$  (corresponding to  $RS=-0.64$ ).

Fixing  $X_R$  and  $RS$  values to +1 and -0.64, respectively, the sand mold sample properties in the job box are calculated (Table 5) and compared to measured properties in a job box printed in the same conditions (Table 6). The mathematical model fits approximatively the real sand mold properties. However, the residual error is greater for permeability and density, suggesting that the compaction effect is the main error in the model. This is believed to be due to a non-perfectly linear sand compaction magnitude in relation to the recoater speed. Therefore the authors suggest that, while X, Y, and  $X_R$  parameters can be kept as two-level factors, the  $RS$  parameter must be studied at least as a three-level factor for future investigations.

**Table 5** : Calculated mold sample properties for  $X_R$  and  $RS$  values of 140  $\mu\text{m}$  and  $158 \text{ mm}\cdot\text{s}^{-1}$  according to the model proposed in Table 3.

X	Y	$P_X$ (GP)	$P_Y$ (GP)	$P_Z$ (GP)	$\sigma_X$ (MPa)	$\sigma_Y$ (MPa)	$\rho$ ( $\text{kg}\cdot\text{m}^{-3}$ )
-1	-1	115	101	96	1.81	1.87	1324
1	-1	95	76	79	1.87	1.98	1356
-1	1	111	100	92	1.81	1.89	1314
1	1	93	81	78	2.02	2.16	1358

<b>Average</b>	93.1	1.92	1338
<b>Standard deviation</b>	12.8	0.12	22

**Table 6 :** Measured mold sample properties for  $X_R$  and RS values of  $140 \mu\text{m}$  and  $158 \text{mm}\cdot\text{s}^{-1}$

<b>X</b>	<b>Y</b>	<b>P<sub>X</sub>(GP)</b>	<b>P<sub>Y</sub>(GP)</b>	<b>P<sub>Z</sub>(GP)</b>	<b><math>\sigma_x</math> (MPa)</b>	<b><math>\sigma_y</math> (MPa)</b>	<b><math>\rho</math> (<math>\text{kg}\cdot\text{m}^{-3}</math>)</b>
-1	-1	98	78	76	1.70	1.85	1341
1	-1	93	71	69	1.85	1.90	1382
-1	1	96	77	80	1.85	1.90	1338
1	1	85	65	66	2.20	2.00	1385
<b>Average</b>		79.5			1.91		1362
<b>Standard deviation</b>		11.4			0.15		25

## V. CONCLUSIONS

The measured properties of the 3D printed furan sand molds were analyzed using the statistical design of experiments to identify the important factors. Mathematical models revealed that the mold properties were dependent upon the process parameters, such as recoater speed and print resolution, and their positions, within the job box, during printing. While the recoater speed influenced both strength and permeability, the print resolution only affected the mold strength at the current settings. An optimization procedure is proposed by setting the flexural stress of mold samples at 1.80 MPa or above (an arbitrary value) with a minimum furan amount. The model proposed for the 3D printer was validated by measuring the properties of the sand specimens at the determined printing conditions. **If small permeabilities are accepted for sand molds, slow recoater speeds can be used. However, if sand molds are manufactured with a high permeability using fast recoater speeds, it leads unfortunately to anisotropic properties of the sand specimens within a given job-box. Novel findings of this paper include in particular the quantification of the printing parameters effect on the characteristics of the sand mold specimens. Moreover, the machine model enables to calculate the different permeability-strength couples achievable by our ExOne S-Print™ machine.**

Although the statistical analysis provides a best-fitting linear regression for strength and permeability of the printed sand specimens in relation to the 3D printer settings, what is of particular importance here is the ability to control them independently, up to a limit, to predict the permeability and strength properties. Nevertheless, the effect of the printing parameters on the casting properties needs to be investigated. Therefore future work will focus on the consequence of sand mold manufacturing conditions on the casting properties, as flexural strength and permeability values for the sand mold are

1 achievable with different values of recoater speed and print resolution. In addition, the consideration  
2 of the Z-direction for flexural strength, which may be a weak direction, must be analyzed with future  
3 mold printings.  
4  
5  
6  
7  
8  
9

## 10 **VI. ACKNOWLEDGEMENTS**

11 The authors acknowledge the help of the following colleagues at Arts et Métiers ParisTech. Thanks  
12 are due to J. Bourgeois for his technical support on 3D printing and M. Pons for his advice on  
13 statistical designs.  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23

## 24 **VII. REFERENCES**

- 25  
26  
27  
28 [1] Dimitrov D, Schreve K, de Beer N, Chritiane P. Three dimensional printing in the South  
29 African industrial environment. *South African J ...* 2008;19:195–213.  
30  
31 [2] Sachs E, Cima M, Cornie J, Brancazio D. Dimensional Printing: Rapid Tooling and Prototypes  
32 Directly from CAD Representation. *Solid Free Fabr Symp* 1990:27–47. doi:10.1016/S0007-  
33 8506(07)61035-X.  
34  
35 [3] Travitzky N, Bonet A, Dermeik B, Fey T, Filbert-Demut I, Schlier L, et al. Additive  
36 manufacturing of ceramic-based materials. *Adv Eng Mater* 2014;16:729–54.  
37 doi:10.1002/adem.201400097.  
38  
39 [4] Singamneni S, Diegel O. Some recent developments and experiences with Rapid  
40 Manufacturing by indirect means. *Asian Int J Sci Technol Prod Manuf Eng* 2010;3:7–14.  
41  
42 [5] Snelling D, Williams CB, Druschitz AP. A Comparison of Binder Burnout and Mechanical  
43 Characteristics of Printed and Chemically Bonded Sand Molds. *SFF Symp* 2014:197–209.  
44  
45 [6] Stefanic I, Raos P, Samardzic I, Tintor B, Musser E. Rapid Prototyping of Casting Cores. *Teh*  
46 *Vjesn Gaz* 2012;19:459–64.  
47  
48 [7] Budzik G. Possibilities of utilizing 3DP technology for foundry mould making. *Arch Foundry*  
49 *Eng* 2007;7:65–8.  
50  
51 [8] Drokina V V., Belov VD, Chekhonin SN. Obtaining casts of aluminum alloys by foundry in  
52  
53  
54  
55  
56  
57  
58  
59

- 1 loose molds fabricated on installations of three-dimensional printing. *Russ J Non-Ferrous Met*  
2 2011;52:24–8. doi:10.3103/S1067821211010081.
- 3  
4
- 5 [9] Koltygin A V., Bazhenov VE. Development of a Substitute for Z Cast Molding Sand Used on  
6 Installations of 3D Printing for Obtaining Aluminum, Magnesium, and Iron Casting. *Russ J*  
7 *Non-Ferrous Met* 2012;53:38–41. doi:10.3103/S1067821212010129.
- 8  
9
- 10 [10] Kumar R, Ahuja IPS, Singh R. Experimental and Analytical Analysis of Light Alloy Shell  
11 Castings Using Three Dimensional Printing 2014;2:650–62.
- 12  
13
- 14 [11] Gill SS, Kaplas M. Efficacy of powder-based three-dimensional printing (3DP) technologies  
15 for rapid casting of light alloys. *Int J Adv Manuf Technol* 2011;52:53–64.
- 16  
17
- 18 [12] Bobby SS. A PRELIMINARY INVESTIGATION OF GYPSUM BONDED MOULDS BY  
19 THREE DIMENSIONAL PRINTING 2014:501–7.
- 20  
21
- 22 [13] Hościło B, Kaczyński R, Skorulski G. Rapid Prototyping Technology Using for Casting  
23 Process of Mini Turbine Runner. *Arch Foundry Eng* 2014;14:83–6.
- 24  
25
- 26 [14] Snelling D, Li Q, Meisel N, Williams CB, Batra RC, Druschitz AP. Lightweight metal cellular  
27 structures fabricated via 3D printing of sand cast molds. *Adv Eng Mater* 2015;17:923–32.  
28 doi:10.1002/adem.201400524.
- 29  
30
- 31 [15] Mckenna N, Singamneni S, Diegel O, Singh D, Neitzert T, George JS, et al. Direct Metal  
32 casting through 3D printing : A critical analysis of the mould characteristics. 9th Glob Congr  
33 Manuf Manag 2008:12–4.
- 34  
35  
36
- 37 [16] Motoyama Y, Inoue Y, Saito G, Yoshida M. A verification of the thermal stress analysis,  
38 including the furan sand mold, used to predict the thermal stress in castings. *J Mater Process*  
39 *Technol* 2013;213:2270–7. doi:10.1016/j.jmatprotec.2013.06.024.
- 40  
41  
42
- 43 [17] Motoyama Y, Takahashi H, Inoue Y, Shinji K, Yoshida M. Dymanic Measurements of the  
44 Load on Castings and the Contraction of Castings During Cooling in Sand Molds. *J Mater*  
45 *Process Technol* 2013;213:238–44.
- 46  
47
- 48 [18] Nyembwe K, de Beer DJ, van der Walt JG, Bhero S. Assessment of Surface Finish and  
49 Dimensional Accuracy of Tools. *South African J Ind Eng* 2012;23:130–43.
- 50  
51
- 52 [19] Singh R. Three Dimensional Printing for Casting Applications: A State of Art Review and  
53 Future Perspectives. *Adv Mater Res* 2009;83–86:342–9.  
54 doi:10.4028/www.scientific.net/AMR.83-86.342.
- 55  
56
- 57 [20] Ollison T, Berisso K. Three-Dimensional Printing Build Variables That Impact Cylindricity. *J*  
58

- 1 Ind Technol 2010;26:1–10.
- 2
- 3
- 4 [21] Lee S-JJ, Sachs E, Cima M. Layer position accuracy in powder-based rapid prototyping. *Rapid*
- 5 *Prototyp J* 1995;1:24–37. doi:10.1108/13552549510104447.
- 6
- 7 [22] Lee S-JJ, Sachs E, Cima M. Powder layer position accuracy in powder-based rapid
- 8 prototyping. *Best Available* 1993:223.
- 9
- 10 [23] Brabazon D, Kennedy D, Tyrell M. Development of technique for 3D printed mould intricate
- 11 rapid casting. *Solid Free. Fabr. Symp.*, 2010, p. 800–8.
- 12
- 13 [24] Dimitrov D, Beer N De. Developing Capability Profile for the Three Dimensional Printing
- 14 Process. *R D J* 2006;22:17–25.
- 15
- 16 [25] Snelling D, Blount H, Forman C, Ramsburg K, Wentzel A, Williams C, et al. The effects of 3D
- 17 printed molds on metal castings. *Solid Free Fabr Symp* 2013:827–45.
- 18
- 19 [26] Frascati J. Effects of position, orientation, and infiltrating material on three-dimensional
- 20 printing models. 2007.
- 21
- 22 [27] Vaezi M, Chua CK. Effects of layer thickness and binder saturation level parameters on 3D
- 23 printing process. *Int J Adv Manuf Technol* 2011;53:275–84. doi:10.1007/s00170-010-2821-1.
- 24
- 25 [28] Castings n.d.
- 26
- 27 [29] Meisel N a., Williams CB, Druschitz A. Lightweight Metal Cellular Structures via Indirect 3D
- 28 Printing and Casting. *Solid Free. Fabr. Symp.*, 2012, p. 162–76.
- 29
- 30 [30] Budding A, Vaneker THJ. New strategies for powder compaction in powder-based rapid
- 31 prototyping techniques. *Procedia CIRP* 2013;6:527–32. doi:10.1016/j.procir.2013.03.100.
- 32
- 33 [31] Renhe H, Hongmei G, Yaoji T, Qingyun L. Curing mechanism of furan resin modified with
- 34 different agents and their thermal strength. *China Foundry* 2011;8:161–5.
- 35
- 36 [32] Sivarupan T, Mansori MEL, Coniglio N. 3D Printing Process Parameters and Properties of
- 37 Additively Manufactured Sand Mold for Rapid Casting: Strength and Permeability. *Addit*
- 38 *Manuf* 2017.
- 39
- 40 [33] Hussein NIS, Ayof MN, Sokri NIM, Engineering M. Mechanical Properties and Loss on
- 41 Ignition of Phenolic and Furan Resin Bonded Sand Casting 2013;1:1–5.
- 42
- 43 [34] Galeta T, Kladarić I, Karakašić M. Influence of Processing Factors on Tensile Strength of 3D
- 44 Printed Models. *Strojarstvo* 2011;47:781–8.
- 45
- 46 [35] Farzadi A, Waran V, Solati-Hashjin M, Rahman ZAA, Asadi M, Osman NAA. Effect of layer
- 47
- 48
- 49
- 50
- 51
- 52
- 53
- 54
- 55
- 56
- 57
- 58
- 59



printing delay on mechanical properties and dimensional accuracy of 3D printed porous prototypes in bone tissue engineering. *Ceram Int* 2015;41:8320–30. doi:10.1016/j.ceramint.2015.03.004.

[36] Szucs TD, Brabazon D. Analysis of the effects of 3DP parameters on part feature dimensional accuracy. *Solid Free. Fabr. Symp. Proc.*, 2007, p. 470–81.

## VIII. APPENDIX

**Table A.1** : Average values of permeability, flexural stress, and density for various process parameters.

Level of Process Parameters				$P_X$ (GP)	$P_Y$ (GP)	$P_Z$ (GP)	$\sigma_X$ (MPa)	$\sigma_Y$ (MPa)	$\rho$ ( $\text{kg}\cdot\text{m}^{-3}$ )
X	Y	$X_R$	RS						
-1	-1	-1	-1	95.94	81.38	79.94	2.31	2.59	1358
1	-1	-1	-1	92.69	74.38	71.69	2.39	2.56	1370
-1	1	-1	-1	93.19	79.63	80.19	2.56	2.66	1358
1	1	-1	-1	92.19	81.63	75.19	2.79	2.79	1383
-1	-1	1	-1	106.94	94.88	87.19	1.94	2.02	1343
1	-1	1	-1	90.44	72.38	74.19	1.96	2.08	1368
-1	1	1	-1	103.94	93.13	85.69	1.89	2.03	1330
1	1	1	-1	89.69	79.63	75.94	2.06	2.27	1368
-1	-1	-1	1	154.19	130.38	144.69	1.28	1.58	1225
1	-1	-1	1	127.19	104.88	112.69	1.58	1.77	1275
-1	1	-1	1	143.69	118.63	130.19	1.80	1.67	1238
1	1	-1	1	118.94	102.13	101.44	2.25	2.03	1300
-1	-1	1	1	159.94	134.38	140.19	1.18	1.16	1233
1	-1	1	1	119.69	93.38	103.44	1.43	1.44	1295
-1	1	1	1	149.19	122.63	123.94	1.40	1.19	1233
1	1	1	1	111.19	90.63	90.44	1.80	1.66	1308

## LIST OF FIGURES

---

**Fig. 1:** Overview of 3D sand mold printer.


**Fig.2:** Top view of the job-box design.

**Fig. 3:** Schematic of (a) the direction of permeability test on the X, Y and Z cylindrical specimens and (b) the 3PB test specimen. [32].


**Fig. 4:** Relationship between density and permeability for x-, y-, and z- oriented specimens.

**Fig. 5:** Relationship between density and 3PB strength for x-, y-, and z- oriented specimens.

**Fig. 6:** Relationship between 3PB strength and permeability for x- and y-oriented specimens.

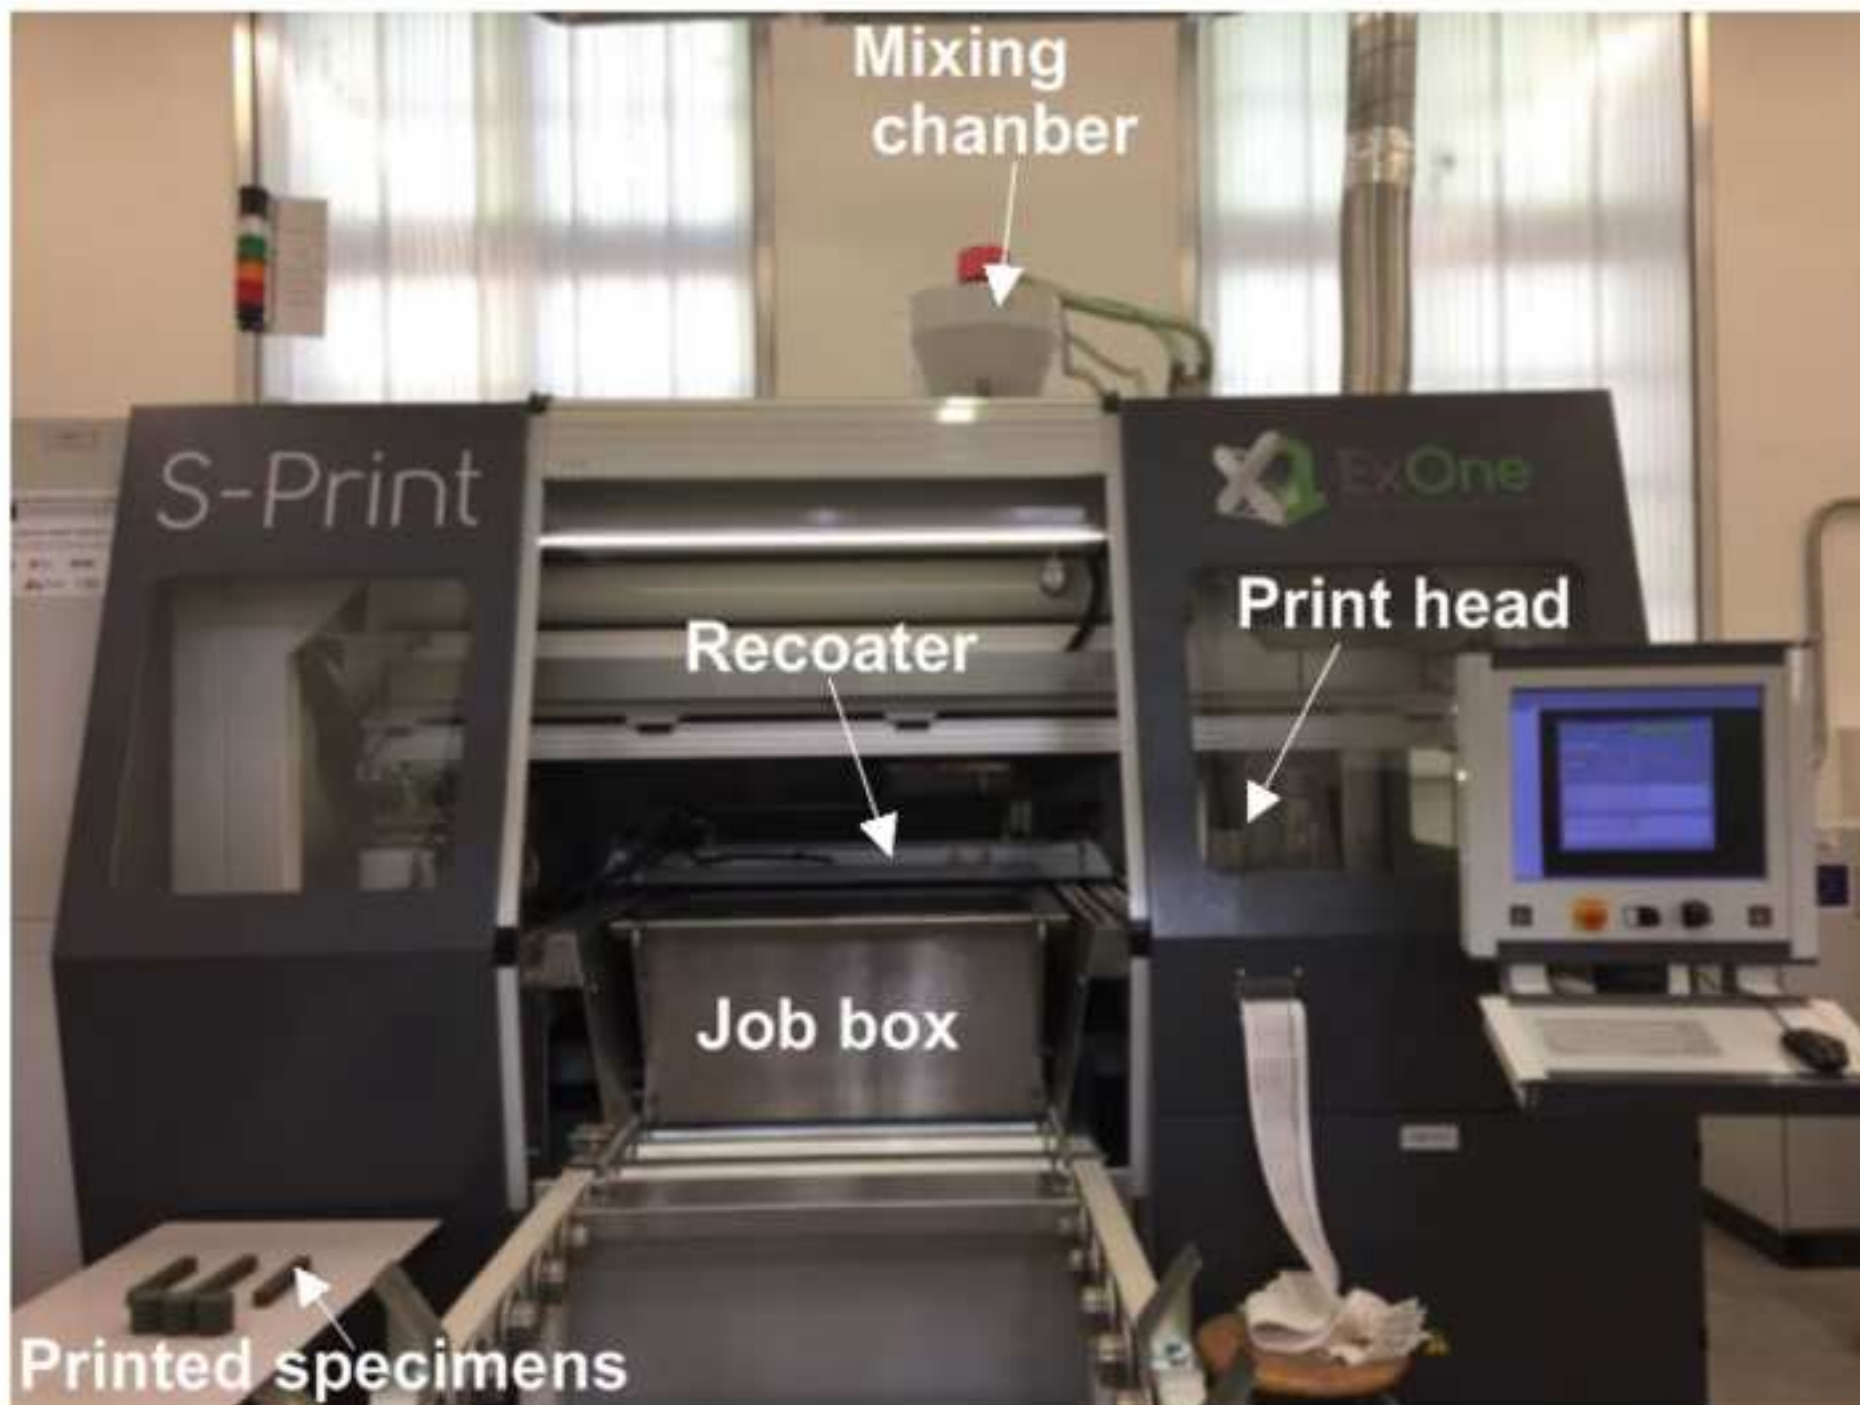



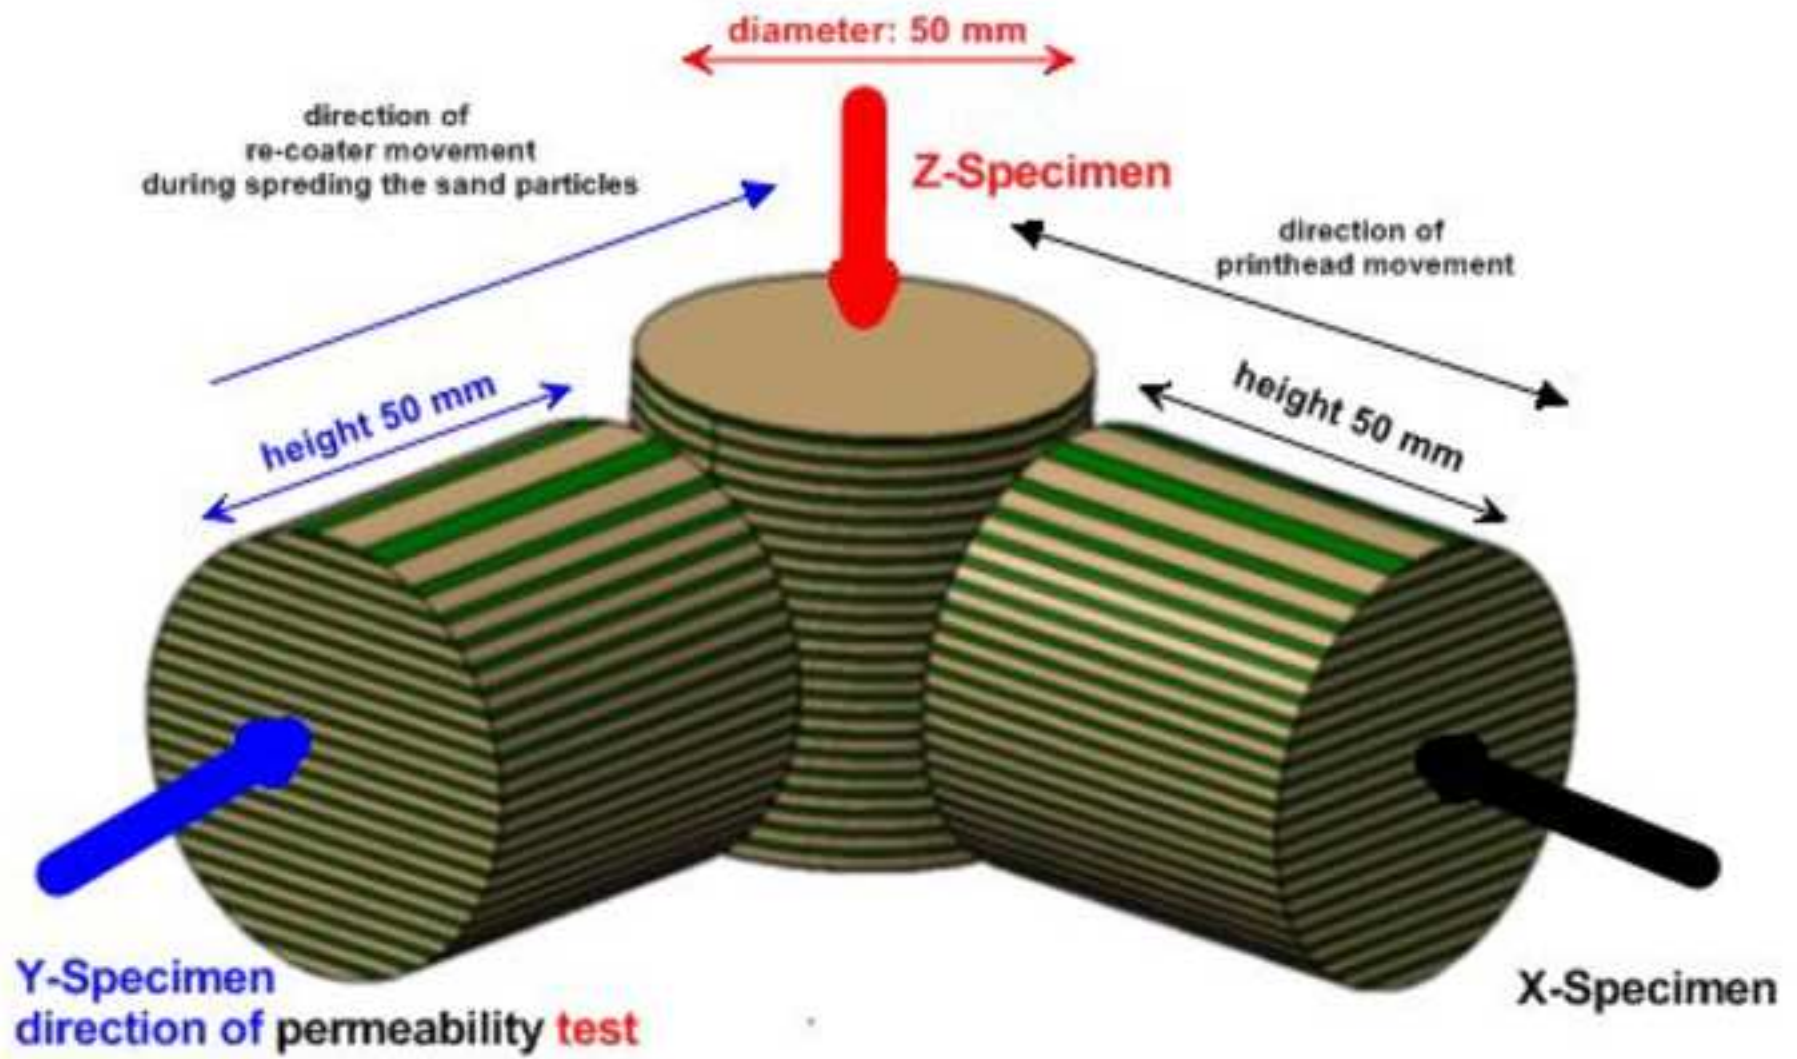

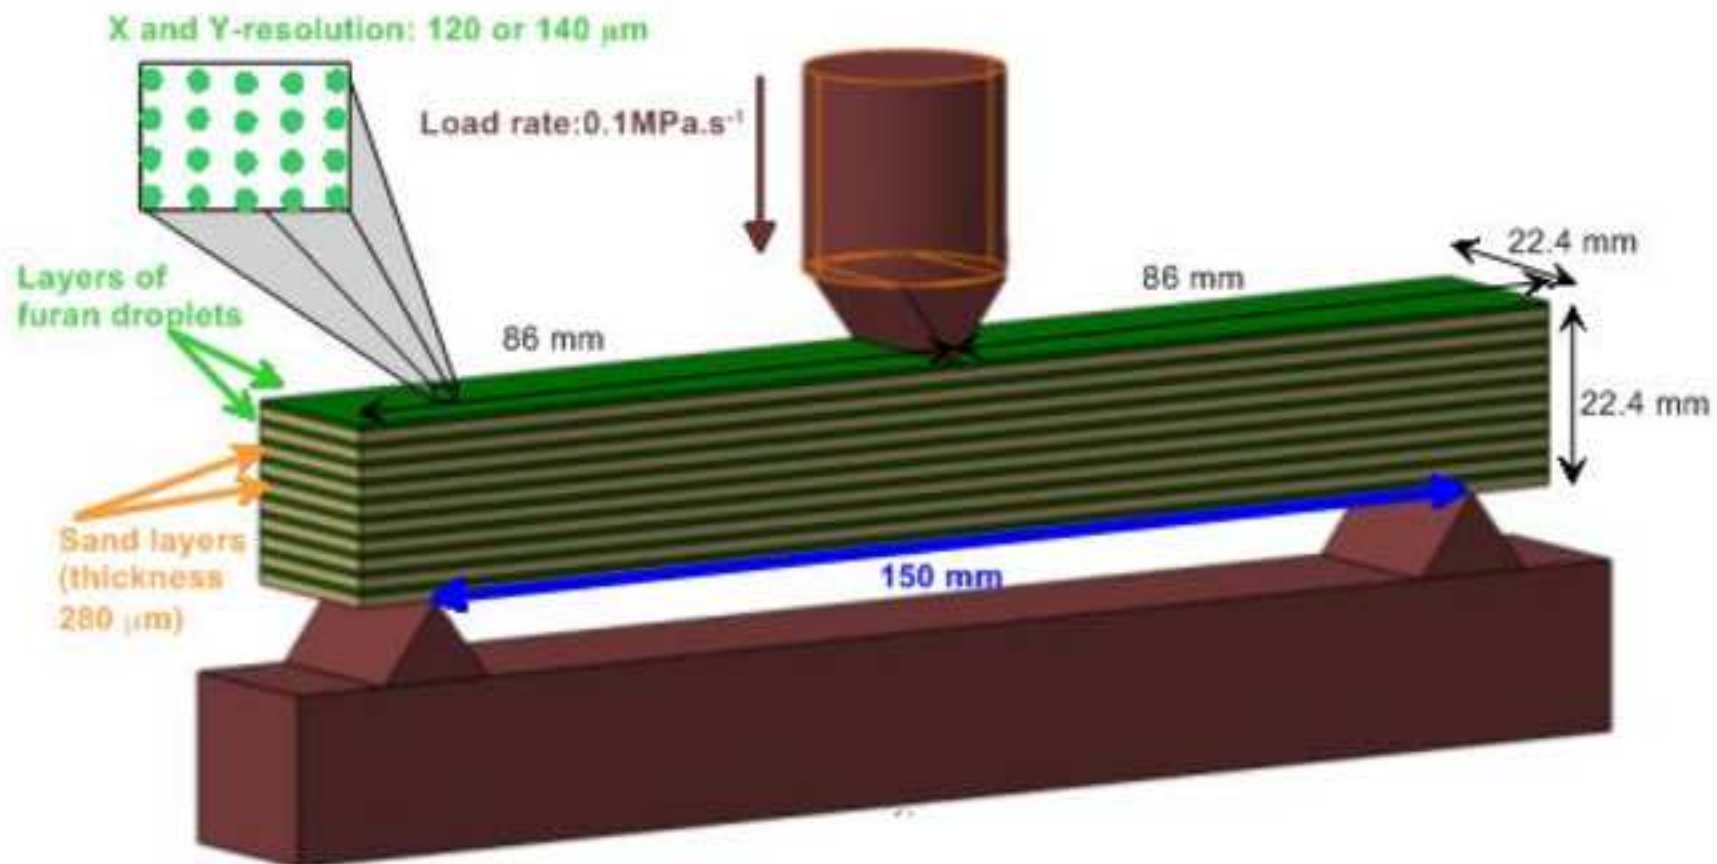
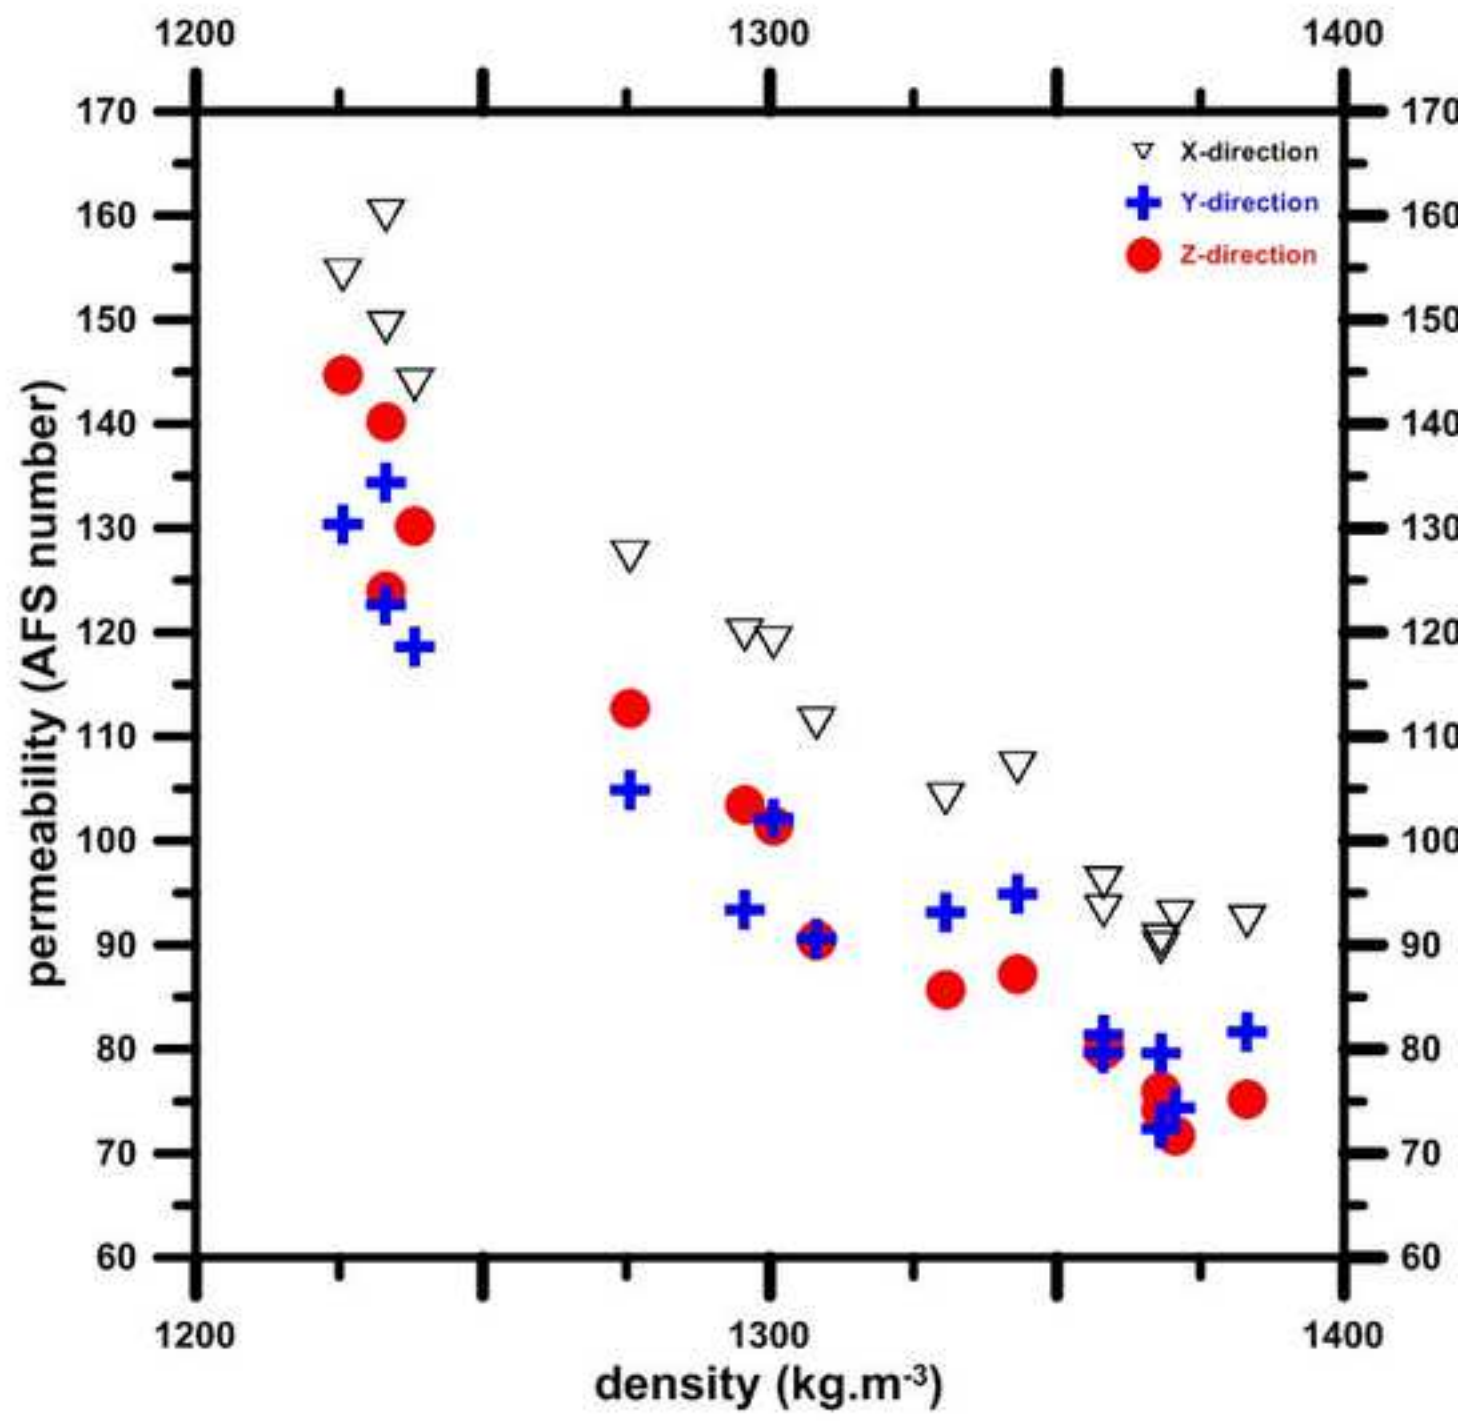
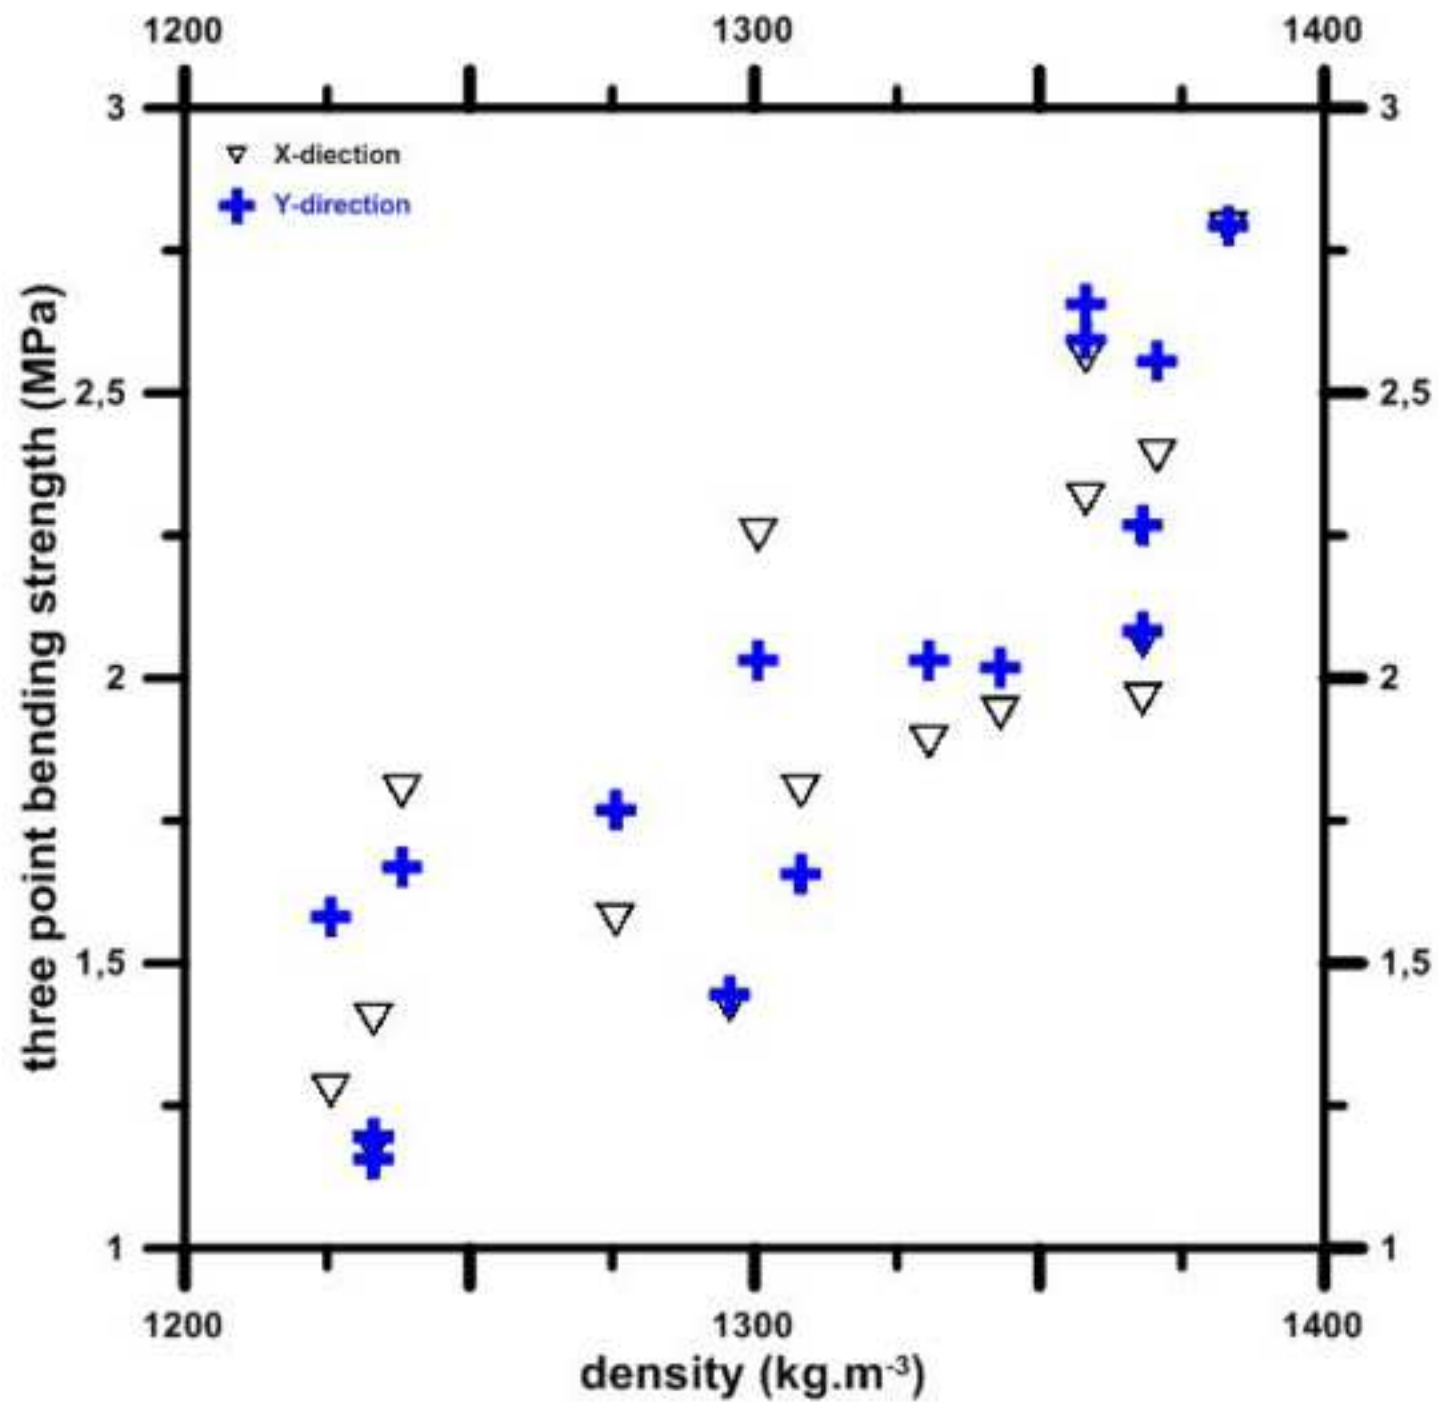


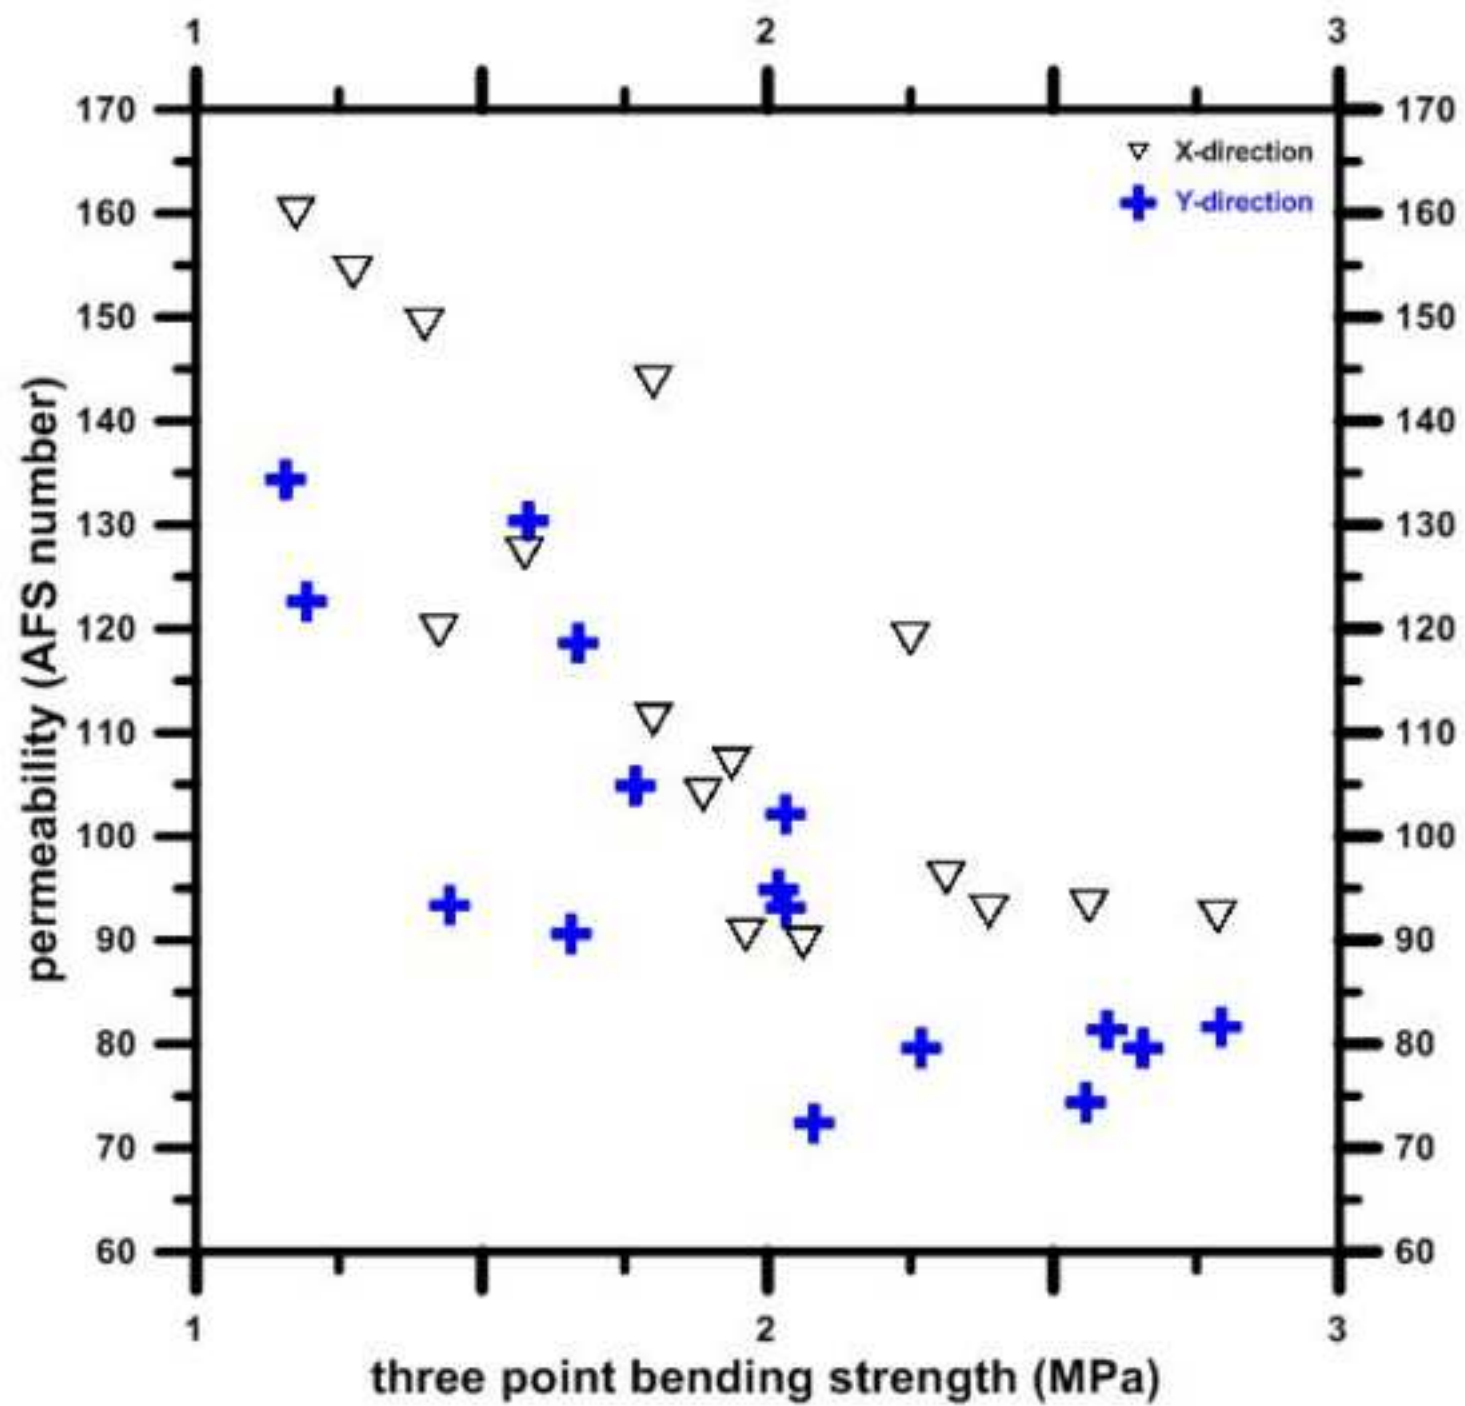


Figure 4









## List of Tables

---

**Table 1** : Dimensions, quantity, and orientations of specimens printed in each job box.

Specimen	Dimensions (mm)	Direction	Number
Bar (for 3PB test)	22.4 x 22.4 x 172	X	18
		Y	14
Cylinder (for permeability test)	Diameter = 50 Height = 50	X	12
		Y	12
		Z	12

**Table 2** :3D printing process parameters for the sand specimens.

Average sand grain size	140 $\mu\text{m}$
Activator content	0.18 wt.% <sup>*</sup>
Inhibitor content	0.4 wt. % <sup>†</sup>
Print head voltage	78 V
Layer thickness	280 $\mu\text{m}$
Heating temperature	305 K
Print resolution	120 - 140 $\mu\text{m}$
Recoater speed	130 - 286 $\text{mm}\cdot\text{s}^{-1}$

**Table 3**: Process parameters with their ranges and values at two levels.

Parameter Designation	Process Parameter	Range	Level 1	Level 2
X	X-position in job box (mm)	50 – 750	50	750
Y	Y-position in job box (mm)	50 – 450	50	450
$X_R$	Print Resolution ( $\mu\text{m}$ )	120 – 140	120	140
RS	Recoater Speed ( $\text{mm}\cdot\text{s}^{-1}$ )	130 – 286	130	286

---

<sup>\*</sup> Of the sand weight.

<sup>†</sup> Of the sand weight.

**Table 4** : Coefficients of process parameter effects on permeability, flexural stress, and density.

Parameters	Identifiers	$P_X$ (GP <sup>‡</sup> )	$P_Y$ (GP)	$P_Z$ (GP)	$\sigma_x$ (MPa)	$\sigma_y$ (MPa)	$\rho$ (kg·m <sup>-3</sup> )
Average	M	115.6	97.1	98.6	1.913	1.969	1311
X	A	-10.3	-9.8	-10.4	0.119	0.106	22
Y	B	-2.8	-1.1	-3.2	0.157	0.069	3
X <sub>R</sub>	C	0.8	0.5	-0.9	-0.206	-0.238	-2
RS	D	19.9	15	19.8	-0.325	-0.406	-4.8
X-Y	AB	0.6	2.3	0.8	0.038	0.043	3
X- X <sub>R</sub>	AC	-3.3	-3.8	-1.2	-0.013	0.025	3
X-RS	AD	-5.9	-4.6	-5.9	0.056	0.056	9
Y- X <sub>R</sub>	BC	-0.1	0	-0.4	-0.075	-0.013	-3
Y-RS	BD	-1.9	-2.5	-3.6	0.069	0.006	3
X <sub>R</sub> -RS	CD	-1.3	-2.3	-2.9	0.069	0.038	6
<i>Maximum residual errors</i>		6	9	4	0.11	0.09	8
<i>Minimum</i>		89.7	72.3	71.7	1.175	1.156	1226
<i>Maximum</i>		159.9	134.4	144.7	2.788	2.794	1383

**Table 5** : Calculated mold sample properties for X<sub>R</sub> and RS values of 140 μm and 158 mm·s<sup>-1</sup> according to the model proposed in Table 3

X	Y	P <sub>X</sub> (GP)	P <sub>Y</sub> (GP)	P <sub>Z</sub> (GP)	σ <sub>X</sub> (MPa)	σ <sub>Y</sub> (MPa)	ρ (kg·m <sup>-3</sup> )
-1	-1	115	101	96	1.81	1.87	1324
1	-1	95	76	79	1.87	1.98	1356
-1	1	111	100	92	1.81	1.89	1314
1	1	93	81	78	2.02	2.16	1358
<b>Average</b>		93.1			1.92		1338
<b>Standard deviation</b>		12.8			0.12		22

**Table 6** : Measured mold sample properties for X<sub>R</sub> and RS values of 140 μm and 158 mm·s<sup>-1</sup>

X	Y	P <sub>X</sub> (GP)	P <sub>Y</sub> (GP)	P <sub>Z</sub> (GP)	σ <sub>X</sub> (MPa)	σ <sub>Y</sub> (MPa)	ρ (kg·m <sup>-3</sup> )
-1	-1	98	78	76	1.70	1.85	1341
1	-1	93	71	69	1.85	1.90	1382
-1	1	96	77	80	1.85	1.90	1338
1	1	85	65	66	2.20	2.00	1385
<b>Average</b>		79.5			1.91		1362
<b>Standard deviation</b>		11.4			0.15		25

<sup>‡</sup> Commonly used AFS number for gas permeability of sand mold, but does not have the SI or proper scientific unit.

**Table A.1** : Average values of permeability, flexural stress, and density for various process parameters.

Level of Process Parameters				$P_X$ (GP)	$P_Y$ (GP)	$P_Z$ (GP)	$\sigma_X$ (MPa)	$\sigma_Y$ (MPa)	$\rho$ (kg·m <sup>-3</sup> )
X	Y	X <sub>R</sub>	RS						
-1	-1	-1	-1	95.94	81.38	79.94	2.31	2.59	1.3581
1	-1	-1	-1	92.69	74.38	71.69	2.39	2.56	1.3706
-1	1	-1	-1	93.19	79.63	80.19	2.56	2.66	1.3581
1	1	-1	-1	92.19	81.63	75.19	2.79	2.79	1.3831
-1	-1	1	-1	106.94	94.88	87.19	1.94	2.02	1.3431
1	-1	1	-1	90.44	72.38	74.19	1.96	2.08	1.3681
-1	1	1	-1	103.94	93.13	85.69	1.89	2.03	1.3306
1	1	1	-1	89.69	79.63	75.94	2.06	2.27	1.3681
-1	-1	-1	1	154.19	130.38	144.69	1.28	1.58	1.2256
1	-1	-1	1	127.19	104.88	112.69	1.58	1.77	1.2756
-1	1	-1	1	143.69	118.63	130.19	1.80	1.67	1.2381
1	1	-1	1	118.94	102.13	101.44	2.25	2.03	1.3006
-1	-1	1	1	159.94	134.38	140.19	1.18	1.16	1.2331
1	-1	1	1	119.69	93.38	103.44	1.43	1.44	1.2956
-1	1	1	1	149.19	122.63	123.94	1.40	1.19	1.2331
1	1	1	1	111.19	90.63	90.44	1.80	1.66	1.3081