



### Science Arts & Métiers (SAM)

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>  
Handle ID: <http://hdl.handle.net/10985/8783>

#### To cite this version :

Marianne PROT, Dominique SALETTI, Stéphane PATTOFATTO, Valérie BOUSSON, Sébastien LAPORTE - Links between microstructural properties of cancellous bone and its mechanical response to different strain rates. - In: SB2012, France, 2012-09 - Computer Methods in Biomechanics and Biomedical Engineering, 15:sup1, 291-292 - 2013

Any correspondence concerning this service should be sent to the repository

Administrator : [scienceouverte@ensam.eu](mailto:scienceouverte@ensam.eu)



# Links between microstructural properties of cancellous bone and its mechanical response to different strain rates.

M. PROT\*<sup>1</sup>, D. SALETTI<sup>1</sup>, S. PATTOFATTO<sup>2</sup>, V. BOUSSON<sup>3</sup> and S. LAPORTE<sup>1</sup>

<sup>1</sup> Arts et Métiers ParisTech, LBM, Paris, France

<sup>2</sup> LMT-Cachan (ENS Cachan/CNRS/Université Paris VI/Pres UniversSud Paris), Cachan, France.

<sup>3</sup> Service de Radiologie Ostéo-Articulaire, Hôpital Lariboisière, Paris, France.

*Keywords:* Architectural Parameters; Cancellous Bone; Dynamic; Confined Dynamic; Quasi-Static.

## 1 Introduction

Automobile accidents and sporting injuries may lead to osseous fractures. To reduce the number of road accidents and their societal costs, governments have partnered with car manufacturers to develop an overall road safety. To achieve this, researchers are working on improving the design of automotive structures. However, researchers must first quantify the risk of injury incurred during an impact. Indeed, in France osteoporosis is responsible of approximately 150 000 fractures per year. A better understanding of this fracture mechanism will aid in the design of protective features that will guard against fracture under these loading conditions.

Bone is generally divided into two micro-structural types: cortical and cancellous bone. Cortical bone is a compact bone, denser than cancellous bone and accounts for 80 % of the skeletal mass in the human body. Cancellous bone, also called trabecular or spongy bone has a porous structure that protects the bone marrow, acts as a core material to support the shape of thin layers of cortical bone and assist in transferring joint forces to the thick load bearing cortical bone layers.

Several studies have been able to make great progress on characterizing and modeling the behavior of cortical bone. Regarding the cancellous bone, much remains to be done and studies are mainly focused on quasi-static loadings cases [1]. In order to analyze and understand the mechanism of cancellous bone for speed ranges above the quasi-static regime, experimental work using SHPB have been. However, no modeling, including the different parameters of cancellous bone, have yet been developed to analyze and understand the mechanism of rupture of the cancellous bone.

This issue raises a keen interest in the scientific community, and this comes through in the work presented here. Indeed, the aim of this study is to

characterize the mechanical properties of cancellous bovine bone for compression loading under different strain rates and identifying links with the microstructural description.

## 2 Methods

### 2.1 Microstructure Properties

Microstructural characterization is performed on 25 cylindrical specimens of distal parts of bovine femoral bones (diameter: 41mm, length: 15mm). The peripheral quantitative tomodensitometry technique (pQCT) was used to identify the microstructure properties of each frozen cylinder. Several architectural parameters of cancellous bone were computed with Image J software: BV/TV (Bone Volume/ Total Volume), Tb. Th (mean thickness of trabeculae), BS (Bone Surface), Conn.D (Connectivity Density or number of trabeculae per unit volume), DA (Degree of Anisotropy), SMI (Structure Model Index) and FD (Fractal Dimension).

### 2.2 Experimental Technique & Mechanical Properties

The samples were divided in three groups and three different tests were performed: quasi static tests (QS, ca  $0.001 \text{ s}^{-1}$ ), dynamic tests (D, ca  $1000 \text{ s}^{-1}$ ) and confined dynamic tests (CD, ca  $1500 \text{ s}^{-1}$ ). Mechanical parameters identified are: E (Apparent Young's modulus),  $\epsilon_{\text{Max}}$  (maximum strain),  $\sigma_{\text{Max}}$  (yield stress) and  $\sigma_p$  (Plateau stress).

### 2.3 Statistical Analysis

Kruskal-Wallis statistical test assessed that the samples are from the same distribution. Then, the Mann-Whitney statistical test was performed to identify the influence of the boundary conditions. Finally, Spearman statistical test was used to highlight correlations between mechanical and microstructural properties.

---

\*Corresponding author. Email: Marianne.PROT@ensam.eu

### 3 Results and Discussion

#### 3.1 Influence of the architectural properties on quasi-static loading mechanical properties.

$\epsilon_{Max}$  is found to have significant correlations with Conn. D & DA.  $\sigma_{Max}$  correlates with BV/TV, Tb.Th & BS and  $\sigma_p$  with BV/TV, BS, Conn.D. Similar results were found in litteratury. No correlation was found in regards with E. Follet [1] and Mittra et al. [2] found E to be correlated with Tb.Th and BV/TV. This difference could be explained by the fact that they were working with other species. For Syahrom [4], who were testing on bovine bone too, shows that E correlates well with BV/TV. The lack of similar correlation in the present study could be explained because Syahrom cleaned the bone marrow from the specimens.

The table 1 presents Spearman's test results and a highlighting of correlations between mechanical properties (dynamic and quasi-static loadings) and architectural parameters.

	BV/TV	Tb.Th	BS	Conn.D	DA	SMI	FD
E	NS	NS	NS	NS	NS	NS	NS
$\epsilon_{Max}$	NS	NS	NS	*	*	NS	NS
$\sigma_{Max}$	*	*	*	NS	NS	NS	NS
$\sigma_p$	*	NS	****	*	NS	NS	NS

Table 1 : a) Quasi-Static loading correlations

	BV/TV	Tb.Th	BS	Conn.D	DA	SMI	FD
E	NS	NS	NS	NS	NS	NS	NS
$\epsilon_{Max}$	NS	NS	NS	NS	NS	NS	NS
$\sigma_{Max}$	*	NS	**	NS	NS	NS	****
$\sigma_p$	**	*	**	NS	*	*	*

Table 1: b) Dynamic loading correlations NS: Not Significant, \*  $p < 0.05$ , \*\*  $p < 0.01$ , \*\*\*  $p < 0.001$ , \*\*\*\*  $p < 0.0001$

#### 3.2 Influence of the architectural properties on dynamic loading mechanical properties

$\sigma_{Max}$  is having a significant correlation with BV/TV, BS, FD and  $\sigma_p$  with BV/TV, BS, DA, SMI and FD. Dynamic correlations were found to be relevant in comparison with Halgrin work [5].

#### 3.2 Influence of the architectural properties on confined dynamic loading mechanical properties

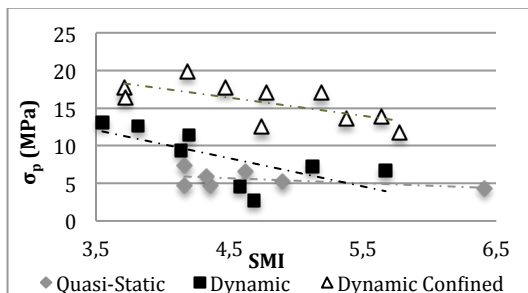


Figure 1: Correlation for the plateau stress

No correlation is significant for E or  $\sigma_{Max}$ . As for dynamic loading, correlations for confined dynamic loading are established:  $\sigma_p$  correlates with BV/TV, BS, and SMI (Figure 1). However for confined dynamic loading,  $\epsilon_{Max}$  is found correlated with FD.

The differences between dynamic loading and confined dynamic testing, especially for DA correlation, could be explained by the bone marrow influence and the limit conditions of the confinement.

### 4 Conclusions

Results prove that architectural parameters such as BV/TV, BS, Tb.Th and DA can predict bone stiffness and strength, at different strain rate, through imaging, as they shown significant correlation with mechanical response parameters. Moreover, the additional correlation of SMI and FD regarding dynamic loading and Conn.D regarding quasi-static loading could improve the prediction.

Finally, this study permitted to underline in what extent the marrow will influence the global behaviour of cancellous bone.

An analytical model of the rupture mechanism via imaging acquisition method could then be developed based on the previous investigation results. Parameters identified as "main" parameters *i.e* having a significant influence on mechanical behaviour will be inputs for the running mode.

### References

- [1] Follet, H, Caractérisation biomécanique et modélisation 3D par imagerie X et IRM haute résolution de l'os spongieux humain : évaluation du risque fracturaire. *PhD thesis*, 02.
- [2] Mittra, E., Rubin, C., and Qin, Y., Interrelationship of trabecular mechanical and microstructural properties in sheep trabecular bone. *Journal of biomechanics*, 05, 1229–1237
- [3] Teo, J., Si-Hoe, K., Keh, J., and Teoh, S., Relationship between ct intensity, micro-architecture and mechanical properties of porcine vertebral cancellous bone. *Clinical biomechanics*, 06, 21(3):235–244.
- [4] Syahrom A., Mechanical and micro-architectural analysis of cancellous bone through experiment and computer simulation. *International Federation for Medical and Biological Engineering*, 11, DOI 10.1007/s11517-011-0833-0.
- [5] Halgrin, J, Influence des paramètres architecturaux sur le comportement mécanique de l'os trabéculaire. *PhD thesis*.