



### **Science Arts & Métiers (SAM)**

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>  
Handle ID: <http://hdl.handle.net/10985/19787>

#### **To cite this version :**

Bertrand MARCON, Jean-Claude BUTAUD, Louis DENAUD, Robert COLLET, Joffrey VIGUIER -  
Panel Shear of Plywood in Structural Sizes - Assessment Improvement Using Digital Image  
Correlation - Experimental Techniques p.0 - 2021

Any correspondence concerning this service should be sent to the repository

Administrator : [scienceouverte@ensam.eu](mailto:scienceouverte@ensam.eu)





# Panel Shear of Plywood in Structural Sizes - Assessment Improvement Using Digital Image Correlation

J. Viguier<sup>1</sup> · B. Marcon<sup>1</sup> · J. C. Butaud<sup>1</sup> · L. Denaud<sup>1</sup> · R. Collet<sup>1</sup>

Received: 25 June 2019 / Accepted: 8 December 2020  
© Springer Nature Switzerland AG part of Springer Nature 2020

## Abstract

This paper introduces a new test configuration for the determination of panel shear properties in structural sizes. This original test configuration has been successfully applied to calculate the shear properties of beech plywood. A numerical model has been developed to evaluate the influence of such a novel setup in comparison to the common standard. The research includes the mechanical characterization of a total of 36 samples using Digital Image Correlation (DIC) to measure the in plane displacements. The use of DIC has been proven to be efficient to measure the shear properties and also acts as a tool to ensure that the solicitation was adequate during the test. Finally, the results highlight the interest to actually perform the proposed test instead of using the alternative density-based equivalencies provided by the standards.

**Keywords** Shear · DIC · Beech · Plywood

## Introduction

Plywood is often used in the construction sector. In particular, high quality beech plywood could exhibit great features to be used in the construction for plywood gussets in nailed or glued trusses or as a web of I-Joist. Therefore obtaining reliable shear properties for plywood is essential to ensure security and cost efficiency in the legal range of the building standards. The measured shear properties has not been found to be a constant value [1], but appears to be affected by the method of shear properties determination even when controlling all factors which normally affect the mechanical properties of wood. The evaluation of shear properties has conducted to create a wide range of standardized and non-standardized test methods (two rails, plate shear, bending tests, torsion, ...). Among those, the two rails type seems to be preferred in order to test plywood in structural size. During this test, the load is transferred to the specimen through two pair of rails glued or bolted parallel to its longer edge in such a way that the shear is nearly pure in the central area. Several studies [2–6] have

been conducted over the years to develop or assessing the difference between two-rails type tests.

The area exposed to shear has been kept nearly constant over the years to a rectangle of approximately 200 by 600 mm<sup>2</sup>. Different strategies to perform this test have been experienced, all of them requiring complicated apparatus (see Fig. 1). In the latest European standard (EN 789 [7]), this area has been changed to a more complicated shape with a slightly lower area (see Fig. 1(c)) but the principle and the complexity remain constant. This complexity probably causes the lack of values issued from plywood performance declaration of the majority of the plywood panel manufacturers. Indeed, the producers prefer to use density equivalencies given in EN 12369-2 [8] to provide shear properties even if they are very penalizing and do not reflect the true mechanical properties of plywood panels especially in the case of beech.

Panels shear modulus is usually measured using a Linear Variable Differential Transformer (LVDT) orientated by 45° across the central area (symbolized by a rectangle in Fig. 1) on each side of the specimen and then averaged. Timbers shear modulus can also be determined through flexural [9] or torsional [10] vibration mechanical tests with accelerometers and more or less complex finite elements analysis (FEA). In this study, Digital Image Correlation (DIC) is proposed as an alternative to the fixation of LVDT and as a substantial improvement to measure those displacements. In the past 30 years, DIC has proved to be

✉ J. Viguier  
joffrey.viguier@gmail.com

<sup>1</sup> LaBoMaP, Arts et Metiers Institute of Technology, LaBoMaP, HESAM Université, rue Porte de Paris, F-71250, Cluny, France



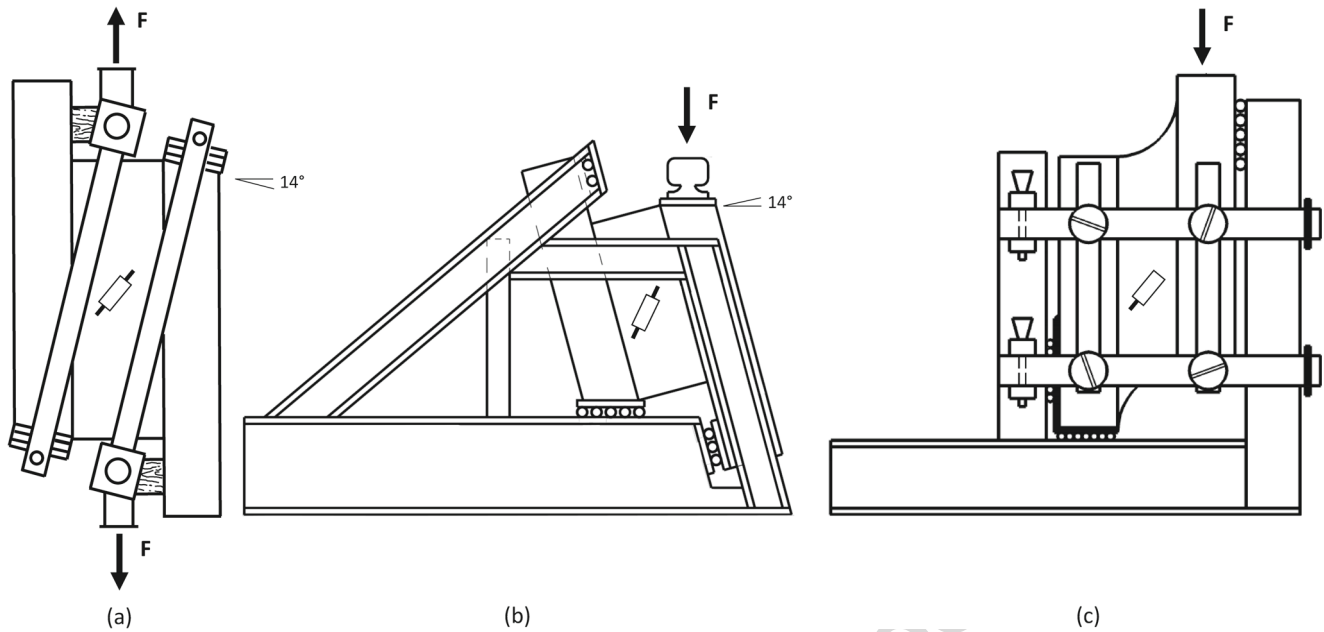


Fig. 1 Different two-rails configuration tests used or in use within the past 30 years

a very valuable non-invasive tool for full-field displacement measurements [11–14] and its accuracy has been proven [15]. The use of DIC in the field of wood testing is increasing [16–18].

The main objective of the present study is to propose a simpler method to determine the shear properties of wooden panels and more particularly plywood ones. In addition an experimental part designed to validate the modified test using full field measurements, finite elements numerical simulations have been used to determine the influence of using the proposed test method on the mechanical properties of the plywood panels.

## Materials and Methods

### Sampling

A total of 18 beech plywood panels were used for this study and two different thicknesses (18 and 25 mm with respectively 9 and 11 plies) have been studied. Samples were cut using a three-axis router machine according to the shape described in Fig. 2. In order to define a test which can be performed easier than the one described in the standard [7], involving a less bulky setup, the chosen strategy was to tilt the sample. For the experimental part, the angle  $\alpha$  has been taken equal to  $18^\circ$  in such a way that the moment is nearly equal to 0. In doing so, the special apparatus described in the standard was not needed anymore and the initially complex test looks like a simple self balanced compression test. Four Douglas-fir timber

rails with a thickness equals to 35 mm have then been glued using polyvinyl acetate (PVAC) to each specimen to avoid buckling of the sample during the test as required by the standard [7]. Two samples have been cut from each panel : one having its external ply with fiber along the longest dimension and the second one perpendicular to its longest dimension. Finally, 36 samples have been made.

### Mechanical Test and Displacements Measurement

The tests were performed with a Zwick Roell static material testing machine with a 250 kN load cell. The load was applied on the top surface of the timber rails with an adjusted application rate, so that the maximum load was reached within  $300 \pm 120$  s according to EN 789 [7]. In practice, the loading rate has been chosen equals to 2 mm/min. The shear deformation was measured on both faces in the middle of the specimen using 2D digital image correlation. Images of both faces and their corresponding load were recorded during the whole test. Digital frames of both sides of the specimen were recorded using two Basler ace acA1920-155um type imagers equipped with Pentax Ricoh FL-CC3516-2M - 1.6 / 35 mm lenses. Those cameras exhibit a resolution of 1920 by 1200 square pixels with a pitch size of  $5.86e^{-3} \text{ mm}^2$ . The observed area was set to 211 by 132  $\text{mm}^2$  thanks to extension tubes with a working distance (standoff distance) of 1 meter. The scene was illuminated using identical white LED projectors on both sides and a built-in lens diaphragm used to reach identical grey level repartition histograms for both sides of the specimen. The geometrical centres had been marked

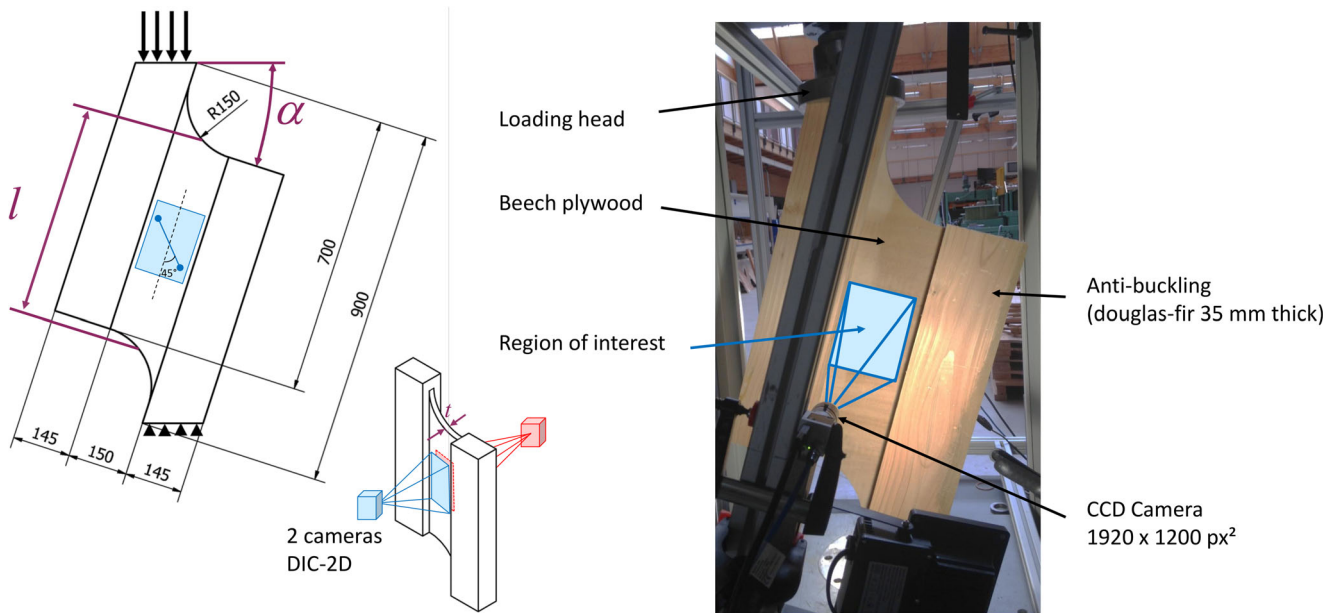


Fig. 2 Experimental test setup


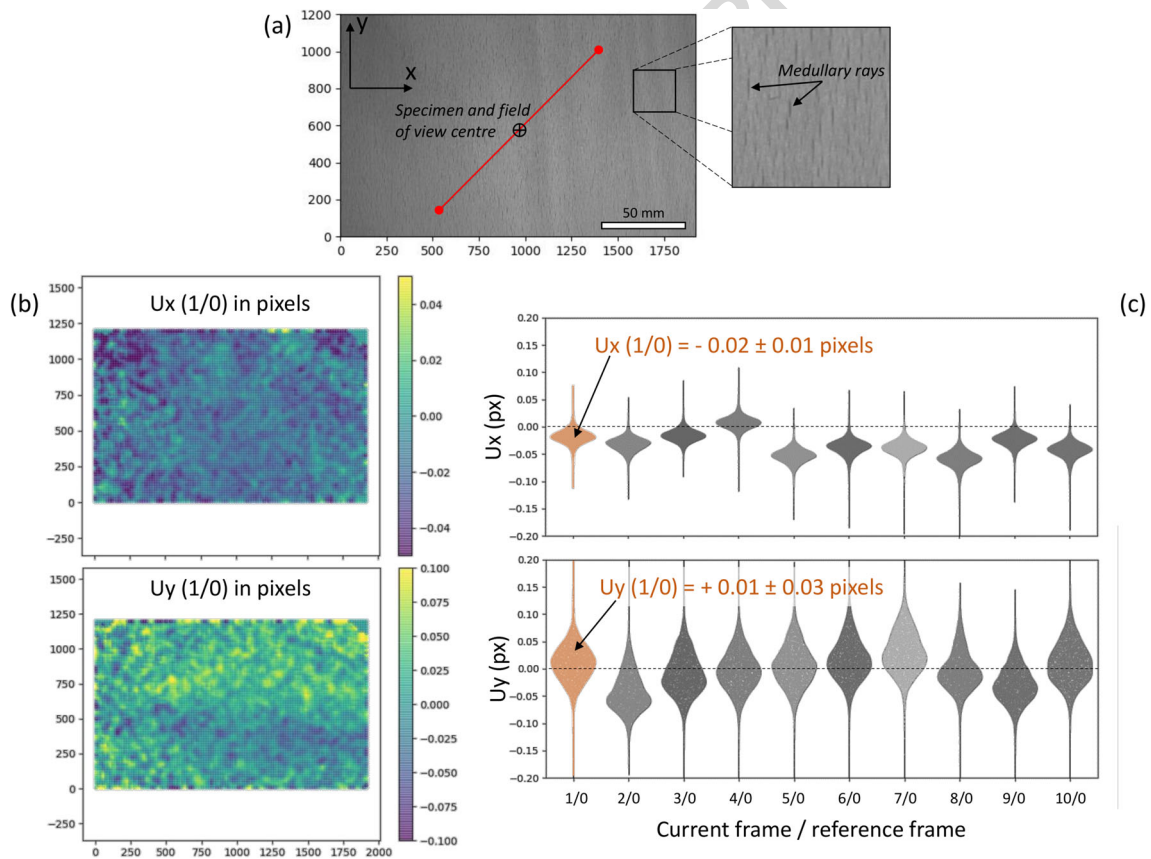


Fig. 3 a beech natural pattern for DIC on one sample showing medullary rays (elliptical darker shapes), b corresponding X-and Y-displacement fields obtained between the first image and the reference image, c DIC pseudostatic accuracy assessment from 10 consecutive images taken free from loading

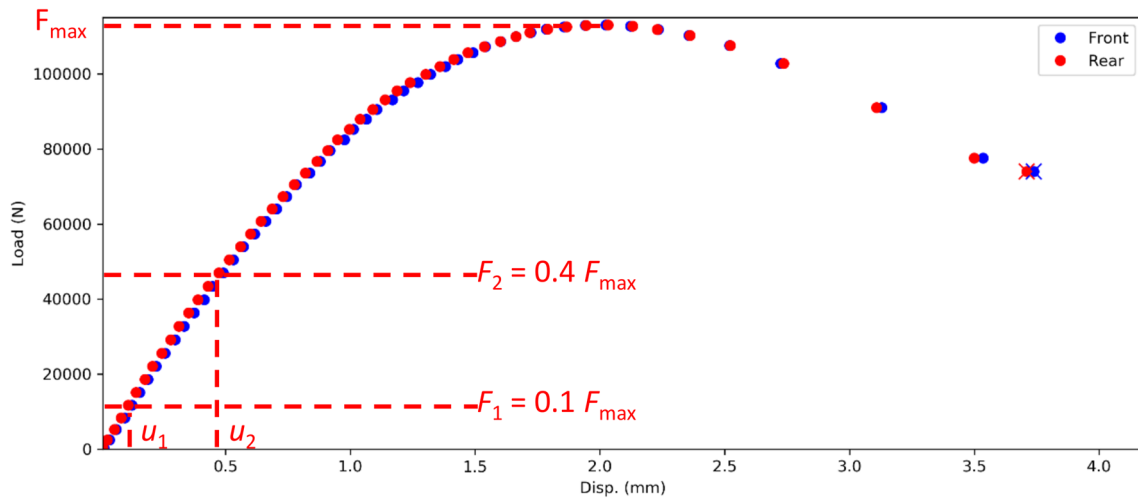


**Fig. 4** Typical load-displacement curves (front and rear) used for the panel shear properties assessments. The displacement represents the distance measured by DIC between two points located on the compression diagonal at  $45^\circ$  to the rails passing through the centre of the shear area

precisely on both sides of the specimen and centred on both camera respective fields of view before tests were performed (see Fig. 3(a)). Moreover, the alignment of the camera axis with the specimen ones, as represented in the Fig. 2, was ensured by imposing their correspondence with the anti-buckling beams, and the camera orientation (sensor parallel with the observed area) was checked using a grid calibration plate. The magnification factor obtained with such experimental set up was 9.08 px/mm (or 0.11 mm/px). Hardware and software resources have been developed specifically to record simultaneously the load value and its corresponding pictures. The experimental test setup is described in Fig. 2.

The principle of Digital Image Correlation is to compare digitized images of non-deformed specimen (reference) to multiple images of the same specimen while applying the loading to obtain the full-field displacement. An important element of the measurement procedure is the image analysis software package which is supposed to provide an apparent 2-D displacement field that maps a so-called "reference image" to a "deformed image" at a discrete set of positions, according to the principle of optical flow conservation. The displacement was computed using the image analysis software, DaVIS 10.0.5, by LaVision. In the case of this

study, no surface preparation of the observed area has been done, the medullary rays of beech as shown in (Fig. 3(b)) have been directly used as the pattern from which to correlate the images between two successive loading steps. The subsize and the stepsize have been taken equal to 51 and 17 pixels respectively. The region of interest is shown in Fig. 2. The image acquisition frequency was fixed at 0.2 Hz.

The natural pattern the beech plywood featured, see (Fig. 3(a)), appeared as really satisfying among the different surface preparation considering the difficulty to master the paint application on big amount of samples compared to the accuracy required for the shear modulus determination (some details regarding this will be discussed in Section "Mechanical Properties Calculation"). Nonetheless, the natural pattern of beech veneer is anisotropic due to the presence of elliptic and oriented medullary rays affecting the correlation error which becomes anisotropic correspondingly.

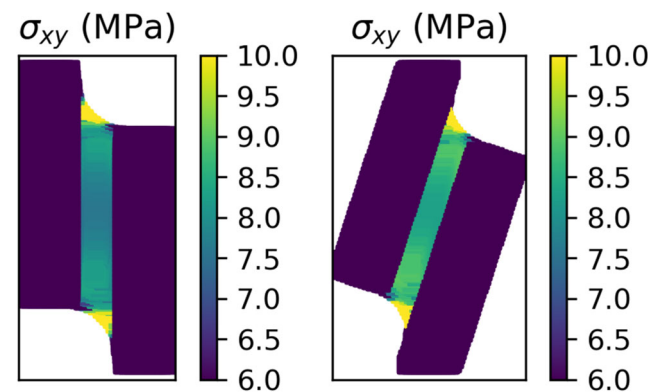


**Fig. 5** Comparison of the modeled strain field obtained from vertical and tilted samples

**Table 1** Material properties used in finite elements analysis

Property	Ply material (beech) [20]	Wood support (Douglas fir) [21]
$E_X$ (MPa)	14000	14740
$E_Y$ (MPa)	1160	737
$\nu_{XY}$	0.45	0.45
$G_{XY}$ (MPa)	1080	1150



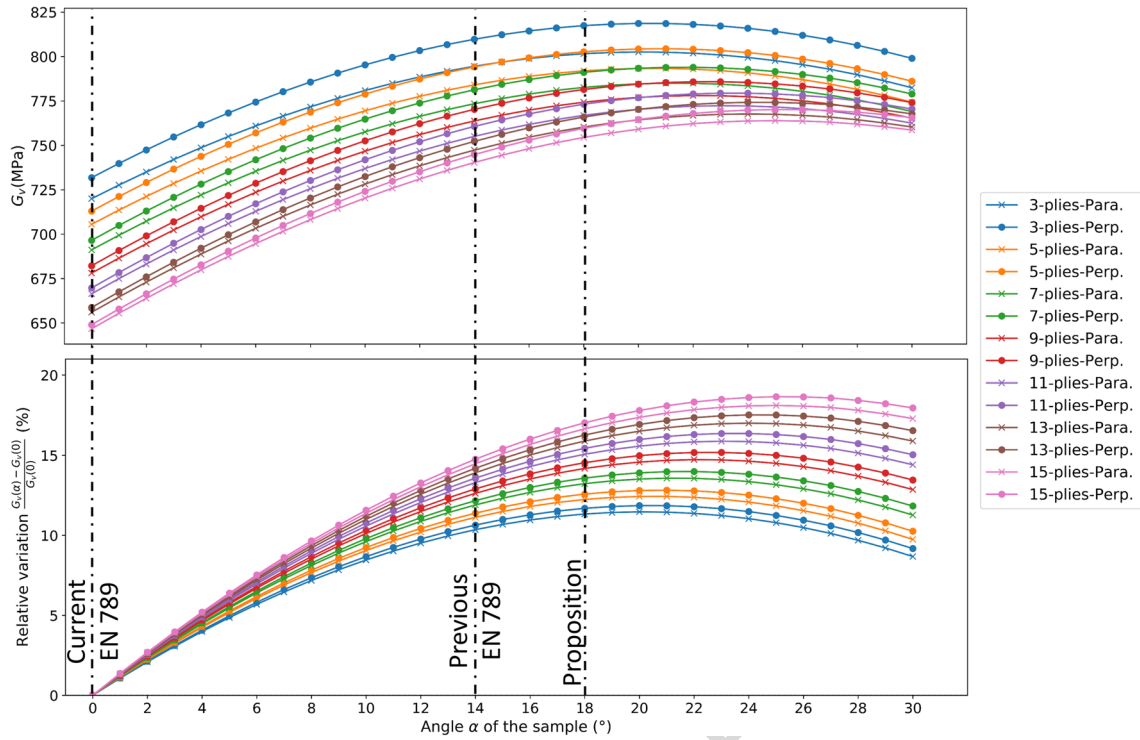

**Fig. 6** Influence of tilting the sample at different angle on the calculation of  $G_v$ . The results for two types of sample (Parallel and Perpendicular) and different thicknesses are presented. The upper part shows the calculated  $G_v$  and the lower part the relative variation observed with the configuration without tilting the sample

The average correlation error is determined using the 10 images taken before the loading is applied for each sample, performing a DIC computation on them under the exact same calculation settings (subset size 51 pixels and step size 17 pixels), and extracting the standard deviation at 68% confidence interval of the X- and Y-displacement fields obtained for those non-deformed configurations. An example is provided in (Fig. 3(b)). Thus, the average displacement field error, arising from the whole samples batch on both sides, were  $\pm 4.4E^{-3}$  mm ( $\pm 0.02$  pixel) and  $\pm 2.2E^{-3}$  mm ( $\pm 0.01$  pixel) respectively for the medullary rays direction and its normal one displayed by (Fig. 3(b) and (c)). Those values embed the pattern quality, the enlightenment intensity variations and the eventual whole system vibrations (rigid body displacement between the sample and the cameras). The influence of this error on the calculation of the shear modulus will be discussed later.

## Mechanical Properties Calculation

The calculation of the shear modulus is based on load-displacement curves. The displacement is measured between two selected positions on the images. Those two positions were located on the compression diagonal at  $45^\circ$  to the rails passing through the centre of the shear area. The distance between the two points is equal to 120 mm and


corresponds to the theoretical position of the extensometer prescribed in EN 789 [7] (see Fig. 2).

The invasive attachment of a physical extensometer with pins inserted in holes is not necessary thanks to the use of DIC. An example on a load-displacement curves obtained on the two faces of the sample is described in Fig. 4. The section of the graph between  $0.1F_{max}$  and  $0.4F_{max}$  is used for a linear regression analyses and the panel shear modulus of rigidity is then calculated using (equation (1)). This equation is similar to the one given in the standard except for the  $\cos(\alpha)$  term introduced to take into account the tilting angle [7].

$$G_v = \frac{0.5\cos(\alpha)(F_2 - F_1)l_1}{(u_2 - u_1)lt} \quad (1)$$

where:

- $(F_2 - F_1)$  is the increment of load between  $0.1F_{max}$  and  $0.4F_{max}$  in N,
- $(u_2 - u_1)$  is the increment of deflection corresponding to  $(F_2 - F_1)$  using a linear regression in mm,
- $l_1$  is the distance between the two selected points and is equal to 120 mm,
- $l$  is the length of the test piece measured along the centre line of the shear area (including the radius section) in mm,

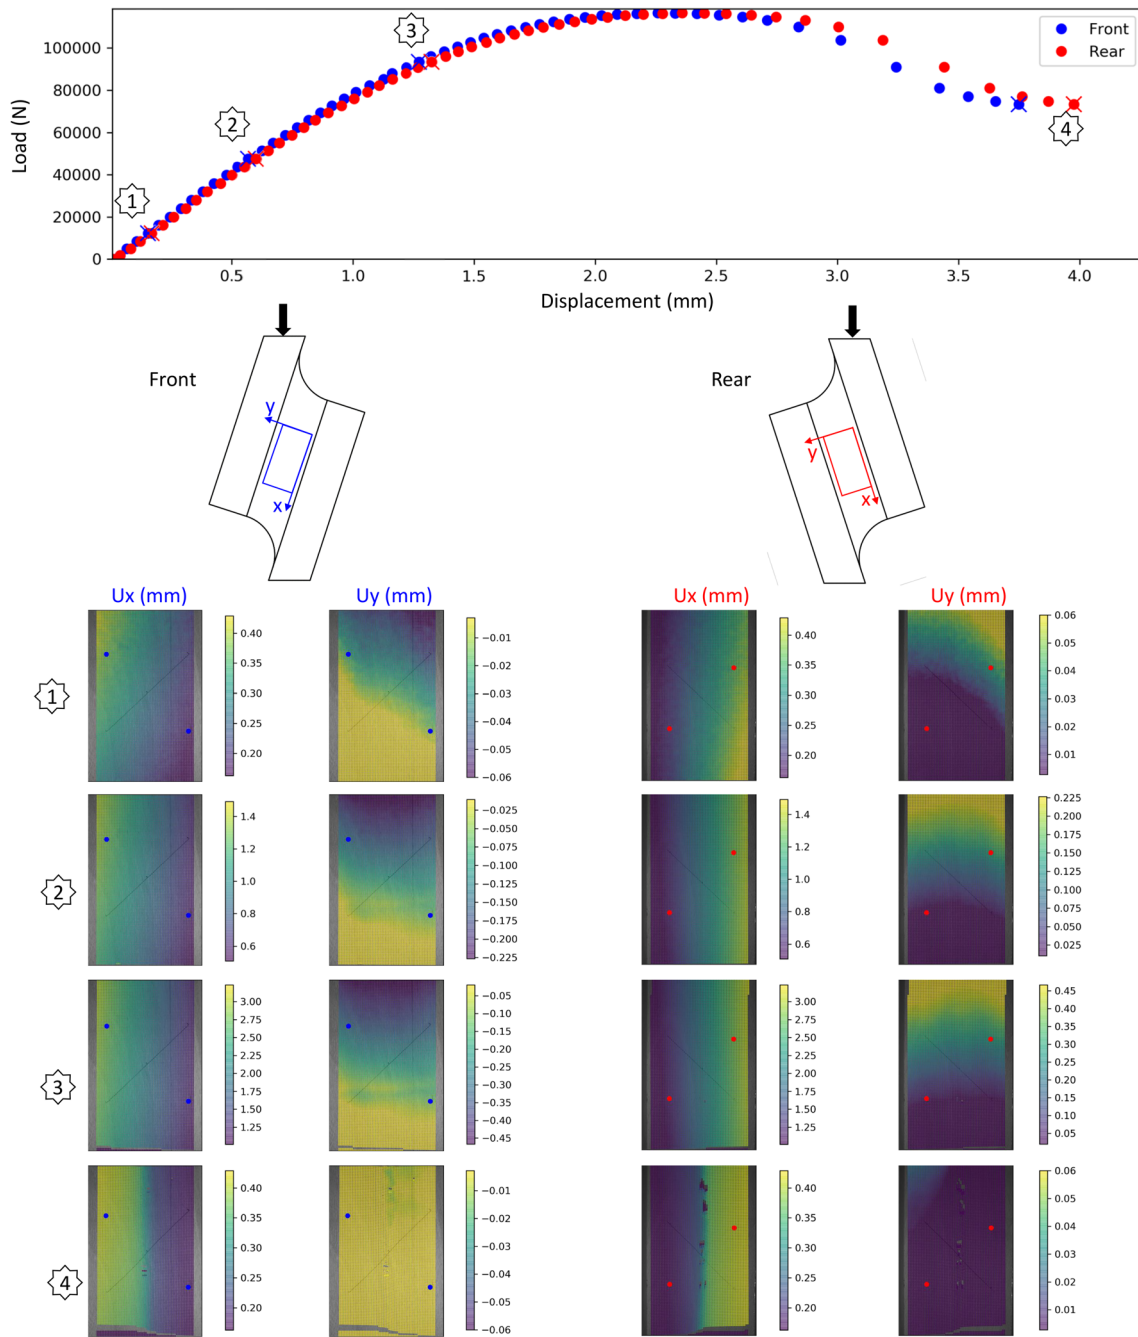


**Fig. 7** Typical results of a shear test. The upper part represents the load-displacement curve during the test. Four levels of solicitation are highlighted and their respective displacement fields for both sample sides and two directions are presented in the lower part

- 192 –  $t$  is the average thickness of the test piece measured at
- 193 two points along the centre line of the shear area in mm,
- 194 –  $\alpha$  is the tilting angle of the sample in  $^{\circ}$ .

195 An analysis of the error sources to determine the shear  
196 modulus  $G_v$  from (equation (1)) leads to a relative error on

the shear modulus of 1.4 % with the following individual  
error (experimentally determined or from device calibration  
certificates):  $\Delta\alpha = \pm 1^{\circ}$ ;  $\Delta F = \pm 0.5\% F = \pm 344 \text{ N}$ ;  
 $\Delta u = \pm 4.9\text{E-}3 \text{ mm}$ ;  $\Delta l_1 = \pm 0.5 \text{ mm}$ ;  $\Delta l = \pm 1 \text{ mm}$ ;  $\Delta t$   
 $= \pm 0.01 \text{ mm}$ . This determined  $G_v$  error is mostly affected  
by the displacement one but remains very low, sustaining

**Fig. 8** Comparison of displacements fields obtained on the front side experimentally by DIC and numerically by FEM

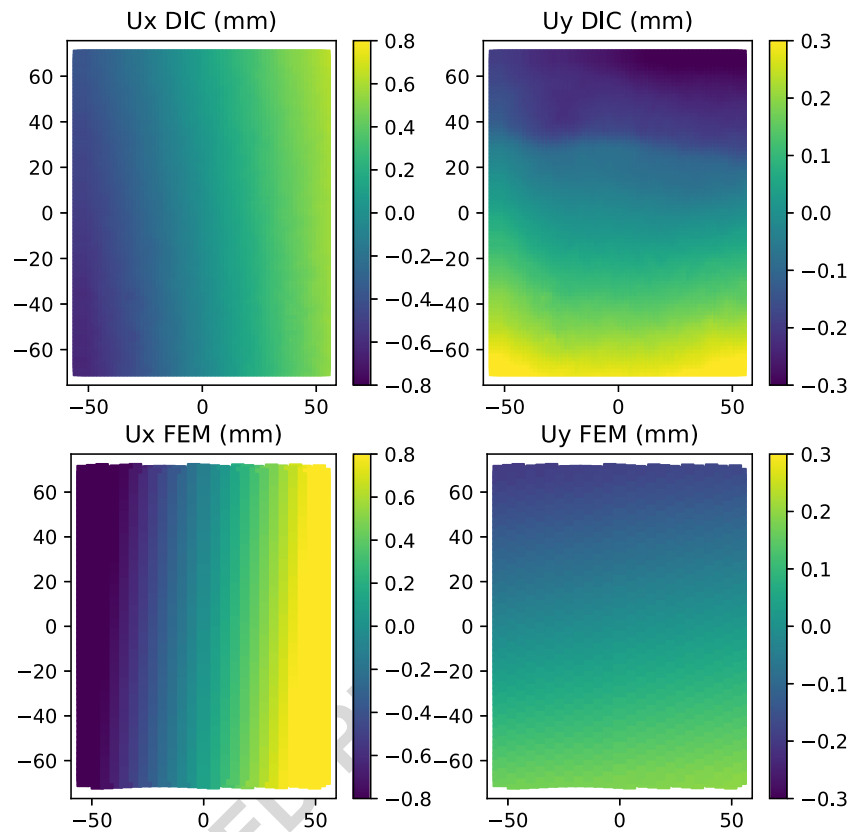

the applicability of DIC method using directly the natural beech wood aspect (medullary rays) as pattern (no surface preparation as paint speckle needed).

The panel shear strength is calculated from (equation (2)) where  $F_{max}$  is the maximum load applied up to failure. In this case too the equation only differs by the  $\cos(\alpha)$  term [7].

$$f_v = \frac{F_{max} \cos(\alpha)}{l_t} \quad (2)$$

## Numerical Model

To evaluate the influence of the test modification, a model has been developed using quadratic triangular elements (6-nodes) with orthotropic material properties. The finite element solver used for this study is CAST3M 2019 [19], the mechanical software developed by the CEA (French Atomic Energy and Alternative Energies Commission). The grain directions between the different plies were alternatively  $0^\circ$  and  $90^\circ$  to fit with plywood panel composition. The performed simulations were linear regarding the material properties and deflections. The boundary conditions were as follows: for the lower support, displacements were locked in both directions (X and Y), and in the upper support displacements were locked in horizontal direction (X). The tilting angle of the sample varies between  $0^\circ$  and  $30^\circ$ , and the number of plies varies between 3 and 15. The thickness of each ply has been

taken equal to 2 mm. The material properties used in the calculations are shown in Table 1 and were taken from the literature [20, 21]. X and Y directions being respectively the fiber direction and the direction perpendicular to the fiber. Given the purpose of the model, the interface between the plies is not modeled.

In addition, two types of specimens were modeled in a similar way to the normative recommendations: test specimens with their face grain angle oriented parallel to the load (called type Parallel), and specimens with their face grain angle oriented perpendicular to the load (called type Perpendicular).

## Results and Discussions


### Results of the Numerical Model

The comparison of the shear stress fields, for the same displacement of the loading head, obtained thanks to the FEM after tilting the sample is given in Fig. 5. The different fields were really close to each other either quantitatively or qualitatively. The shear stress in the middle part of the sample is nearly constant in both cases and validate the sample tilting strategy.

The shear modulus of rigidity calculated for each simulation is presented in Fig. 6. As one of the model



**Fig. 9** Distance between the failure position identified using DIC and the geometric centre of the sample. The upper part is related to 18 mm thick samples and the lower part show the results for 25 mm thick samples

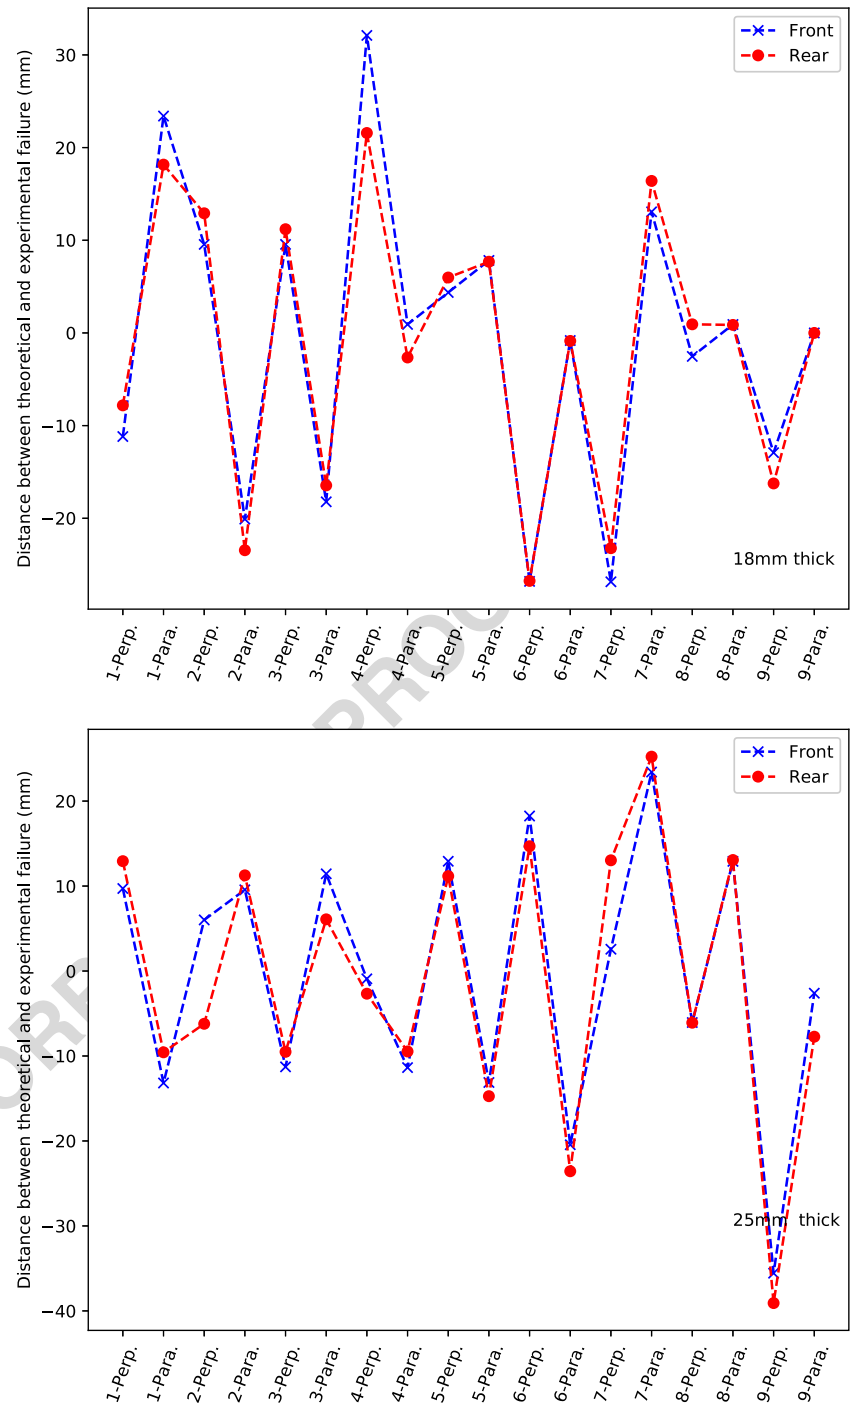


249 outcomes, it can be seen that the sample type Perpendicular  
 250 has a higher shear modulus than the Parallel type. The  
 251 difference observed between the sample types is higher for  
 252 panels with a lower number of plies. These results highlight  
 253 the homogenization process that occurs by increasing the  
 254 number of plies. The shear modulus of rigidity is lower as  
 255 the number of plies increases. The modeled shear modulus  
 256 is increasing as the angle of the sample increases until

it reaches a maximum value (from 20° to 26° depending  
 on the number of plies), then it decreases as the angle  
 continues to increase. The relative variation of the shear  
 modulus of rigidity for several tilting angles compared to  
 the simulation with the non tilted configuration ( $\alpha = 0^\circ$ ) is  
 presented in Fig. 6. The variation is inferior to 20% in every  
 cases. As the number of plies increases the relative variation  
 also increases. The relative variation for an angle of 18°

257  
 258  
 259  
 260  
 261  
 262  
 263  
 264

**Fig. 10** Comparison of the shear modulus calculated on both side of the sample. The upper part is related to 18 mm thick samples and the lower part shows the results for 25 mm thick samples

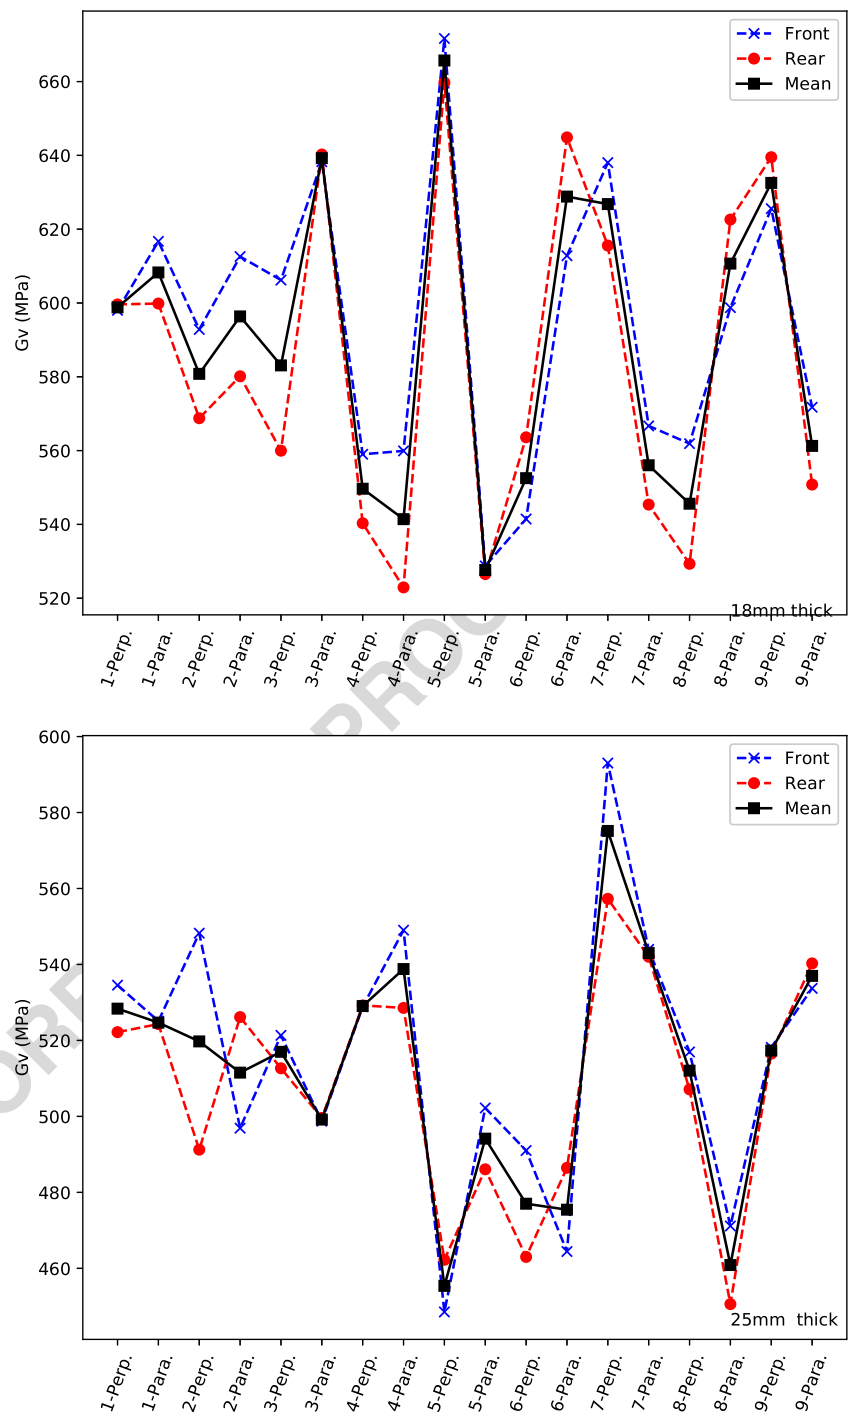

is comprised between 11% and 17% for every modeled cases. This value has to be compared to a relative variation comprised between 10% and 15% for an angle equal to 14° as it was in the previous standard EN 789 (Fig. 1(b)).

**Displacement Field and Shear Solicitation**

The typical results obtained for a single test are presented in Fig. 7 (18 mm thick and Parallel type panel). The load-

**Table 2** Minimum, mean, maximum, 5% percentiles values, standard deviations and coefficient of variation for different characterized properties

	Min	5% quant.	Mean	Max	SD	CV (%)
Density ( $\text{kg.m}^{-3}$ )						
18 mm thick.	661.9	682.4	717.7	752.2	18.3	2.5
Para.	699.7	695.5	720.7	741.2	11.9	1.6
Perp.	661.9	664.8	714.8	752.2	23.4	3.3
25 mm thick.	699.9	699.8	729.8	755.3	15.5	2.1
Para.	702.9	695.9	731.2	755.3	16.6	2.3
Perp.	699.9	695.9	728.5	746.9	15.3	2.1
All samples	661.9	690.9	723.8	755.3	17.8	2.5
$G_v$ (MPa)						
18 mm thick.	520.8	506.2	587.6	665.7	42.1	7.2
Para.	527.6	500.4	585.5	639.2	40.0	6.8
Perp.	520.8	490.7	589.6	665.7	46.5	7.9
25 mm thick.	455.4	452.7	512.0	575.1	30.7	6.0
Para.	455.4	428.5	498.2	543.0	32.8	6.6
Perp.	494.1	478.2	525.7	575.1	22.4	4.3
All samples	455.4	452.5	549.8	665.7	52.8	9.6
$f_v$ (MPa)						
18 mm thick.	10.5	10.5	12.0	13.1	0.7	6.1
Para.	10.5	10.1	11.8	12.9	0.8	6.7
Perp.	11.0	10.7	12.1	13.1	0.7	5.6
25 mm thick.	10.0	10.1	11.6	12.8	0.8	7.0
Para.	10.0	9.6	11.5	12.4	0.9	7.7
Perp.	10.8	10.2	11.8	12.8	0.7	6.2
All samples	10.0	10.4	11.8	13.1	0.8	6.6

displacement curves are presented in the upper part. The displacement represents the relative displacement of the two points as it was described before in the Section “[Mechanical Properties Calculation](#)” for each side of the panel (front and rear) analogously to the method described in EN 789. The two selected points are also visible on the displacements fields. The different steps for which displacements field are plotted correspond respectively to results under a load equal to  $0.1 F_{max}$ ,  $0.4 F_{max}$ ,  $0.8 F_{max}$  and after failure under a residual load equal to  $0.63 F_{max}$ . For each step displacement fields in x-direction for both sides (Ux Front and Ux Rear) and in y-direction (Uy Front and Uy Rear) are presented. The measured displacement on both sides were really close to each other. This result can be seen on the load-displacement curve as well as on the displacement fields.

One of the advantages of DIC is that it allows to check the validity of the solicitation. The comparison of the displacements fields obtained on the front side by DIC and by FEM is presented in Fig. 8. The comparison is made at the same load and corresponds to the third step described previously (i.e at  $0.8 F_{max}$ ). The comparison is done on the


displacements fields where the rigid body motion had been removed. It can be seen that the displacements fields in both directions were similar quantitatively.

The lower part of Fig. 7 shows that this method is an effective way to identify the failure position. The failure position computed on the two sides of every samples is presented in Fig. 9. The distance from the centre and the actual failure path is comprised between -39.1 and 32.1 mm. Therefore, every sample has been accepted for the computation of the shear strength since no failure occurred in another way than in shear between the two rails. The average absolute distance between the failure and the geometric centre is equal to 12.4 mm which can be considered low enough to use the shear length  $l$  in the calculation of the shear strength.

## Mechanical Properties Analysis

Figure 10 presents the results of the shear modulus for the 36 panels, the upper part for the 18 mm thick panels and the lower part for the 25 mm thick panels. The blue dashed line represents the shear modulus calculated on the

**Fig. 11** Comparison between experimental values and equivalencies given in EN 12369-2

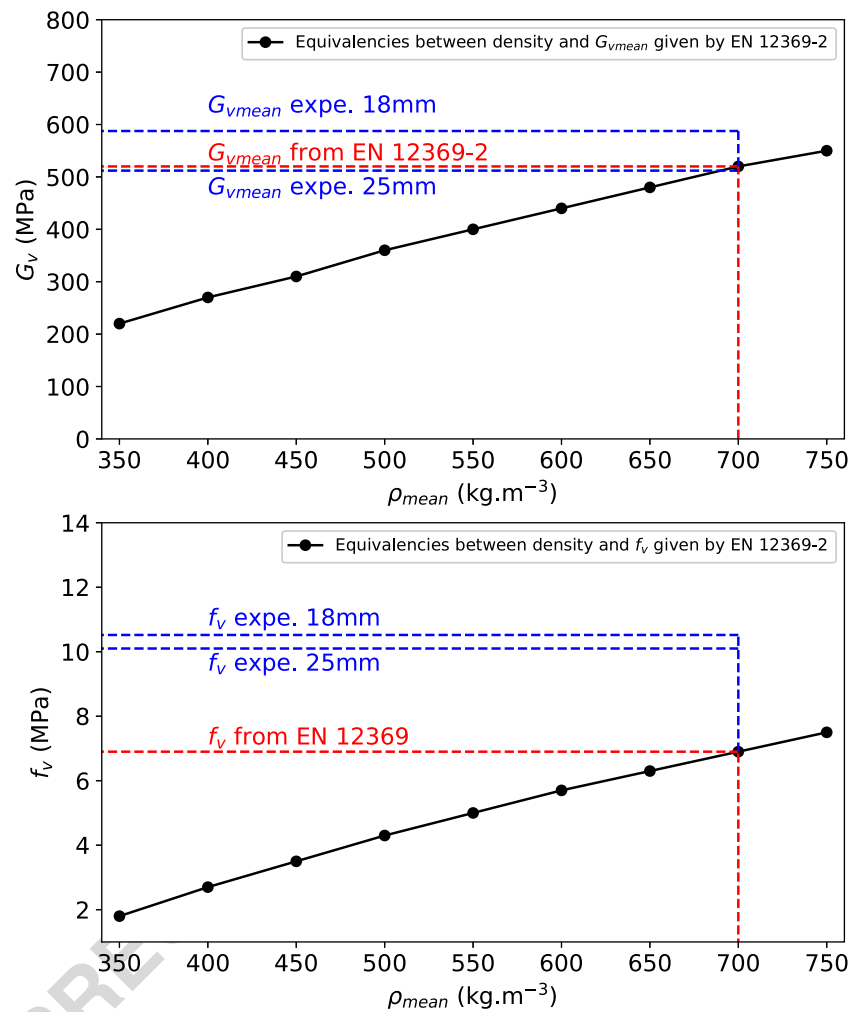

basis of the DIC measurement on the front side, the red dashed line the one measured on the rear side, and the black plain line their mean value. Those results show that the difference between the shear modulus calculated on both sides is low. Indeed, the mean relative variation is equal to only 3.6% with a maximal relative variation equal to 13.7%. These percentages represent a mean absolute variation of 20.2 MPa and a maximal variation of 76.5 MPa on the shear modulus.

Descriptive statistics for the density, the shear modulus, and the shear strength are given in Table 2. The mean value for 18 mm thick and 25 mm thick panel were respectively equal to 717.7 and 729.8  $\text{kg.m}^{-3}$ . The corresponding coefficients of variation were equal to 2.5 and 2.1% which is consistent with the literature in the case of beech [22–25]. The mean shear modulus  $G_v$  is respectively equal to 587.6 and 512.0 MPa for 18 and 25 mm thick samples. This result is consistent with the results based on the numerical model. In addition, the samples from the type Perp. have a higher shear modulus in every case which is also in accordance with the numerical model. Finally, the average

shear strength  $f_v$  and its corresponding variability were really close for every thicknesses and sample types; the global averaged shear strength is approximately equal to 12 MPa.

### Interest of the Test Realization Over Density Based Equivalencies

The survey conducted on the plywood panel manufacturers' performances reports in Europe revealed that the majority of producers use density-based equivalencies given by the standards [8] to provide shear properties. The average densities for 18 mm and 25 mm thick panels were respectively 717 and 729  $\text{kg.m}^{-3}$ , according to the same standard the value of 700  $\text{kg.m}^{-3}$  must be used (N.B: its lower limit must be used). Using this threshold, the shear properties could be taken equal to 520 and 6.9 MPa for the shear modulus and the shear strength respectively. Figure 11 presents the comparison between values obtained experimentally in this study and the values taken from the equivalencies applying the standards. These results show

that the realization of the shear tests is favorable or at least equivalent in the case of the shear modulus and always favorable for the calculation of the shear strength.

## Conclusion

This study proposed a modified of the two rails shear test in a more functional configuration, meaning without the use of a bulky apparatus. The validity of the tests has been shown by the use of full field measurement using DIC. Nevertheless, the test could still be performed using a simpler measurement device such as a LVDT in the tilted proposed configuration. The interest of the realization of these tests has been highlighted in comparison with the use of equivalences based on the measurement of the average density. In any case, the measurements taken from the tests can lead to the declaration of shear properties equivalent or even greater than those expected by the standard and thus enhance significantly the valorization of beech plywood.

**Acknowledgements** The present study was financed by the company Fernand BRUGERE. This study was performed thanks to the partnership build by BOPLI: a shared public-private laboratory build between Bourgogne Franche-Comté region, LaBoMaP and the company Fernand BRUGERE. The authors would also like to thank the Xylomat Technical Platform from the Xylomat Scientific Network funded by ANR-10-EQPX-16 XYLOFOREST.

## Compliance with Ethical Standards

**Conflict of interests** The authors declare that they have no conflict of interest.

## References

- Dobbin McNatt J (1969) Rail shear test for evaluating edgewise shear properties of wood base panel products. tech. rep., U.S.D.A Forest Service, Forest Products Laboratory. Madison
- Munthe B, Ethington RL (1968) Method for evaluating shear properties of wood. US Department of Agriculture, Forest Service, Forest Products Laboratory
- Rune Z (1994) Evaluation Of test methods for wood based panels. Determination of shear modulus and shear strength. Tech. Rep. Nordtest Project No. 1060–92, Swedish National Testing and Research Institute
- Ehlbeck J, Colling F (1984) Determination of panel shear strength and shear modulus of beech plywood in structural sizes. (SWITZERLAND)
- Wilson CR, Parasin AV (1979) A comparison of plywood modulus of rigidity determined by the ASTM and RILEM/CIB-3tt test methods. (Austria)
- Booth LG, Kuipers J, Noren B, Wilson CR (1977) Methods of test for the determination of mechanical properties of plywood, (Sweden)
- CEN (2005) EN 789 timber structures - test methods - determination of mechanical properties of wood based panels

- CEN (2011) EN 12369-2 wood-based panels - characteristic values for structural design - Part 2: Plywood
- Yoshihara H, Yoshinobu M (2015) Young's modulus and shear modulus of solid wood measured by the flexural vibration test of specimens with large height/length ratios. *Holzforschung* 69(4):493–499
- Cavalli A, Marcon B, Cibecchini D, Mazzanti P, Fioravanti M, Procino L, Togni M (2017) Dynamic excitation and FE analysis to assess the shear modulus of structural timber. *Mater Struct* 50(2):130
- Vacher P, Dumoulin S, Morestin F, Mguil-Touchal S (1999) Bidimensional strain measurement using digital images. *Proc Inst Mech Eng C J Mech Eng Sci* 213(8):811–817
- Wattrisse B, Chrysochoos A, Muracciole J-M, Némotz-Gaillard M (2001) Analysis of strain localization during tensile tests by digital image correlation. *Exp Mech* 41(1):29–39
- Sutton M, Wolters W, Peters W, Ranson W, McNeill S (1983) Determination of displacements using an improved digital correlation method. *Image Vis Comput* 1(3):133–139
- Bruck H, McNeill S, Sutton MA, Peters W (1989) Digital image correlation using newton-Raphson method of partial differential correction. *Exp Mech* 29(3):261–267
- Bornert M, Brémand F, Doumalin P, Dupré J-C, Fazzini M, Grédiac M, Hild F, Mistou S, Molimard J, Orteu J-J, Robert L, Sirel Y, Vacher P, Wattrisse B (2009) Assessment of digital image correlation measurement errors: methodology and results. *Exp Mech* 49(3):353–370
- Jeong GY, Zink-Sharp A, Hindman DP (2009) Tensile properties of earlywood and latewood from loblolly pine (*Pinus taeda*) using digital image correlation. *Wood Fiber Sci* 41(1):51–63
- Zink AG, Davidson RW, Hanna RB (2007) Strain measurement in wood using a digital image correlation technique. *Wood Fiber Sci* 27(4):346–359
- Halder S, Gheewala N, Grande-Allen K, Sutton M, Bruck H (2011) Multi-scale mechanical characterization of palmetto wood using digital image correlation to develop a template for biologically-inspired polymer composites. *Exp Mech* 51(4):575–589
- CEA (2019) Cast3m
- Guitard D (1987) Mécanique du matériau bois et composites. NABLA, cepadues ed.
- Bergman R, Cai Z, Carll CG, Clausen CA, Dietenberger MA, Falk RH, Frihart CR, Glass SV, Hunt CG, Ibach RE (2010) Wood handbook: Wood as an engineering material. Forest Products Laboratory
- Gérard J, Guibal D, Paradis S, Vernay M, Beauchêne J, Brancheriau L, Châlon I, Daigremont C, Détienné P, Fouquet D, Langbour P, Lotte S, Thévenon M-F, Méjean C, Thibaut A (2011) *Tropix* 7
- Pöhler E, Klingner R, Künniger T (2006) Beech (*Fagus sylvatica* L.) – Technological properties, adhesion behaviour and colour stability with and without coatings of the red heartwood. *Annals Forest Sci* 63(2):129–137
- Viguier J, Bourgeay C, Rohumaa A, Pot G, Denaud L (2018) An innovative method based on grain angle measurement to sort veneer and predict mechanical properties of beech laminated veneer lumber. *Constr Build Mater* 181:146–155
- Viguier J, Marcon B, Girardon S, Denaud L (2017) Effect of forestry management and veneer defects identified by x-ray analysis on mechanical properties of laminated veneer lumber beams made of beech. *BioResources*

**Publisher's Note** Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

