



Science Arts & Métiers (SAM)

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>
Handle ID: <http://hdl.handle.net/10985/26323>

To cite this version :

Xin CHEN, Mariem BEN SAADA, BRUNO LAVISSE, Amine AMMAR - Recent advances in the remelting process for recycling aluminium alloy chips: a critical review - International Journal of Material Forming - Vol. 42, p.15 - 2025

Any correspondence concerning this service should be sent to the repository

Administrator : scienceouverte@ensam.eu





Recent advances in the remelting process for recycling aluminium alloy chips: a critical review

Xin Chen¹ · Mariem Ben Saada¹ · Bruno Lavissee¹ · Amine Ammar¹

Received: 7 March 2025 / Accepted: 12 April 2025
© The Author(s) 2025

Abstract

This critical review examines advances in preprocessing and remelting processes for aluminium alloy chip recycling, emphasizing pre-treatment and remelting techniques that improve both resource recovery and material quality. Pre-treatment strategies, particularly cleaning methods and compaction are critically evaluated. Various cleaning methods, including centrifugation, ultrasonic solvent washing, extraction, and distillation are compared based on their ability to remove residual cutting fluids. Cold compaction, which augments chip density to approximately 2.5 g/cm³, significantly curtails oxidation losses and enhances metal recovery. During remelting, NaCl-KCl-based fluxes with limited fluoride additions (e.g., 3–7 wt% Na₃AlF₆) disrupt oxide networks but require careful dosage control to minimize furnace corrosion and environmental hazards. Moreover, mechanical stirring combined with suitable melting temperatures reduces porosity while enhancing melt purity. Future research should prioritize the development of low-energy cleaning methods, flux composition optimization, and scalable production techniques to further advance sustainable aluminium recycling.

Keywords Aluminium alloy · Metallic chips · Remelting recycling process · Material recovery

Introduction

Aluminium alloys, recognized for their high mechanical properties—including strength and corrosion resistance [1–3], are extensively used in various industrial sectors, such as aerospace [4], aircraft [5], automotive [6], and marine engineering [7]. The machining process involves substantial material removal in the form of chips to achieve the desired final shape and size. Notably, in sectors such as mold making and aeronautics, chip removal can constitute up to 80% of the original workpiece mass [8]. The compelling economic

and environmental advantages of aluminium recycling have drawn increasing attention. In particular, primary aluminium production requires approximately 45 kWh per kg and produces 12 kg CO₂ per kg, while secondary production through aluminium scrap remelting requires only 2.8 kWh per kg and emits 0.6 kg CO₂ per kg [9]. This pronounced disparity in resource utilization is mirrored in market pricing, as secondary aluminium enjoys a cost advantage of \$441–\$661 per ton relative to primary aluminium in North America, sometimes more [10]. Collectively, these factors underscore the potential of aluminium recycling to dramatically enhance the metal’s sustainability profile while delivering significant economic benefits. Over the past forty years, the recycling and recovery of aluminium alloys have significantly increased, driven by their cost-effectiveness, environmental sustainability, and reliability in the production of aluminium parts [11]. Additionally, aluminium is considered one of the critical raw materials in Europe, underscoring its importance in the region’s industrial landscape [12]. This increased focus on sustainability is evidenced by the emergence of a market trend for “green aluminium,” with the establishment of a new trading platform for low-carbon aluminium at the London Metal Exchange in 2020. Currently, about one-third of aluminium production is sourced

✉ Mariem Ben Saada
mariem.bensaada@ensam.eu

Xin Chen
xin.chen@ensam.eu

Bruno Lavissee
bruno.lavissee@ensam.eu

Amine Ammar
amine.ammar@ensam.eu

¹ LAMPA Laboratory, Arts et Métiers Institute of Technology,
2 boulevard du Ronceray, BP 93525, Angers cedex 01
49035, France

from scrap aluminium. The International Aluminium Institute projects this number to surpass 50% by 2050, as shown in Fig. 1. Consequently, research on scrap aluminium recycling has emerged as a prominent area of focus.

Researchers have proposed various methods for recycling aluminium chips, categorizing them into two main approaches: remelting methods and alternative methods [15]. In remelt recycling, the chips are typically heated and melted before being re-prepared through casting or other techniques [16]. However, this method presents certain challenges including a relatively higher metal loss and lower recovery rate due to the increased chemical reactivity and larger specific surface area of the metal chips [17, 18]. The recovery rate was calculated using Eq. (1) [19]. Moreover, the combustion of the oil emulsion adhering to the scrap chips can lead to the generation of toxic gases [20]. Consequently, the remelting casting method for recycling usually requires the processing of the chips [21], like cleaning, which leads to greater energy consumption and higher costs. Therefore, many scholars have changed their research direction to develop many new technologies.

$$R = \frac{m_1}{m_0} \times 100\% \quad (1)$$

Where R is the recovery rate of aluminium chips; m_0 is the total mass used of aluminium chips; m_1 is the mass of recycled aluminium.

In recent years, technologies that have been reported so far are: hot extrusion [22], Equal Channel Angular Pressing (ECAP) [23], Cyclic Extrusion Compression (CEC) [24], Friction Stir Extrusion (FSE) [25], High Pressure Torsion (HPT) [26], Ploughing Extrusion Cutting (PEC) [27], Screw Extrusion (SE) [28] Spark Plasma Sintering (SPS) [29], and Solid-State Electrolysis (SSE) [30]. These new recycling

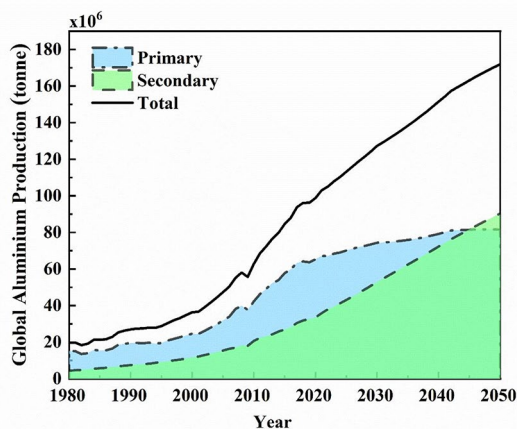


Fig. 1 Global aluminium production from primary and secondary sources [13, 14]

methods can be divided into two methods [20]: solid-state recycling techniques based on Severe Plastic Deformation (SPD) and solid-state recycling techniques based on Powder Metallurgy (PM). SPD methods including hot extrusion, ECAP, CEC, FSE, HPT, SE, and PEC, rely on extreme plastic deformation to bond aluminium chips into dense bulk materials. While these methods improve mechanical properties, they often require high processing loads, leading to excessive tool wear and high energy consumption [20]. These methods effectively achieve high-density structures but face issues like porosity, oxidation, and the need for additional processing steps, increasing costs [31]. Moreover, contamination from cutting fluid and oxide layers can hinder the bonding of aluminium particles, affecting mechanical strength [32]. PM methods such as SPS involve the compaction of aluminium chips into powder-like forms before consolidation. This process will also result in high energy consumption compared with other solid-state recycling methods, therefore, it is necessary to improve this problem by shortening the sintering cycle, mass production or improving energy efficiency [33].

Given the inherent limitations of solid-state recycling processes, the remelting method has become the method of choice in industry owing to its simplicity [34]. Typically, the process involves remelting chip material followed by casting to produce new components. However, manufacturing generates chips often contaminated with cutting fluids or other substances; recycling these untreated chips can markedly reduce the metal recovery rate. Thus, the pretreatment of chips is essential. Here, we focus on two critical aspects: the pretreatment of chips and the optimization of the remelting-casting process.

Pre-treatment of chips

Cleaning methods

Thorough cleaning to remove residual cutting fluid is crucial in the process of recycling aluminium chips. Cutting fluids (e.g., oils, oil-water emulsions and so on) contain additives that may contaminate recycled aluminium. Ineffective cleaning poses environmental risks, complicates processing, and consumes resources. Moreover, conducting direct remelting recovery without any intermediate processing can result in the formation of flames or toxic gases, posing significant health risks to operating personnel [20, 35]. Current cleaning methods from literature research mainly include centrifugation, washing with solvents, extraction, ultrasonic cleaning, thermal methods, distillation and so on [17].

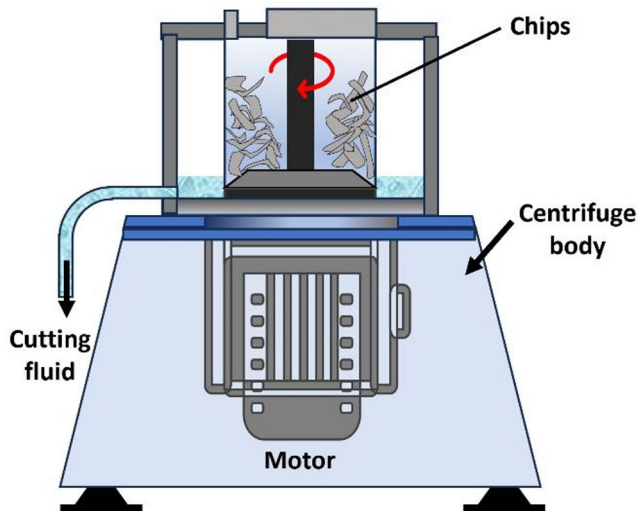


Fig. 2 Centrifugal separation system for chips cleaning. (Adapted from Ref [38, 39])

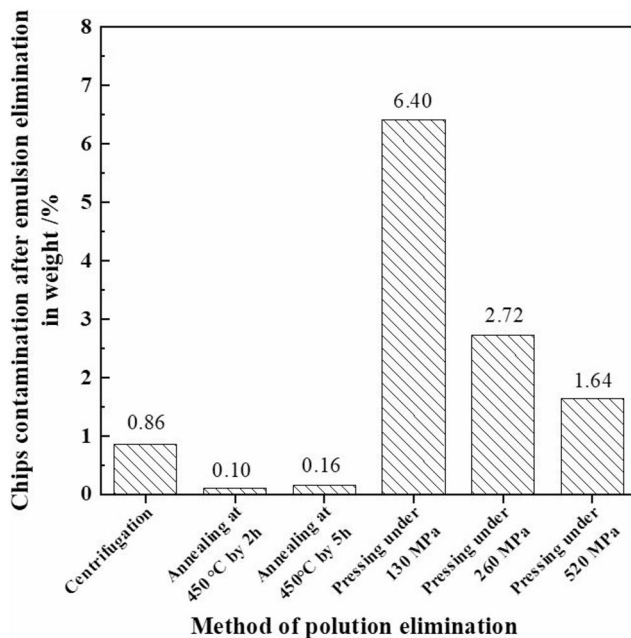


Fig. 3 Results of different emulsion elimination methods data from [37]

Centrifugation

Centrifugal separation leverages centrifugal force to remove cutting fluids from chips (Fig. 2). This method is widely adopted in industry due to its scalability. It has undergone continuous enhancement and optimization processes. Many scholars have adopted the centrifugal method to clean cutting fluid that is adhered to the chips. Wang et al. [36] combined cyclone separation with heating to purify chips, achieved high-quality recycled aluminium alloy with a 25.95% metal loss. Mateusz et al. [37] compared centrifugation, thermal,

and pressing methods (Fig. 3), finding centrifugation eco-friendly and effective (<1% contaminants), with reusable cutting fluids. Centrifugation is predominantly adopted in high-volume, low-cost sectors like automotive parts manufacturing (e.g., Mateusz et al. [37]’s study on casting Al-Si alloy). Its scalability and compatibility with cutting fluid reuse align with industries prioritizing rapid processing of bulk chips over ultra-high purity.

Ultrasonication and washing with solvents

Solvents such as water, alkaline solutions (e.g., NaOH), and organics (e.g., acetone) are used to dissolve cutting fluids. Cooper et al. [40] and Xiong [41] demonstrated that acetone reduces metal loss during remelting. Hyodo et al. [42] cleaned AA7050 chips with an alkaline solution, carefully dried them using a propane flame, and utilized them as raw materials for recycling processes. Perez-Rangel et al. [34] purified the chips by a solution of caustic soda (NaOH) in water, recycled them with the casting method, and obtained a solid aluminium bar that meets the hardness standard.

In some cases, ultrasonic cleaning is employed in conjunction with solvent cleaning to enhance effectiveness. Khamis et al. [43] and Pandey et al. [44] immersed chips in acetone with ultrasonication, achieving efficient degreasing. Kore et al. [45] crushed 6082 aluminium chips into particles smaller than 5 mm and then sieved them. The particles were cleaned with soap and acetone in an ultrasonic bath, demonstrating the effectiveness of the cleaning method in achieving good organization during solid-state recovery.

It is worth noting that titanium chip cleaning methods, similar to aluminium, provide valuable references. Bao et al. [46] and Malec et al. [47] compared the removal rates of cutting fluid attached to titanium chips in ultrasonic cleaning with different cleaning agents (Na₂CO₃, acetone-CH₃COCH₃, cyclohexane-C₆H₁₂ and so on.), the measurement results, present in Fig. 4 (b), show that the cleaning effect of Na₂CO₃ and acetone is better, with a carbon removal rate of nearly 80%, while the cleaning effect of cyclohexane is relatively poor. In the study by Denkena et al. [48], the chips undergo a sequential cleaning procedure comprising immersion in water and liquid soap, followed by thorough rinsing until foam-free. Subsequently, the chips undergo a meticulous cleaning process utilizing acetone in an ultrasonic bath, with a duration of 15 min. Finally, the specimens are subjected to air drying. For the industrial application, the high cleanliness achieved by ultrasonic-solvent methods (e.g., <1% contaminants) makes them suitable for high-performance alloy recycling, such as aerospace-grade AA7050 [42], where residual impurities critically affect mechanical properties.

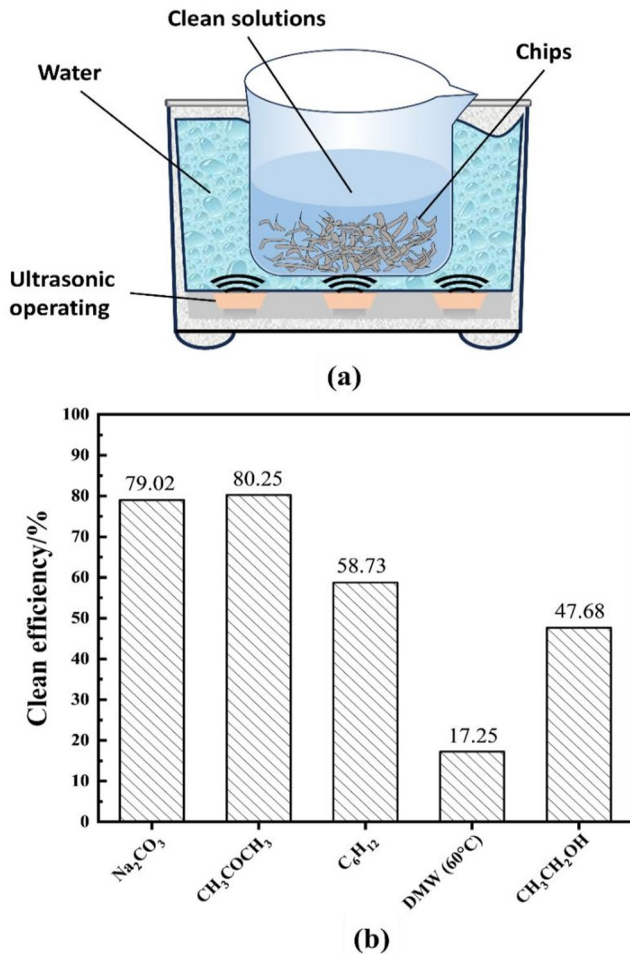


Fig. 4 Cleaning methods and results: (a) Ultrasonic cleaning machine, (b) The influence of different cleaning agent type on the clean efficiency (DMW-Demineralized Water) (data from [46, 47])

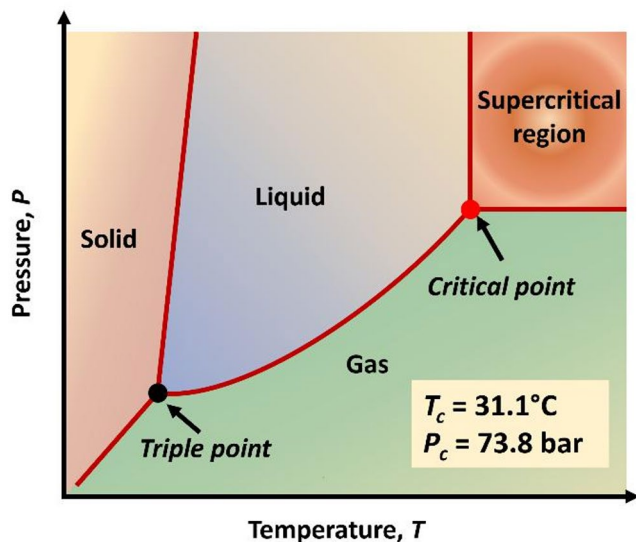


Fig. 5 Supercritical CO_2 P-T diagram [50]

Extraction

Research on extracting cutting fluid from chip surfaces dates to 1999, when scholars explored various separation methods using organic solvents and extractants to simultaneously achieve chip cleaning and cutting fluid recovery. A notable contribution came from Leffrang et al. [49], who proposed the separation of metal grinding sludge into oil and metal by using supercritical carbon dioxide (CO_2) extraction. Operating above its critical temperature (304.25 K or 31.1 °C) and pressure (73.8 bar), CO_2 behaves as a supercritical fluid—expanding to fill its container like a gas while maintaining a density akin to that of a liquid [50], as shown in Fig. 5. This method is particularly advantageous, as supercritical CO_2 exhibits solvent properties comparable to those of conventional organic solvents like benzene and carbon tetrachloride in dissolving grinding oils, yet it offers considerable environmental benefits over these traditional options. Fu et al. [51] discovered that the removal effect of cutting fluid using supercritical CO_2 extraction and washing with water-based surfactants is comparable. Moreover, Großwendt et al. [52] employed the supercritical CO_2 extraction process to clean tool steel swarf and separate cutting fluid. They subsequently utilized a densification process for metal recovery, resulting in less than 1 vol% residual contaminants in the recovered samples. Overall, supercritical CO_2 extraction can be adopted in specialized applications requiring ultra-low contamination, though its reliance on high-pressure systems limits broad industrial adoption.

Thermal methods

Thermal methods can also be employed to remove cutting fluids from machined aluminium chips. Heat application evaporates and decomposes organic cutting fluids, effectively cleaning chips without extra solvents [53]. Palimaka [21] and Gronostajski [54] report that the thermal method is also a good method to clean the chips; Cui et al. [55] conducted a study comparing the efficacy of thermal and acetone methods in degreasing aluminium chips, followed by their recycling using the CEC method. The findings revealed that utilizing the thermal method for degreasing aluminium chips, as opposed to the acetone method, led to a heightened oxidation of the aluminium chips and an increase in the thickness of the oxide film. In industry, thermal cleaning can be applied to low-grade scrap recycling (e.g., construction materials), where Cui et al. [55]’s observed oxidation losses are economically tolerable compared to upfront cost savings.

Distillation

During the distillation process, the method can be employed to remove cutting fluid from the surface of chips. Distillation removes cutting fluids from chips, enabling their recovery and reuse. Wang et al. [17] utilized the distillation method to eliminate cutting fluid from 7075 aluminium chips. They investigated the removal mechanism of this approach and, through integration with simulation techniques, identified the ideal operating temperature and processing duration for attaining the highest removal efficiency. Following the optimization process, the oil and water removal rates were remarkably enhanced, achieving a remarkable 99.7% efficiency. Distillation's high removal efficiency (99.7%) supports its use in high-value aluminium grades, where cutting fluid recovery offsets the process's energy intensity. Closed-loop fluid systems further enhance distillation's viability in resource-conscious industries like sustainable manufacturing.

Considerations such as safety of cleaning methods, equipment costs, and time consumption are crucial in actual production processes. While thermal methods offer a simple approach, they are often time-consuming and

energy-intensive, potentially exacerbating oxidation of the aluminium chips, which can negatively impact metal recovery rates [55]. Alternatively, extraction and distillation techniques allow for the simultaneous cleaning of metal chips and recovery of cutting fluid lubricating oil. However, these methods introduce complexities that may hinder overall production efficiency. In contrast, combined approaches utilizing ultrasonic cleaning and washing techniques have demonstrated high effectiveness in removing cutting fluid residues from aluminium chip surfaces [56] and are widely adopted in current production due to their simplicity, cost-effectiveness, and practicality. Nevertheless, the responsible disposal of spent solvents from these processes remains a significant concern requiring diligent management. Table 1 summarizes cleaning methods, and their associated parameters as employed in selected studies focused on aluminium alloy recycling. It is worth noting that these studies provide strong evidence for the effects of different cleaning techniques on chip recycling, almost none have evaluated the related energy consumption and environmental impact.

From the preceding discussion, it is evident that although numerous cleaning methods are currently available, achieving an optimal balance among cleaning efficiency, energy

Table 1 Clean methods employed in the chips recycling process

Ref	Cleaning Type	Operation parameters	Main outcome
[57]	Centrifugation	Centrifuged for 10 min at 400 rpm	Thermal degreasing of aluminium scrap increases the thickness of the oxide film layer
[55]	Thermal method	Thermally treated in a muffle furnace at 460 °C for 30 min	
	Washing with solvents	Cleaned with acetone	
[42]	Washing with solvents	Washed with alkaline cleaner	centrifugation was found to be both eco-friendly and successful in keeping contaminants below 1%
[35]	Centrifugation	Centrifuged for 10 min at 400 rpm.	
[43]	Ultrasonic solvent cleaning	Cleaned by ultrasonic bath using acetone solution	
[37]	Centrifugation	Centrifuged with rotation speed of 2800 rev./min	
	Thermal method	1.Heating: 450 °C for 2 h or 5 h 2.Annealing: 450 °C for 2 h	
	Pressing method	Pressed under the pressure of 130 MPa, 260 MPa and 520 MPa	
[45]	Washing with solvents, ultrasonication	Cleaned via soap solution → ultrasonic acetone bath	
[58]	Washing with solvents, ultrasonication	Cleaned via acetone then cleaned by ultrasonic bath for 30 min	
[44]	Ultrasonic solvent cleaning	Chips were cleaned by acetone in an ultrasonic bath for 30 min	
[48]	Washing with solvents, ultrasonic solvent cleaning	Chips are first washed with water and liquid soap, then cleaned in an ultrasonic acetone bath for 15 min	
[56]	Ultrasonic solvent cleaning	Best condition: Ultrasonic cleaning for 30 min with a 2:5 scrap-to-agent ratio, 60 °C temperature, and 28 kHz frequency	
[46]	Ultrasonic solvent cleaning	The chips were immersed in sodium carbonate (Na ₂ CO ₃) /acetone/cyclohexane (C ₆ H ₁₂), ultrasonically cleaned at 40 kHz, rinsed with deionized water to neutrality, and oven-dried at 105 °C for 2 h	
[52]	Extraction	Residual oil was removed via supercritical CO ₂ extraction (scCO ₂)	
[17]	Distillation	The chips underwent centrifugation, followed by distillation to remove and collect residual oil/water, with heating at 370 °C for 70 min under a 3 cm loading thickness	The removal rate of water and oil is up to 99.7% with best conditions.
[59]	Thermal method	Heated at temperatures around 250 °C for approximately 2–3 h	

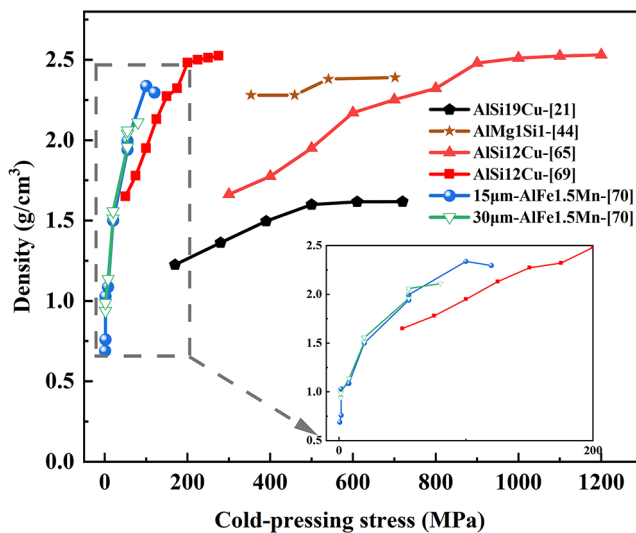


Fig. 6 Compressibility curve of different Al alloy (The data used to rebuild the diagrams were obtained from [21, 44, 65, 69, 70])

consumption, and environmental impact remains a challenge. Addressing these issues at their source may present a more effective solution. In this context, a novel approach is gaining traction within the manufacturing sector - cryogenic machining. This innovative technique eliminates the need for conventional oil-based emulsions as cutting fluid, instead employing environmentally benign alternatives such as liquid nitrogen [60] or liquid carbon dioxide [61] as cutting fluids.

In machining applications, cryogenic assistance enabled a better heat absorption in the contact zone, significantly reducing tool wear and thereby extending tool life [62]. This method also enhances surface finish quality [63]. From a chip recycling perspective, chips generated using cryogenic-assisted methods are free from contaminant residues [64], eliminating the need for cleaning during recycling. Furthermore, the reduced processing temperatures help mitigate chip oxidation, which may be helpful to improve metal recovery rates.

Chips compaction

Compaction is a critical preprocessing step in aluminium chip recycling, directly enhancing both logistical efficiency and metallurgical outcomes. By reducing chip volume and increasing density, compacted materials are easier to handle, charge into furnaces, and exhibit lower oxidative losses during remelting [65, 66]. These combined effects significantly improves overall metal recovery rates [67].

Studies consistently highlight the influence of compaction pressure on recycling efficiency. For example, Bhaskar et al. [68] demonstrated that compacting aluminium

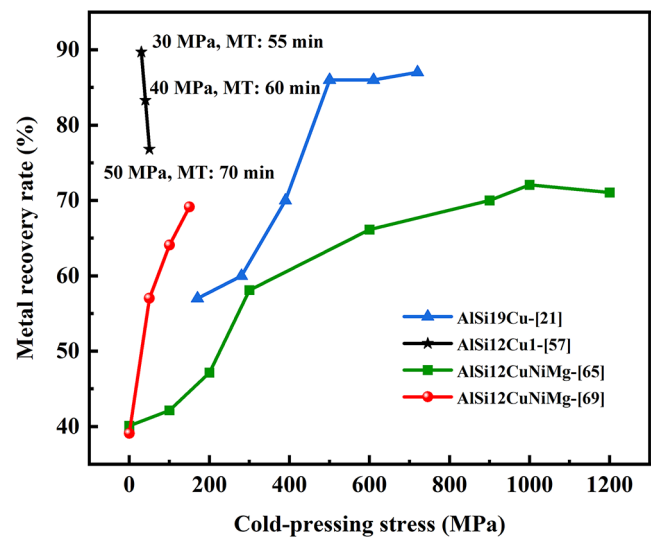


Fig. 7 The impact of different processes on the recovery of Aluminium scrap (MT: Melting time) (The data used to rebuild the diagrams were obtained from [21, 57, 65, 69])

scrap, regardless of the furnace type, reduces melt losses and enhances metal recovery. Research consistently demonstrates that varying compaction pressures result in chips with different densities, significantly influencing recycling efficiency. Despite variations in target materials across studies, the compression-density curve consistently follows a similar pattern. As illustrated in Fig. 6, increasing compaction pressure raises chip density. However, once the density approaches approximately 2.5 g/cm³, further increases in pressure yield minimal density gains.

The correlation between compaction pressure and recovery efficiency has been systematically investigated. Moloodi et al. and P. Palimaka [21, 65, 69] examined cold pressing effects on aluminium alloy chips through controlled experiments, including pure scrap recycling and flux-assisted treatments. Despite minor variations in material composition, the experimental results demonstrate that cold pressing within optimal pressure ranges significantly enhances metal recovery rates. This trend is illustrated in Fig. 7, which shows that pressing with or without flux results in measurable improvements. The established near-linear relationship suggests higher pressures generally correlate with improved yields.

However, exceptions to this trend exist. Puga et al. [57] reported lower compaction pressures enhancing recovery rates when recycling AlSi12Cu1 alloy chips blended with 66.7% ingots, as shown in Fig. 7. It is important to note that differences in melting time across the experiments may also have contributed to the observed outcomes. Similarly, Vallejo-Olivares et al. [71] compared uniaxial compaction and Moderate Pressure Torsion (MPT) for aluminium sheet

fragments. MPT-produced high-density samples generated 29 wt% dross (of charged mass) and achieved only 97% total metal recovery. This reduced yield was attributed to the compaction-induced restriction of pyrolytic decomposition of organic residues during melting. This study reveals the critical importance of removing organic residues from recycled materials. Accordingly, for aluminium alloy recycling, the optimal protocol involves eliminating organic contaminants—such as cutting fluids or other coatings—prior to compaction, thereby facilitating a higher metal recovery rate.

Collectively, these studies emphasize that compaction alone cannot maximize recovery. Effective preprocessing, particularly organic contaminant removal (e.g., cutting fluids)—is essential to mitigate dross formation. When combined with optimized pressure, such steps ensure energy-efficient recycling with minimal oxidative losses.

Remelting recycle process

Oxidation reduction using flux

The most crucial aspect of the aluminium chips recycling process is to enhance the recovery rate while preserving the performance of the recycled metal. The high oxygen affinity of aluminium inevitably leads to oxide formation during remelting [72], which degrades metal properties and increases energy consumption [57]. Fluxes counteract these effects by suppressing oxidation and enhancing melt purity, thereby improving both recovery rates and recycled metal quality [73, 74].

In conventional casting without fluxes, aluminium oxidation upon contact with water leads to the formation of white dross on the furnace surface [67]. Drosses usually contain around 60–80% aluminium, with the remaining portion being aluminium oxide. Improved fluxing and drossing techniques can reduce dross metal content to 30% [75]. According to Tenorio et al. [76], drosses present intricate structural compositions. The oxides in the dross form a continuous net structure that ensnares the aluminium within. This framework can be broken by the molten flux, which then assists in the coalescence of aluminium drops that sink into the aluminium molten, the mechanism of action of fluxes is depicted in Fig. 8. A widely employed flux is a blend of equimolar sodium chloride (NaCl) and potassium chloride (KCl), with the potential addition of fluoride to enhance the purification effect [77, 78].

Numerous studies indicate that optimal flux parameters depend on alloy composition and processing conditions. For instance, Cooper et al. [40] recovered AA6060 alloy using an equimolar NaCl–KCl flux (35% of the crucible mass) heated to 800 °C with the chips prior to casting, thereby enhancing material recovery. Similarly, Bhaskar et al. [68] employed a 3:1 NaCl–KCl mixture in Al–Si8Cu3Fe alloys at 750 °C to minimize metal loss, while Saleh et al. [16, 79] demonstrated that fluxes improve the melting of Al–Si7Mg swarf, and that melting temperature affects oxidation intensity.

The performance of flux is affected by the melting temperature, the flux-to-metal ratio, and the type of fluoride additives used. Commonly employed fluoride additives include KF, NaF, CaF₂, Na₃AlF₆, K₃AlF₆, NaAlF₄, KAlF₄, and their combinations [13]. Tenorio et al. [80] conducted a study that revealed the enhancing effect of an equimolar NaCl–KCl mixture when coupled with fluoride addition on the dissolution velocity. Research by Wan et al. [81] showed that reducing the interfacial tension between the molten aluminium and the salt flux promotes the flux's diffusion on the melt surface, facilitating the removal of solid inclusions. Additionally, lowering the interfacial tension between the salt flux and inclusions, while increasing tension between the aluminium melt and inclusions, also aids in the removal of solid inclusions by the flux. Figure 9 illustrates the impact of different fluoride additions in the flux on interfacial tension. Shi et al. [82] investigated the effects of fluoride type and content on interfacial tension using the sessile drop method [83] and observed its influence on impurity removal. Their results demonstrated a significant reduction in hydrogen content (by 40.4%) and impurity content in the alloy (by 90.2%) under optimal process conditions, resulting in improved mechanical properties. Figure 10 illustrates the impact of fluxes with varying types and fluoride contents on microstructure. Despite the differences in types and contents, all fluxes demonstrate a reduction in the shrinkage ratio. Furthermore, several studies have indicated that the use of Na₃AlF₆, NaF, and KF can significantly improve agglomeration efficiency [81, 82, 84].

This fluoride-driven interfacial optimization requires stringent concentration control in industrial settings to balance efficiency and sustainability. Ozer et al. [73] demonstrated that 5 wt% fluoride content in flux (added at 1 wt% of metal charge) as the optimal threshold for maximizing used Aluminium Beverage Cans recycling efficiency. While the addition of fluorides can improve the melt's cleaning efficiency, excessive fluoride levels may compromise the

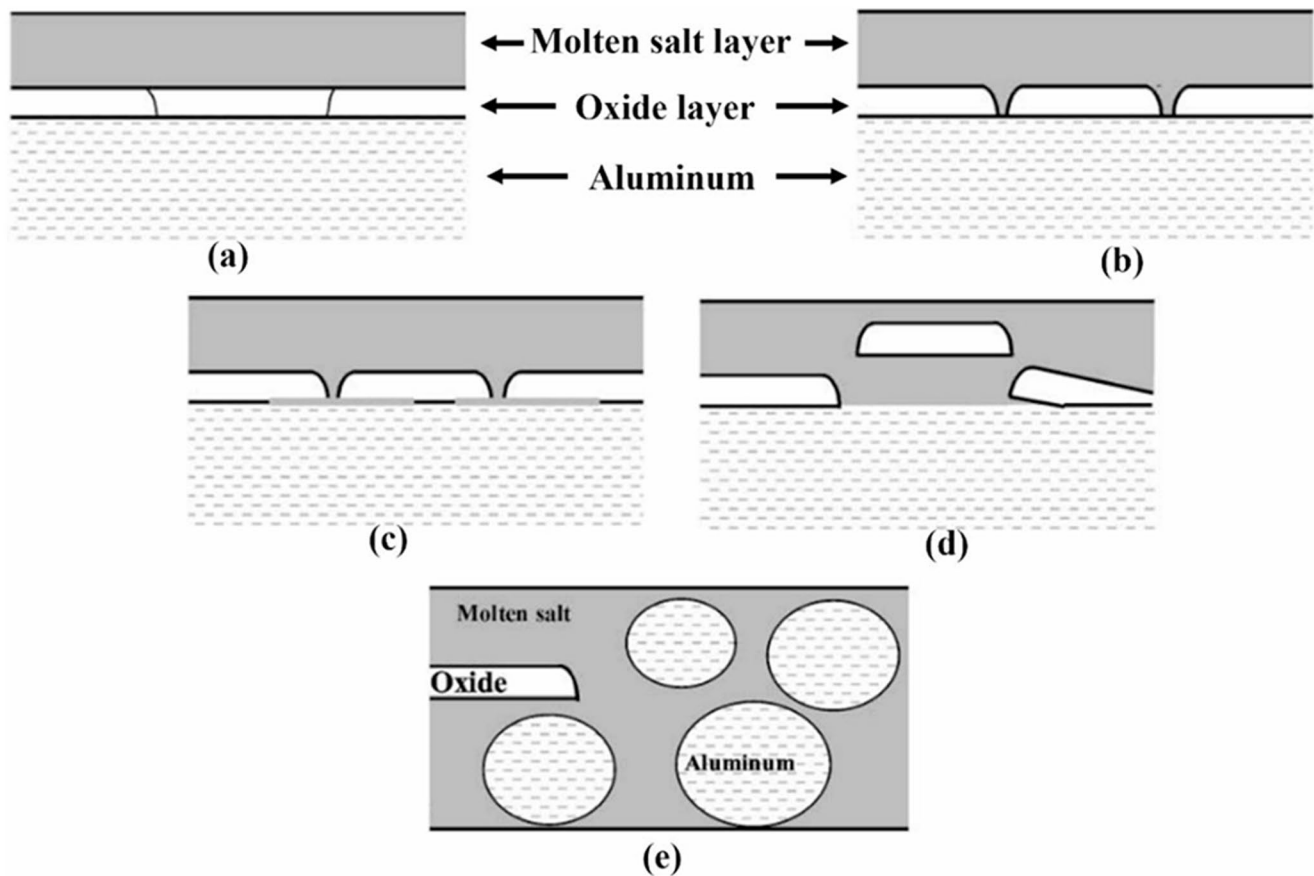


Fig. 8 Sketch of the oxide detachment caused by the molten salt: (a) Contact of molten salt and the oxide layer, (b) corrosion of oxide at the boundaries, (c) diffusion of Cl to the oxide/aluminium interface, (d) oxide detachment to the salt, and (e) aluminium drops [76]

furnace's refractoriness and pose potential environmental risks [13, 85], including hazardous gas emissions and increased greenhouse effect [86, 87]. Therefore, it is imperative to minimize fluoride addition to balance effective metal recovery with environmental considerations. In industrial processes, fluoride is typically added in concentrations ranging from 3 to 7% of the total flux weight. For scrap remelting, the amount of salt used for scrap treatment generally varies between 2% and 5% of the total scrap charge weight [88]. Table 2 summarizes the flux types employed in select studies on aluminium alloy recycling, along with their corresponding parameter selections.

Mechanical stirring and temperature control

Factors such as mechanical stirring and temperature control, in addition to regulating flux content and fluorides, play a significant role in the purification of aluminium melt

and recycling efficiency. Mechanical stirring aids in metal agglomeration, a vital process in the operation of rotary furnaces [86]. As illustrated on Fig. 11, the melt pool was agitated by a mechanical rotating impeller, with flux concurrently introduced to ensure thorough and intimate contact with the aluminium melt. Research indicates that using mechanical stirring can reduce the formation of bifilms, with its effectiveness further enhanced when used in conjunction with flux. To achieve optimal reduction of bifilms, it is recommended to employ both stirring and flux simultaneously [93]. In Fig. 12, the results of research show that the combination of mechanical stirring and flux addition effectively reduces porosity, with a higher overall rate of decrease in pore density observed in the sample.

The melting temperature is another critical factor influencing the efficiency of flux agents, as it must be carefully balanced to optimize performance. The process of fluxing is inherently dependent on temperature, requiring a

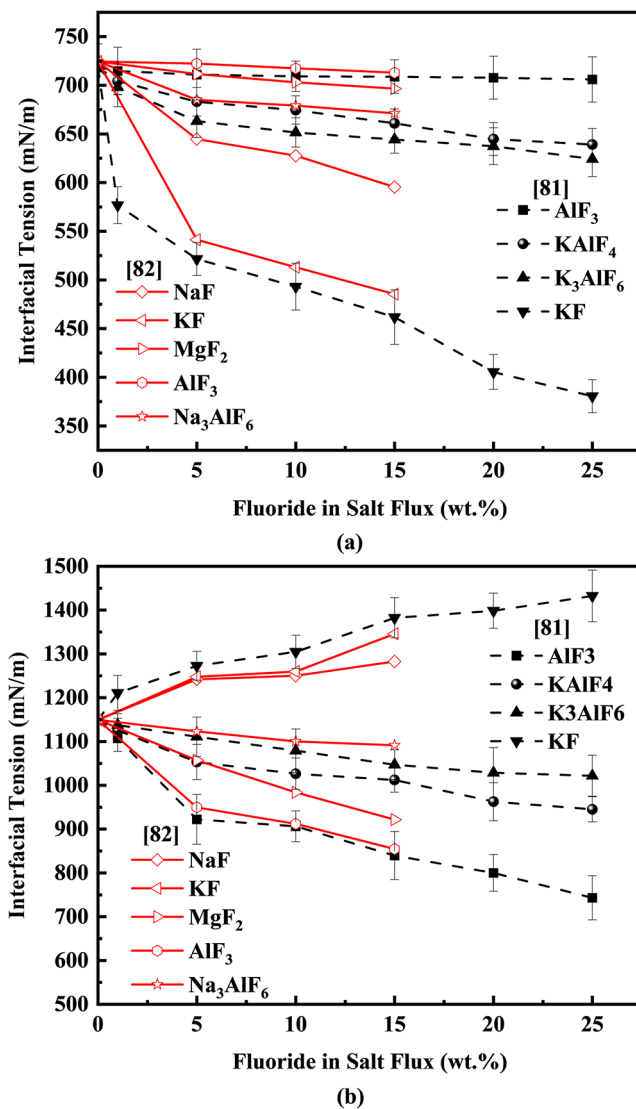


Fig. 9 Effect of some fluoride additions in the flux on the interfacial tension (a) between flux and aluminium melt and (b) between flux and aluminium oxide (The data used to rebuild the diagrams were obtained from [81, 82])

sufficiently high temperature to facilitate effective contact, reactivity, and physical separation [95]. However, excessively high temperatures can aggravate aluminium oxidation and introduce impurity ions due to reactions between the flux agent and the aluminium melt [81]. Therefore, determining the appropriate melting temperature is essential. Research by Máté et al. [90] investigated the melt cleaning efficiency of different fluxes, maintaining the furnace temperature between 730 °C and 750 °C. Their

findings indicated that fluxes with lower melting points were more efficient in removing inclusions due to higher fluidity at the processing temperature. This conclusion aligns with previous research by Majidi et al. [78] and Basakar et al. [68], who investigated the recycling processes of various aluminium alloys—specifically, A380 and A319 by Majidi et al., and Al-Si8Cu3Fe (LM24) alloy by Basakar et al. Their studies suggested optimal melting temperatures of 740 °C and 750 °C, respectively.

Figure 13 presents the recycling casting temperatures for various aluminium alloy chips, highlighting the influence of flux composition. Research indicates that employing a NaCl–KCl flux facilitates operations at relatively lower temperatures. Conversely, the introduction of fluoride raises the casting temperature to a restricted thermal range of 710 °C to 800 °C. This increase in effective casting temperature can be attributed to fluoride-induced changes in the flux viscosity and the interfacial tension between the flux and molten aluminium, which subsequently affect the oxidation kinetics [96]. Among the different alloy systems, the Al–Si alloy, which has been extensively studied, exhibits a casting temperature averaging around 740 °C. However, there is a paucity of data on other alloys, emphasizing the necessity for further research to establish optimal thermal settings. Adjusting the casting temperature according to the specific aluminium alloy and flux type is crucial. Such precise thermal control is essential not only for maximizing metal recovery yield and enhancing alloy performance but also for reducing energy consumption and minimizing environmental impact.

Conclusion

The efficient recycling of aluminium alloy chips hinges on systematic optimization of preprocessing and remelting processes. Through a comprehensive analysis of current research, this study highlights the following critical insights:

1. For cleaning methodologies: Centrifugation cleaning and the integration of solvent cleaning with ultrasonication (e.g., acetone or alkaline solutions) effectively removes cutting fluid residues, mitigating oxidation and toxic gas emissions during remelting. While extraction and distillation show promise in niche applications, their scalability is constrained by operational complexity and cost.

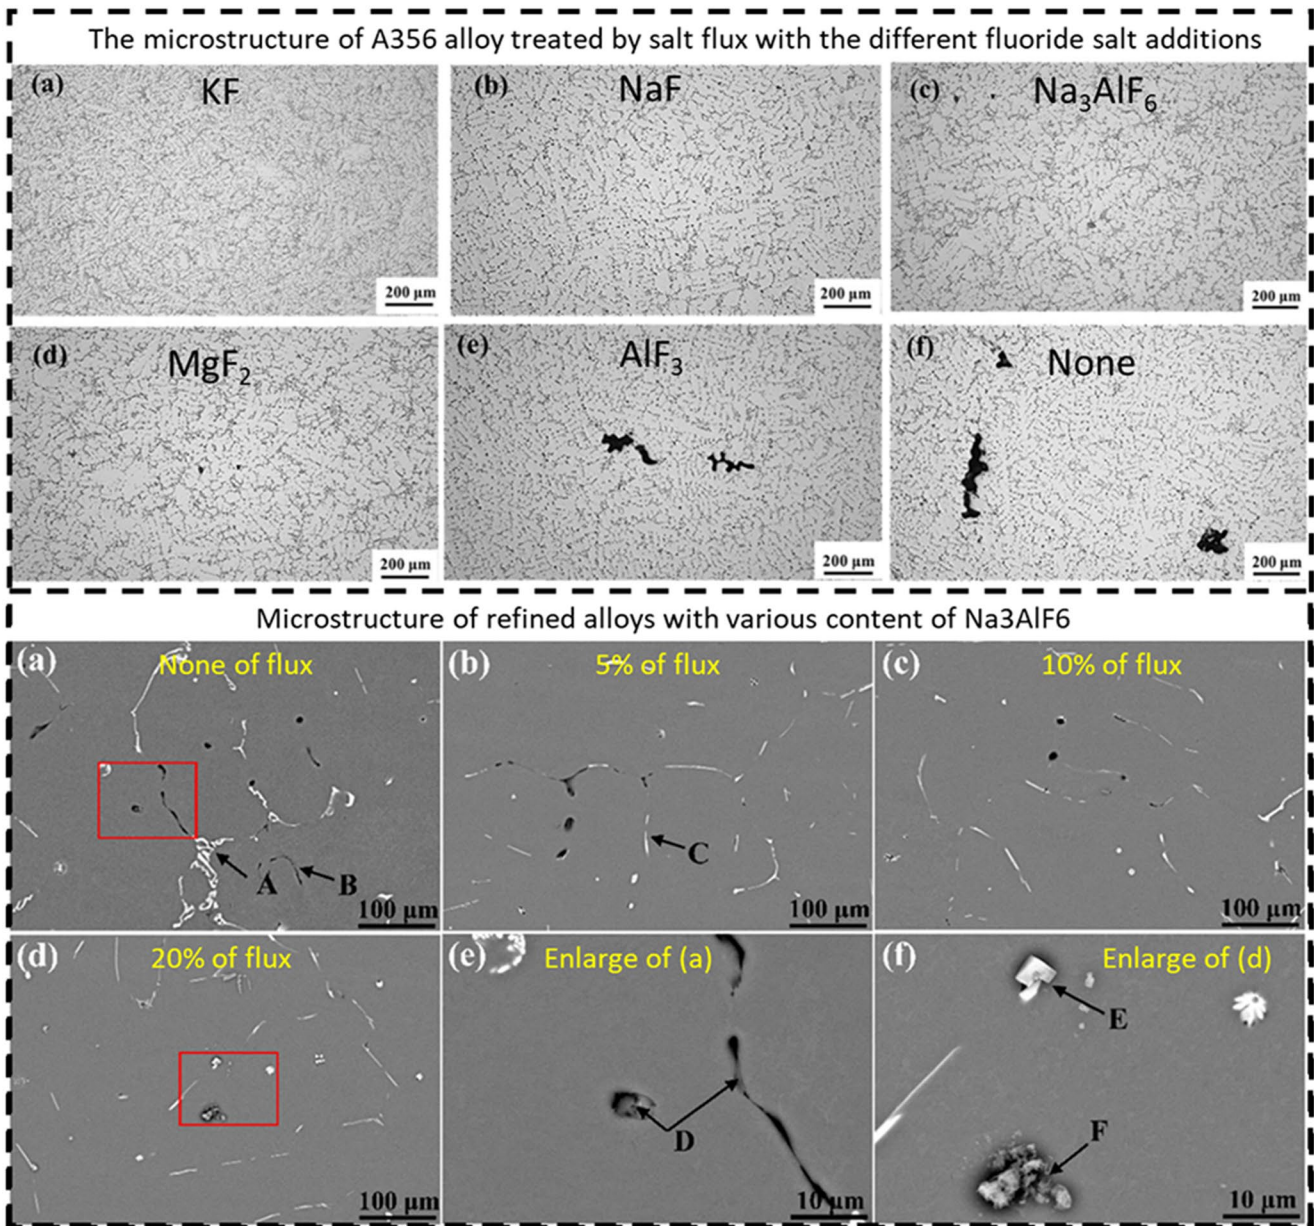


Fig. 10 The microstructure of Al alloy treated by flux with the different type and content fluoride salt additions(Image sources: References [82] and [59], rearranged.)

2. Compaction: Cold pressing enhances chip density (approaching up to 2.5 g/cm³), reducing surface oxidation and improving metal recovery rates. However, excessive compaction for uncleaned chips may impede organic residue burnout, necessitating synergistic optimization with cleaning protocols.
3. For flux engineering: NaCl-KCl-based fluxes disrupt oxide networks to promote aluminium coalescence. Fluoride additives (e.g., Na₃AlF₆ or KF) enhance flux reactivity but must be carefully controlled to mitigate


environmental risks, including furnace corrosion and hazardous emissions.

4. Mechanical stirring combined with a suitable melting temperature can improve melt homogeneity, reducing porosity and inclusion formation.

Future research directions in aluminium recycling should prioritize three synergistic pathways to reconcile process efficiency with sustainability imperatives. First, the development of low-fluoride or fluoride-free flux formulations

Table 2 Fluxing agents employed during the casting process of recycled aluminium alloys

Ref	Material	Type of Flux	Operation parameters
[69]	AA 336 (AlSi12CuNiMg)	NaCl (40%), KCl (50%), KF (10%)	weight ratio of salt to scrap was kept constant of about 2.
[89]	AA319(AlSi5Cu3)	Flux contains NaCl (12wt.%) and KCl (13wt.%)	
[90]	AlSi7Mg	Flux contains NaCl, KCl, Na ₂ SO ₄ and CaF ₂	In each cycle, flux content: 0.2% wt% of the Al melt
[68]	AlSi8Cu3Fe	NaCl and KCl in the ratio of 3:1	Flux content: 1 wt% of scrap
[91]	A356 (AlSi7Mg)	Best condition: MgCl ₂ + KCl with Na ₂ SiF ₆ addition	Flux content: 1 wt% of melt weight
[79]	AlSi7Mg	NaCl and KCl of equimolar mixture	Flux content: 10 wt% and 20wt.% of melt weight
[82]	AlSi7Mg	Best: NaCl and KCl contain 5 wt% KF	Flux content: 0.5 wt% of Al weight
[16]	AlSi7Mg	NaCl (50wt.%) and KCl (50wt.%)	Flux content: 10 wt% and 20wt.% of melt weight
[92]	AC3A (AlSi12)	Na ₂ SO ₄ (44%), NaCl (34%), Na ₂ SiF ₆ (9%), NaNO ₃ (9%), KCl (2%)	Flux content: 0.75wt.% of melt weight
[78]	A380(Al-Si9Cu3) +A319(AlSi5Cu3)	NaCl (45wt. %), KCl (45wt. %), Na ₂ SiF ₆ (8wt. %), CaF ₂ (2wt.%)	Flux content: 0.3wt.% of melt weight
[73]	A3004(AlMn1Mg1), A5182(AlMg4.5Mn0.4)	Best condition: A mixture of NaCl, KCl, Na ₂ SiF ₆ , CaF ₂ , KBF ₄ , and CaCO ₃ (fluoride in the flux: 5%)	Flux content: 1%
[19]	Aluminium foam	NaCl, KCl, and NaF with weight ratio of 3:3:1	Flux content: 35wt.% of total Al foam weight
[59]	6063(AlMg0.7Si) (40%), 6008(AlSi0.9Mg0.7) (60%)	Equimolar NaCl and KCl with 10%Na ₃ AlF ₆ + 2% Fe powder addition	Flux content: 0.25wt.% of melt weight

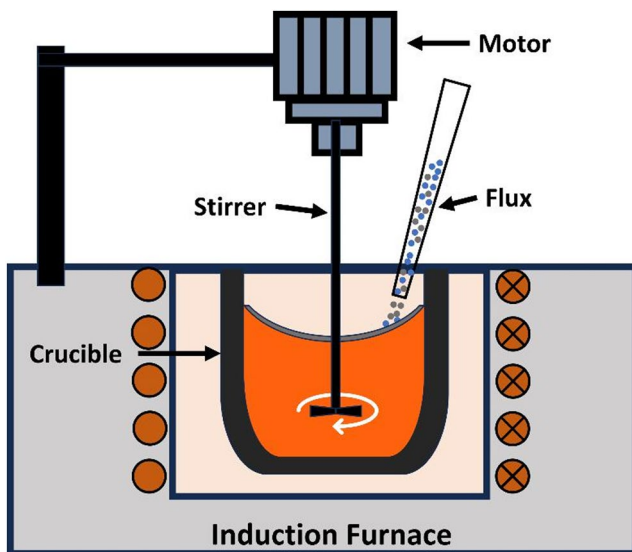**Fig. 11** Schematic image of mechanical stirring during casting. (Adapted from Ref [67, 94])

warrants intensified investigation to achieve effective oxidation suppression while minimizing environmental risks. The second pathway focuses on developing integrated processing systems that combine cleaning, compaction, and remelting operations. Within this context, emerging technologies such as cryogenic machining using liquid nitrogen or CO₂ cooling show promise for reducing contamination during preprocessing, though their process compatibility and economic viability require thorough industrial validation. The integration of these operations could significantly enhance energy efficiency and operational continuity through process intensification. Third, a comprehensive comparative analysis of the total costs and economic benefits associated with various treatment optimization strategies was conducted to identify the most promising technical solutions for diverse industrial applications. Finally, comprehensive life cycle assessments quantifying carbon footprints and resource utilization metrics across alternative recycling routes must be systematically conducted to inform industrial-scale implementation decisions.

Fig. 12 Change in (a) porosity and (b) pore density in the cast samples obtained from the fluxed-covered stagnant and stirred A356 melts (Reference [93], rearranged.)

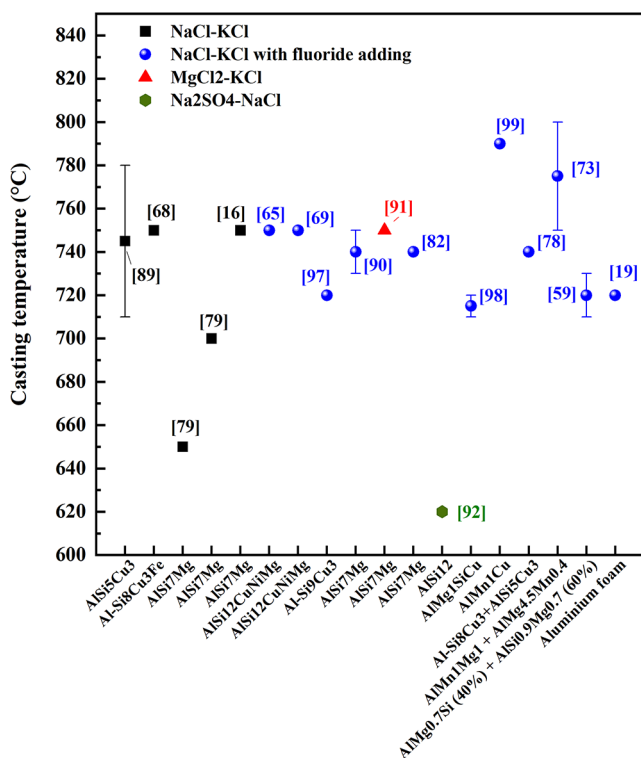
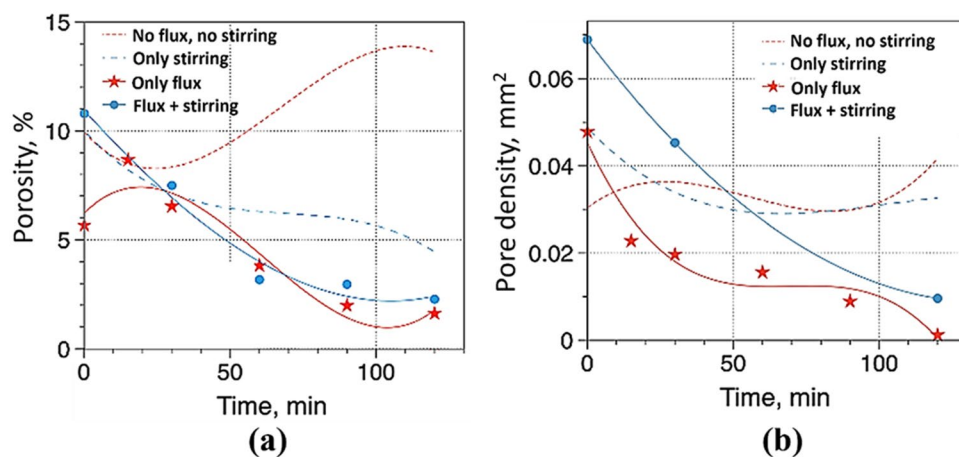


Fig. 13 Effect of different salt flux types on casting temperature of aluminium alloys' chips (The data used to rebuild the diagrams were obtained from [16, 19, 59, 65, 68, 69, 73, 78, 79, 82, 89–92, 97–99])

Supplementary Information The online version contains supplementary material available at <https://doi.org/10.1007/s12289-025-01904-9>.

Acknowledgements This work of the project supported by the China Scholarship Council (CSC), the project of “National constructed high-level university-sponsored graduate programs” (Funding number: 202308120021).

Funding Open access funding provided by Arts et Metiers Institute of Technology.

Data availability No datasets were generated or analysed during the current study.

Declarations

Conflict of interest The authors declare no conflicts of interest.

Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

References

- Sun Y (2023) The use of aluminum alloys in structures: review and outlook. *Structures* 57:105290. <https://doi.org/10.1016/j.istruc.2023.105290>
- Li S, Yue X, Li Q et al (2023) Development and applications of aluminum alloys for aerospace industry. *J Mater Res Technol* 27:944–983. <https://doi.org/10.1016/j.jmrt.2023.09.274>
- Aglawe K, Giri S, Dhande M, Shelare S (2023) Application of aluminum alloys in aviation industry: A review. Baghdad, Iraq, p 020064
- Vasanthakumar P, Sekar K, Venkatesh K (2019) Recent developments in powder metallurgy based aluminium alloy composite for aerospace applications. *Mater Today: Proc* 18:5400–5409. <https://doi.org/10.1016/j.matpr.2019.07.568>
- Dursun T, Soutis C (2014) Recent developments in advanced aircraft aluminium alloys. *Mater Des* (1980–2015) 56:862–871. <http://doi.org/10.1016/j.matdes.2013.12.002>
- Hirsch J (2014) Recent development in aluminium for automotive applications. *Trans Nonferrous Met Soc China* 24:1995–2002. [https://doi.org/10.1016/S1003-6326\(14\)63305-7](https://doi.org/10.1016/S1003-6326(14)63305-7)
- Wahid MA, Siddiquee AN, Khan ZA (2020) Aluminum alloys in marine construction: characteristics, application, and problems from a fabrication viewpoint. *Mar Syst Ocean Technol* 15:70–80. <https://doi.org/10.1007/s40868-019-00069-w>
- Mandatsy MOUNGOMO JB, Nganga Kouya D, Songmene V (2016) Aluminium Machining Chips Formation, Treatment & Recycling:

- A Review. *KEM* 710:71–76. <https://doi.org/10.4028/www.scientific.net/KEM.710.71>
9. Raabe D, Ponge D, Uggowitzer PJ et al (2022) Making sustainable aluminum by recycling scrap: the science of dirty alloys. *Prog Mater Sci* 128:100947. <https://doi.org/10.1016/j.pmatsci.2022.100947>
 10. Sigworth GK (2021) Refining of secondary aluminum: important chemical factors. *JOM* 73:2594–2602. <https://doi.org/10.1007/s11837-021-04774-z>
 11. Moungho JBM, Nganga-Kouya D, Songmene V et al (2016) Machinability study of recycled aluminum cans and machining chips. *Int J Adv Manuf Technol* 87:2551–2566. <https://doi.org/10.1007/s00170-016-8564-x>
 12. Djurdjevic M, Manasijevic S, Mihailović M, Stopic S (2023) From bauxite as a critical material to the required properties of cast aluminum alloys for use in electro automotive parts. *Metals* 13:1796. <https://doi.org/10.3390/met13111796>
 13. Milani V, Timelli G (2023) Solid salt fluxes for molten aluminum Processing—A. *Rev Met* 13:832. <https://doi.org/10.3390/met13050832>
 14. Samberger S, von Czarnowski P, Pogatscher S, Hirsch J (2024) New strategies to improve recycling and reduce CO₂-emission of aluminum production and processing. *J Light Metal Weld* 62:119–132. <https://doi.org/10.11283/jlwa.62.119>
 15. Koch A, Bonhage M, Teschke M et al (2020) Electrical resistance-based fatigue assessment and capability prediction of extrudates from recycled field-assisted sintered EN AW-6082 aluminium chips. *Mater Charact* 169:110644. <https://doi.org/10.1016/j.matchar.2020.110644>
 16. Samian AZ, Saleh A, Nazri NJ et al (2024) The impact of heating temperature and flux ratio on the In-Situ casting technique as a direct recycling of AlSi7Mg machining chips. *ARMNE* 15:31–40. <https://doi.org/10.37934/armne.15.1.3140>
 17. Wang J, Zhang S, Liu B et al (2023) Molecular dynamics simulation and experiment study on technology and mechanism of removing oil and water from aluminum chips. *Trans Nonferrous Met Soc China* 33:3871–3884. [https://doi.org/10.1016/S1003-6326\(23\)66377-0](https://doi.org/10.1016/S1003-6326(23)66377-0)
 18. Krolo J, Dumanić Labetić I, Lela B, Bilušić M (2024) Thixoforming of the hot extruded aluminum AlSi9Cu3(Fe) machining chips. *Metals* 14:796. <https://doi.org/10.3390/met14070796>
 19. Zhang Z, Yang L, Zhao S et al (2022) Effects of stirring speed and flux composition on the recycling of aluminium foams. *Mater Res Express* 9:106516. <https://doi.org/10.1088/2053-1591/ac9958>
 20. Wan B, Chen W, Lu T et al (2017) Review of solid state recycling of aluminum chips. *Resour Conserv Recycl* 125:37–47. <https://doi.org/10.1016/j.resconrec.2017.06.004>
 21. Palimaka P (2020) Thermal cleaning and melting of fine aluminium alloy chips. *Arch Foundry Eng* 91–96. <https://doi.org/10.24425/afe.2020.133353>
 22. Mahmoud SED, El-Gamasy R, El-Wahab AAA (2024) Mechanical behavior of hot extruded aluminum 6082 chip. *Sci Rep* 14:6381. <https://doi.org/10.1038/s41598-024-55151-0>
 23. Pei Y, Ma H, Yuan M, Teng B (2024) Solid state recycling of Mg–Gd–Y–Zn–Zr alloy chips by isothermal sintering and equal channel angular pressing. *J Magnesium Alloys* 12:2725–2740. <https://doi.org/10.1016/j.jma.2022.11.007>
 24. Shahrom MS, Yusoff AR (2017) Cyclic extrusion compression back pressure technique for hot forging process in direct recycling of aluminium 6061 machining chip. *J Manuf Process* 29:1–9. <https://doi.org/10.1016/j.jmapro.2017.07.003>
 25. Asadi P, Akbari M, Armani A et al (2023) Recycling of brass chips by sustainable friction stir extrusion. *J Clean Prod* 418:138132. <https://doi.org/10.1016/j.jclepro.2023.138132>
 26. Abd El Aal MI (2021) Recycling of al chips and al chips composites using high-pressure torsion. *Mater Res Express* 8:056514. <https://doi.org/10.1088/2053-1591/abff76>
 27. Zhang J, Pang X, Chen H et al (2019) Process and forming performance of ploughing extrusion cutting for recycling of metal chips. *J Mater Process Technol* 274:116283. <https://doi.org/10.1016/j.jmatprotec.2019.116283>
 28. Koch A, Henkel T, Walther F (2021) Mechanism-oriented characterization of the anisotropy of extruded profiles based on solid-state recycled EN AW-6060 aluminum chips. *Eng Fail Anal* 121:105099. <https://doi.org/10.1016/j.engfailanal.2020.105099>
 29. Cisló CN, Kronthaler B, Buchmayr B, Weiß C (2020) Solid state recycling of aluminum alloy chips via pulsed electric current sintering. *JMMP* 4:23. <https://doi.org/10.3390/jmmp4010023>
 30. Lu X, Zhang Z, Hiraki T et al (2022) A solid-state electrolysis process for upcycling aluminium scrap. *Nature* 606:511–515. <https://doi.org/10.1038/s41586-022-04748-4>
 31. Rahim SNA, Lajis MA, Ariffin S (2015) A review on recycling aluminum chips by hot extrusion process. *Procedia CIRP* 26:761–766. <https://doi.org/10.1016/j.procir.2015.01.013>
 32. Güley V, Ben Khalifa N, Tekkaya AE (2010) Direct recycling of 1050 aluminum alloy scrap material mixed with 6060 aluminum alloy chips by hot extrusion. *Int J Mater Form* 3:853–856. <https://doi.org/10.1007/s12289-010-0904-z>
 33. Dufflou JR, Tekkaya AE, Haase M et al (2015) Environmental assessment of solid state recycling routes for aluminium alloys: can solid state processes significantly reduce the environmental impact of aluminium recycling? *CIRP Ann* 64:37–40. <https://doi.org/10.1016/j.cirp.2015.04.051>
 34. Perez-Rangel NY, Florez-Solano E, Hoyos Palacio LM (2020) Exploitation of chips and scrap aluminum through physical processes for the development of aluminum sheets and bars. *J Phys: Conf Ser* 1587:012027. <https://doi.org/10.1088/1742-6596/1587/1/012027>
 35. Puga H, Barbosa J, Ribeiro CS (2012) Factors affecting the metal recovery yield during induction melting of aluminium Swarf. *MSF* 730–732:781–786. <https://doi.org/10.4028/www.scientific.net/MSF.730-732.781>
 36. Wang J, Zhang S, Lv Z et al (2023) Microstructure evolution and properties comparison of industrial grade-maintained 7050-T7451 plate recycled from machining chips. *J Mater Res Technol* 25:6011–6026. <https://doi.org/10.1016/j.jmrt.2023.06.233>
 37. Wędrychowicz M, Wzorek Ł, Tokarski T et al (2016) Recycling without melting: an alternative approach to aluminum scrap recovery. *KEM* 682:284–289. <https://doi.org/10.4028/www.scientific.net/KEM.682.284>
 38. Lee C-M, Choi Y-H, Ha J-H, Woo W-S (2017) Eco-friendly technology for recycling of cutting fluids and metal chips: A review. *Int J Precis Eng Manuf-Green Tech* 4:457–468. <https://doi.org/10.1007/s40684-017-0051-9>
 39. Yamamoto T, Watanabe N, Fukui K, Yoshida H (2009) Effect of inner structure of centrifugal separator on particle classification performance. *Powder Technol* 192:268–272. <https://doi.org/10.1016/j.powtec.2009.01.003>
 40. Cooper DR, Song J, Gerard R (2018) Metal recovery during melting of extruded machining chips. *J Clean Prod* 200:282–292. <https://doi.org/10.1016/j.jclepro.2018.07.246>
 41. Xiong B (2015) Optimization of recycling process of die cast aluminum A380 machining chips. *Electronic Theses and Dissertations*, University of Windsor
 42. Hyodo A, Bolfarini C, Ishikawa TT (2012) Chemistry and tensile properties of a recycled AA7050 via spray forming and ECAP/E. *Mat Res* 15:739–748. <https://doi.org/10.1590/S1516-1439201205000097>

43. Khamis SS, Lajis MA, Albert RAO (2015) A sustainable direct recycling of aluminum chip (AA6061) in hot press forging employing response surface methodology. *Procedia CIRP* 26:477–481. <https://doi.org/10.1016/j.procir.2014.07.023>
44. Pandey AK, Prajapati N, Nayak KC, Date PP (2019) Sustainable manufacturing process for recycling of aluminum alloy waste into direct product by high-pressure torsion process. *Materials Today: Proceedings* 18:3099–3108. <https://doi.org/10.1016/j.matpr.2019.07.183>
45. Kore AS, Nayak KC, Date PP (2017) Formability of aluminium sheets manufactured by solid state recycling. *J Phys: Conf Ser* 896:012007. <https://doi.org/10.1088/1742-6596/896/1/012007>
46. Wang Z, Bao Y, Wang M (2022) The effect of different cleaning methods for titanium chips on the carbon content of ferrotitanium after remelting. *J Mater Res Technol* 18:2208–2216. <https://doi.org/10.1016/j.jmrt.2022.03.115>
47. Malec W, Cwolek B, Brudny A et al (2022) Development of process conditions for the Preparation of copper alloys Post-Production chips for the continuous casting process. *Arch Foundry Eng* 43–50. <https://doi.org/10.24425/afe.2023.144294>
48. Denkena B, Krödel A, Pyzdek F et al (2021) Recycled titanium chips as initial product for the atomisation process of powders for additive manufacturing to increase resource efficiency
49. Leffrang U, Büttner K, Schwing R, Ring K (1999) To revert grinding sludge into oil and metal-An application for supercritical fluid extraction in a technical scale. In: *High Pressure Chemical Engineering - Proceedings of the Internal Meeting of the GVC-Fachausschuss Hochdruckverfahrenstechnik*. pp 305–307
50. Cabeza LF, De Gracia A, Fernández AI, Farid MM (2017) Supercritical CO₂ as heat transfer fluid: A review. *Appl Therm Eng* 125:799–810. <https://doi.org/10.1016/j.applthermaleng.2017.07.049>
51. Fu H, Matthews MA (1999) Separation processes for recovering alloy steels from grinding sludge: supercritical carbon dioxide extraction and aqueous cleaning. *Sep Sci Technol* 34:1411–1427. <https://doi.org/10.1080/01496399908951100>
52. Großwendt F, Bürk V, Kopanka B et al (2023) A novel powder-metallurgical eco-friendly recycling process for tool steel grinding sludge. *J Clean Prod* 392:136329. <https://doi.org/10.1016/j.jclepro.2023.136329>
53. Lim SC, Kim DH, Kim JS et al (1997) Decomposition kinetics of machining oil and oxidation of A356.2 aluminium alloy in aluminium recycling process. *Mater Sci Technol* 13:859–864. <https://doi.org/10.1179/mst.1997.13.10.859>
54. Gronostajski J, Marciniak H, Matuszak A (2000) New methods of aluminium and aluminium-alloy chips recycling. *J Mater Process Technol* 106:34–39. [https://doi.org/10.1016/S0924-0136\(00\)00634-8](https://doi.org/10.1016/S0924-0136(00)00634-8)
55. Cui JR, Guo W, Roven HJ et al (2010) Recycling of aluminum scrap by severe plastic deformation. *MSF* 667–669:1177–1182. <https://doi.org/10.4028/www.scientific.net/MSF.667-669.1177>
56. Wang R, Wang M, Gao S et al (2022) Compound purification of nickel base Superalloy cutting waste through special cleaning agent attached to ultrasonic stirring. *J Clean Prod* 378:134548. <https://doi.org/10.1016/j.jclepro.2022.134548>
57. Puga H, Barbosa J, Soares D et al (2009) Recycling of aluminium Swarf by direct incorporation in aluminium melts. *J Mater Process Technol* 209:5195–5203. <https://doi.org/10.1016/j.jmatprotec.2009.03.007>
58. Kuddus S, Mustapa MS, Ibrahim MR et al (2017) Microstructures and tensile characteristics on direct recycled aluminium chips AA6061/Al powder by hot pressing method. *MSF* 909:9–14. <https://doi.org/10.4028/www.scientific.net/MSF.909.9>
59. Cai Y, Song D, Yang D et al (2024) Effect of Na₃AlF₆ contents in refining flux on 3D characteristics of pore and mechanical properties of recycled Al-Mg-Si alloy. *Mater Today Commun* 39:108797. <https://doi.org/10.1016/j.mtcomm.2024.108797>
60. Kaynak Y, Karaca HE, Noebe RD, Jawahir IS (2013) Tool-wear analysis in cryogenic machining of NiTi shape memory alloys: A comparison of tool-wear performance with dry and MQL machining. *Wear* 306:51–63. <https://doi.org/10.1016/j.wear.2013.05.011>
61. Machai C, Biermann D (2011) Machining of β -titanium-alloy Ti–10V–2Fe–3Al under cryogenic conditions: cooling with carbon dioxide snow. *J Mater Process Technol* 211:1175–1183. <https://doi.org/10.1016/j.jmatprotec.2011.01.022>
62. Gupta MK, Niesłony P, Korkmaz ME et al (2023) Potential use of cryogenic cooling for improving the tribological and tool wear characteristics while machining aluminum alloys. *Tribol Int* 183:108434. <https://doi.org/10.1016/j.triboint.2023.108434>
63. Yildiz Y, Nalbant M (2008) A review of cryogenic cooling in machining processes. *Int J Mach Tools Manuf* 48:947–964. <https://doi.org/10.1016/j.ijmactools.2008.01.008>
64. Jamil M, Khan AM, Hegab H et al (2019) Effects of hybrid Al₂O₃-CNT nanofluids and cryogenic cooling on machining of Ti–6Al–4V. *Int J Adv Manuf Technol* 102:3895–3909. <https://doi.org/10.1007/s00170-019-03485-9>
65. Amini Mashhadi H, Moloodi A, Golestanipour M, Karimi EZV (2009) Recycling of aluminium alloy turning scrap via cold pressing and melting with salt flux. *J Mater Process Technol* 209:3138–3142. <https://doi.org/10.1016/j.jmatprotec.2008.07.020>
66. Simon L, Moraes CAM, Modolo RCE et al (2017) Recycling of contaminated metallic chip based on eco-efficiency and eco-effectiveness approaches. *J Clean Prod* 153:417–424. <https://doi.org/10.1016/j.jclepro.2016.11.058>
67. Brough D, Jouhara H (2020) The aluminium industry: A review on state-of-the-art technologies, environmental impacts and possibilities for waste heat recovery. *Int J Thermofluids* 1–2:100007. <https://doi.org/10.1016/j.ijft.2019.100007>
68. Bhaskar M, Anand G, Nallusamy T et al (2022) Recycling of aluminum chips in die casting foundry. *Inter Metalcast* 16:1575–1583. <https://doi.org/10.1007/s40962-021-00707-3>
69. Moloodi A, Amini H, Karimi EZV, Golestanipour M (2011) On the role of both salt flux and cold pressing on physical and mechanical properties of aluminum alloy scraps. *Mater Manuf Processes* 26:1207–1212. <https://doi.org/10.1080/10426914.2011.564250>
70. Vallejo-Olivares A, Philipson H, Gökelman M et al (2021) Compaction of aluminium foil and its effect on oxidation and recycling yield. In: Perander L (ed) *Light metals 2021*. Springer International Publishing, Cham, pp 735–741
71. Vallejo-Olivares A, Gertjegerdes T, Høgåsen S et al (2024) Effects of compaction and thermal Pre-treatments on generation of Dross and Off-Gases in aluminium recycling. *J Sustain Metall* 10:69–82. <https://doi.org/10.1007/s40831-023-00773-3>
72. Liu J, Wang Q, Qi Y (2019) Atomistic simulation of the formation and fracture of oxide bifilms in cast aluminum. *Acta Mater* 164:673–682. <https://doi.org/10.1016/j.actamat.2018.11.008>
73. Ozer G, Yuksel C, Comert ZY, Guler KA (2013) The effects of process parameters on the recycling efficiency of used aluminium beverage cans (UBCs). *Mater Test* 55:396–400. <https://doi.org/10.3139/120.110448>
74. Gillett HW, James GM (1916) *Melting aluminium chips*. U.S. Government Printing Office
75. Gallo R (2001) Development, evaluation, and application of granular and powder fluxes in transfer ladles, crucible, and reverberatory furnaces
76. Tenorio JAS, Espinosa DCR (2002) Effect of salt/oxide interaction on the process of aluminum recycling. *J Light Met* 2:89–93. [https://doi.org/10.1016/S1471-5317\(02\)00027-5](https://doi.org/10.1016/S1471-5317(02)00027-5)

77. Utigard TA, Roy RR, Friesen K (2001) Properties of fluxes used in molten aluminium processing. *High Temp Mater Processes (London)* 20:303–308. <https://doi.org/10.1515/HTMP.2001.20.3-4.303>
78. Majidi O, Shabestari SG, Aboutalebi MR (2007) Study of fluxing temperature in molten aluminum refining process. *J Mater Process Technol* 182:450–455. <https://doi.org/10.1016/j.jmatprotec.2006.09.003>
79. Azmi AA, Samian AZ (2023) Effect of flux application on aluminium-silicon alloy (Al-SiMg) machining chips for in-situ casting process. 4
80. Tenorio JAS, Carboni MC, Espinosa DCR (2001) Recycling of aluminum – effect of fluoride additions on the salt viscosity and on the alumina dissolution. *J Light Met* 1:195–198. [https://doi.org/10.1016/S1471-5317\(01\)00013-X](https://doi.org/10.1016/S1471-5317(01)00013-X)
81. Wan B, Li W, Liu F et al (2020) Determination of fluoride component in the multifunctional refining flux used for recycling aluminum scrap. *J Mater Res Technol* 9:3447–3459. <https://doi.org/10.1016/j.jmrt.2020.01.082>
82. Shi M, Li Y (2022) Performance improvement in aluminum alloy treated by salt flux with different fluorides. *J Mater Eng Perform* 32:3065–3072. <https://doi.org/10.1007/s11665-022-07306-1>
83. Bashforth F, Adams JC (1883) An attempt to test the theories of capillary action by comparing the theoretical and measured forms of drops of fluid. University
84. Roy RR, Sahai Y (1997) Coalescence behavior of aluminum alloy drops in molten salts. *Mater Trans JIM* 38:995–1003. <https://doi.org/10.2320/matertrans1989.38.995>
85. Engel R (2015) Refractory considerations. *Aluminium Int Today* 27:23
86. Xiao Y, Reuter MA, Boin U (2005) Aluminium recycling and environmental issues of salt slag treatment. *J Environ Sci Health Part A* 40:1861–1875. <https://doi.org/10.1080/10934520500183824>
87. Das P, Pooja (2021) Fluorine: risk assessment, environmental, and health hazard. In: hazardous gases. Elsevier, pp 153–167
88. Ireland DT (2000) Method and composition for aluminum recycle using salt flux
89. Velasco E, Nino J (2011) Recycling of aluminium scrap for secondary Al-Si alloys. *Waste Manag Res* 29:686–693. <https://doi.org/10.1177/0734242X10381413>
90. Máté M, Tokár M, Fegyvermeki G, Gyarmati G (2019) The comparative analysis of the inclusion removal efficiency of different fluxes. *Arch Foundry Eng* 53–58. <https://doi.org/10.24425/afe.2020.131302>
91. Yüksel Ç, Dişpınar D, Çiğdem M (2023) An analytical approach for the correlation between bifilm index and tensile properties of AlSi7Mg0.3 (A356) aluminum alloy cleaned via rotary degassing and different fluxes. *Inter Metalcast* 17:1615–1627. <https://doi.org/10.1007/s40962-022-00882-x>
92. Dhaneswara D, Alaydrus MN, Fatriansyah JF, Churiyanto M (2024) Cleaning flux based on sodium sulfate and sodium chloride as an oxide inclusion cleaner in AC3A aluminum smelting recycling. Depok, Indonesia, p 070004
93. Ghanaatian M-H, Raiszadeh R (2022) Effect of different methods for removing bifilm defects from A356 aluminum alloy. *Metall Mater Trans B* 53:503–511. <https://doi.org/10.1007/s11663-021-02386-1>
94. Madhukar P, Selvaraj N, Gujjala R, Rao CSP (2019) Production of high performance AA7150-1% SiC nanocomposite by novel fabrication process of ultrasonication assisted stir casting. *Ultrason Sonochem* 58:104665. <https://doi.org/10.1016/j.ultsonch.2019.104665>
95. Utigard TA (1998) The properties and uses of fluxes in molten aluminum processing. *JOM* 50:38–43. <https://doi.org/10.1007/s11837-998-0285-7>
96. Linden JHLV, Stewart DL (2016) Molten salt flux composition effects in aluminum scrap remelting. In: Grandfield JF, Eskin DG (eds) *Essential readings in light metals: volume 3 cast shop for aluminum production*. Springer International Publishing, Cham, pp 173–180
97. Xiong B, Zhang X, Li F et al (2016) Recycling of aluminum A380 machining chips. In: Hyland M (ed) *Light metals 2015*. Springer International Publishing, Cham, pp 1011–1015
98. Akhtar N, Ahmed R, Arfan M, Ali MN (2017) Mechanical performance and fracture behavior of recycled AA6061-T6 alloy melted from aluminium chips. *Int J Manuf Mater Mech Eng (IJMMME)* 7:1–17. <https://doi.org/10.4018/IJMMME.2017010101>
99. Capuzzi S, Kvithyld A, Timelli G et al (2018) Coalescence of clean, coated, and deoiled aluminum for various salts, and Salt-Scrap ratios. *J Sustain Metall* 4:343–358. <https://doi.org/10.1007/s40831-018-0176-2>

Publisher's note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.