



Science Arts & Métiers (SAM)

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>

Handle ID: <http://hdl.handle.net/10985/21995>



This document is available under CC BY-NC-ND license

To cite this version :

Citra Yanto Ciki PURBA, Myriam CHAPLAIN, Jean-Luc COUREAU, Robert COLLET, Guillaume POT - Assessment of bonding durability of CLT and glulam made from oak and mixed poplar-oak according to bonding pressure and glue type - Construction and Building Materials - Vol. 335, p.127345 - 2022

1 **Assessment of bonding durability of CLT and glulam made from oak and**
2 **mixed poplar-oak according to bonding pressure and glue type**

3 Citra Yanto Ciki Purba, Guillaume Pot, Robert Collet, Myriam Chaplain, Jean-Luc Coureau

5 **Abstract**

6 The objective of this study is to evaluate the influence of manufacturing parameters on the bonding quality of CLT
7 and glulam made from oak and mixing poplar and oak species. Studied bonding parameters were bonding pressure
8 and glue type. To test the bonding durability, the specimens were subjected to a vacuum pressure cycle followed
9 by drying to the initial weight. The bonding quality was then measured from delamination, residual shear strength,
10 and wood failure percentage (WFP). Bonding pressure and type of glue appeared to have a significant influence
11 on the bonding quality of CLT or glulam, with also significant interactions with the kind of species bonded. If a
12 0.8 N/mm² bonding pressure seemed to provide better results, vacuum-pressed (0.085 N/mm² bonding pressure)
13 mixed poplar-oak CLT or glulam glued with PUR were very close to reaching the requirements of the standards.
14 Generally, CLT or glulam entirely made from oak delaminated more than the mixed specimens. However, their
15 residual shear strength can be comparable or even superior to what was obtained with mixed poplar-oak specimens.
16 As a result, residual shear strength after delamination test may be interesting to consider as an additional criterion
17 to assess glue line integrity of hardwood CLT or glulam products.

18 **Keywords:**Engineered wood products,hardwood, gluing, delamination, shear

20 Citra Yanto Ciki Purba

21 Arts et Métiers Institute of Technology, LaBoMaP

22 Rue Porte de Paris, 71250 Cluny, France

23 e-mail: citra.purba@ensam.eu

25 Guillaume Pot

26 Arts et Métiers Institute of Technology, LaBoMaP

27 Rue Porte de Paris, 71250 Cluny, France

29 Robert Collet

30 Arts et Métiers Institute of Technology, LaBoMaP

31 Rue Porte de Paris, 71250 Cluny, France

33 Myriam Chaplain

34 Université de Bordeaux UMR 5295, Institut de Mécanique et d'Ingénierie – Bordeaux (I2M)

35 Bordeaux F-33000, France

37 Jean-Luc Coureau

38 Université de Bordeaux UMR 5295, Institut de Mécanique et d'Ingénierie – Bordeaux (I2M)

39 Bordeaux F-33000, France

40 **1 Introduction**

41 A shift toward forests mixing more softwood and hardwood species in the future has been discussed in many
42 studies [1–3]. In France, oak is already a widely distributed hardwood species which represents 27% of the total
43 volume of standing trees [4]. In addition, as it has a higher tolerance to warmer and drier climates it is considered
44 more adapted to the future climates in comparison to beech, for example [5]. An increasing interest is shown in
45 the manufacturing of engineered wood products (EWP) made from hardwoods, such as cross-laminated timber
46 (CLT) or glued laminated timber (glulam). Both of these EWPs show a strong potential to enable the use of the
47 lowest qualities of hardwoods in the construction industry [6,7].

48 Currently, both CLT and glulam are almost exclusively manufactured from softwood lumber, mainly spruce and
49 fir. EWP made from softwood generally has lower wood density than hardwood ones, thus has also lower stiffness
50 and strength, and especially low rolling shear strength [8,9]. High density is usually associated with enhanced
51 strength and stiffness characteristics as well as increased shrinkage and swelling under moisture changes.
52 Therefore, the stresses in bonds induced by moisture changes may be significantly higher [10]. Higher wood
53 density also means lower porosity and higher cell wall thickness and as a result, less penetration of adhesive which
54 may cause weaker bonds. For this reason, it is generally assumed that high-density woods tend to have a lower
55 bonding performance [11–13]. In addition, more complex hardwood anatomic features and chemical compounds
56 make hardwood gluing more sophisticated. A study by Sikora et al. [11] demonstrated the positive correlation
57 between the wood density with rolling shear strength and the negative correlation with bonding durability.

58 The wood bonding durability is generally assessed through so-called delamination tests consisting in wetting and
59 drying cycles which induce high stresses in the glue lines. Adhesives generally exhibit low swelling capacity,
60 whereas wood swells with moisture in an anisotropic manner. This constraint caused by the adhesive leads to very
61 high stresses in the glue line [14]. The percentage of delamination length and wood failure percentage (WFP) are
62 the criteria to quantify the delamination. The delamination length is the extent of splitting that occurs between two
63 neighboring layers of wood. It is reported as a percentage of the total length of the joint. WFP is a different criterion
64 measured after the complete splitting of the glue line and related to the percentage of the glued surface in which
65 the rupture occurred in or between wood fibers.

66 A common way to measure the bonding strength is through a dry shear test. This method, however, is considered
67 ineffective in determining the influence of various bonding parameters on the bonding quality as it lacks
68 consistency due to the presence of rolling shear failure especially in CLT [15]. However, performing a shear test
69 after wetting and drying cycle which led to delamination make the test more sensitive and objective to the influence
70 of the manufacturing process [13,15,16].

71 Several studies have been conducted to characterize the bonding ability of oak, showing the good shear strength
72 of glue lines of oak glulam glued with polyurethane (PUR) or melamine-urea-formaldehyde (MUF) at dry
73 conditions [17–19]. However, in terms of resistance to stresses caused by moisture changes as in a delamination
74 test, the results in the literature are more contrasted. A study by Konnerth et al. [18] on six plies glulam made of
75 oak or beech showed that samples using MUF, PUR, and phenol-resorcinol-formaldehyde (PRF) adhesives pass
76 the delamination requirements, but glulam samples made of poplar glued with MUF did not pass the requirement.
77 In contrast, Luedtke et al. [17] showed that six plies glulam made from oak glued with PUR did not meet the
78 delamination standard. These authors added that within the tested hardwood species, the diffuse-porous species
79 outperform the ring-porous species *i.e.* oak. The problem with gluing oak is that the wood pattern is ring porous
80 which means that the variations in density and permeability are very distinct between earlywood and latewood
81 [20].

82 The behavior of CLT is not the same as glulam in delamination tests since the orientations of the lamellas are
83 different. Beech glulam may pass the delamination requirements [18,21] but not beech CLT. Brunetti et al. [15]
84 showed that neither the MUF nor the PUR being used to bond beech CLT met the delamination test requirements
85 standard originally made for softwood [22]. Based on previous studies, it is clear that EWPs made of hardwood
86 species, especially CLT, are unlikely to pass the European standard requirement for delamination but can easily
87 exceed the dry shear strength requirements. To date, there has been no report on the bonding durability of oak
88 CLT.

89 Fabrication of EWP mixing wood species is a growing research topic [15,23–26]. Special attention needs to be
90 given since strong wood density differences may affect negatively the bonding properties especially in
91 delamination tests [10]. The advantage of using mixed species has been shown by Castro and Paganini [23] in
92 which mixed glulam made from poplar and eucalyptus showed higher structural efficiency in bending than those

93 entirely constructed from poplar or eucalyptus. Poplar has also shown interest in the fabrication of mixed-species
94 CLT with Douglas-fir and Monterey pine (*Pinus radiata*), for which the mechanical properties were comparable to
95 those made of non-poplar wood [27]. The utilization of poplar as a single CLT material has been also studied
96 before [27–29].

97 Several studies showed that MUF bonded hardwood produced more than 2 times lower delamination compared to
98 PUR bonding [30–32]. A recent study on white oak, white ash, yellow birch, and birch glulam specimens bonded
99 with melamine-formaldehyde (MF) and two-component PUR (2C-PUR) showed that the loss of strength induced
100 by the moisture and differential wood swelling caused by the vacuum-pressure cycle was considerable (50%),
101 especially for high-density specimens bonded with 2C-PUR adhesive (around 60% reduction) [32]. Knorz et al.
102 [30] compared the bonding quality of glulam made of ash with various adhesives *i.e.* PRF, MUF, PUR, emulsion
103 polymer isocyanate (EPI), and varying closed assembly times as a bonding parameter. For all tested adhesives and
104 closed assembly times, the shear tests showed high WFPs and strength values that are comparable to solid ash. In
105 contrast, for delamination tests, significant differences were found between the adhesives as well as between closed
106 assembly times, with improving resistance to delamination for increased closed assembly times. However, none
107 of the five adhesives satisfied the requirement of the current standard. The application of a primer product in
108 combination with a 1C-PUR adhesive appears to be a promising approach for hardwood, and especially oak [17].

109 The two main surface bonding machines used by CLT producers are hydraulic press and vacuum press, which
110 differ considerably with regard to bonding pressures. The pressure obtained in a vacuum press lies below 0.1
111 N/mm² while the pressure obtained with a hydraulic press is generally above 0.4 N/mm². Several studies have
112 reported the influence of the bonding pressure on the bonding quality. Knorz et al. [33] studied the influence of
113 bonding pressure (0.085 vs 0.8 N/mm²) and the timber thickness (20 mm vs 40 mm) on the delamination of spruce
114 CLT glued with 1C-PUR. Their results show that both parameters had no impact on the results of delamination
115 tests. A more recent study on eucalyptus CLT glued with 1C-PUR showed that lower pressure (0.1 N/mm²) results
116 in higher delamination failure [13]. Therefore, a higher pressure seems preferable for hardwood CLT. More
117 pressure results in deeper adhesive penetration and, therefore, better bond durability [11]. For these authors, CLT
118 bonded under high pressure (1 N/mm²) showed up to 100% WFP in the bonding line while CLT bonded under low
119 pressure (0.4-0.6 N/mm²) can reach as low as 40% WFP.

120 There is still no reported results in the available literature investigating whether oak CLT resist to delamination
121 tests or not, nor exploring what is the bonding performance when oak is mixed with another species. Therefore,
122 the objectives of this study are to provide the first results of oak CLT delamination and residual shear strength
123 obtained after the treatment intended for delamination test. The influence of glue type and bonding pressure on the
124 delamination and residual shear strength will be studied for CLT and glulam made from oak and mixed CLT and
125 glulam made from poplar and oak.

126 **2 Material and methods**

127 **2.1 Wood material**

128 Oak (*Quercus petraea* (Matt.) Liebl) boards with cross-sections of 88 mm x 25 mm as well as poplar (*populus*
129 *alba*) boards with dimensions of 88 mm x 23 mm coming from a local forest in Burgundy, France were used for
130 the production of 3-ply CLT and glulam panels. All lamellas showed annual growth rings with tangential
131 orientation (flat-sawn boards). Flat sawing was chosen to ensure high rolling shear properties. A previous study
132 by Aicher et al. [34] showed that quarter sawn boards resulted in the lowest rolling shear thus were less suitable
133 for CLT fabrication.

134 Less than 24 hours before fabrication, all sides of the oak boards were planed to the desired thicknesses of 19.5
135 mm for the outer layers and 23 mm for the inner layer, with a width of 86 mm. The poplar inner layer thickness
136 was reduced to 21 mm. The mean density for oak wood was 0.707 kg/m³ with a standard deviation of 0.107 kg/m³
137 while poplar mean density was 0.341 kg/m³ with a standard deviation of 0.014 kg/m³. The mean value and standard
138 deviation of oak boards' moisture content (MC) were 9.2 ± 0.5 % while poplar MC was 9.3 ± 0.3 % which satisfies
139 the glue manufacturer's requirement which is a MC between 6 % to 15 %.

140 **2.2 Manufacturing of CLT and glulam**

141 To study the influence of the adhesives on bonding quality, PUR and MUF were employed in this study. PUR is
142 broadly used in the industry since it is more eco-friendly. MUF is cheaper compared to PUR but less eco-friendly
143 as it contains formaldehyde. However, MUF had been proved to provide higher wood bonding quality than PUR.

144 Both PUR and MUF are cold-setting chemical adhesive systems that meet the requirements of adhesive type I
145 according to EN 15425 [35] for structural bonding of wood.

146 3-layered CLT and glulam panels were assembled in two different compositions. First composition was CLT or
147 glulam entirely made from (named oak) with nominal dimensions of 400 mm x 400 mm x 62 mm. The second
148 composition was CLT or glulam made from oak as outer layers and poplar as inner layer (oak-poplar-oak, named
149 mixed poplar-oak) with nominal dimensions of 400 mm x 400 mm x 60 mm. CLT lamellas orientation was cross-
150 layered while glulam lamellas were parallel. The boards were sanded just before bonding in order to obtain smooth
151 surfaces suited to the process and to assemble oak panels 62 mm thick and mixed poplar-oak panels 60 mm thick.
152 The time between surface preparation and bonding was at most 6 h. Surfaces were cleaned using filtered
153 compressed air before gluing, in order to remove dust.

154 The adhesive was applied to the faces of the lamellas using a spatula. The amount of adhesive spread, as well as
155 assembly time and pressing time, were in accordance with adhesive manufacturers' recommendations. The spread
156 rate of PUR was about 150 g/m² and, when used, the primer amount was of 20 g/m²; MUF adhesive spread was
157 about 300 g/m². The primer was applied to each adherend and was followed by an open time of 30 min before the
158 application of PUR. The closed assembly time for PUR was not more than 60 min, while for MUF it was 30 min.

159 **Table 1.** Outline of the treatment, number of specimens used and code used to shorten the names

| No | Code | Type of assembly | Species | Pressure | Glue type | Nb layers | Nb specimens |
|----|------|------------------|---------|-----------|-----------|-----------|--------------|
| 1 | CMHM | CLT | Mix | Hydraulic | MUF | 3 | 9 |
| 2 | CMHP | CLT | Mix | Hydraulic | PUR | 3 | 9 |
| 3 | CMVM | CLT | Mix | Vacuum | MUF | 3 | 9 |
| 4 | CMVP | CLT | Mix | Vacuum | PUR | 3 | 9 |
| 5 | COHM | CLT | Oak | Hydraulic | MUF | 3 | 9 |
| 6 | COHP | CLT | Oak | Hydraulic | PUR | 3 | 9 |
| 7 | COVM | CLT | Oak | Vacuum | MUF | 3 | 9 |
| 8 | COVP | CLT | Oak | Vacuum | PUR | 3 | 9 |
| 9 | GMHM | Glulam | Mix | Hydraulic | MUF | 3 | 9 |
| 10 | GMHP | Glulam | Mix | Hydraulic | PUR | 3 | 9 |
| 11 | GMVM | Glulam | Mix | Vacuum | MUF | 3 | 9 |
| 12 | GMVP | Glulam | Mix | Vacuum | PUR | 3 | 9 |
| 13 | GOHM | Glulam | Oak | Hydraulic | MUF | 3 | 9 |
| 14 | GOHP | Glulam | Oak | Hydraulic | PUR | 3 | 9 |
| 15 | GOVM | Glulam | Oak | Vacuum | MUF | 3 | 9 |
| 16 | GOVP | Glulam | Oak | Vacuum | PUR | 3 | 9 |

160

161 To study the influence of bonding pressure on the bonding quality, a vacuum press (pressure: 0.085± 0.05 N/ mm²)
162 and a hydraulic press (pressure: 0.8 N/mm²) were used. After manufacturing, the panels were stored for 30 days
163 at 20.2 C and 37.5 % of relative humidity.

164 **2.3 Measurement of bonding quality**

165 The testing materials, consisting of one 400 x 400 mm² panel for each of 16 experimental modalities (2 lamella
166 orientation x 2 press typologies x 2 species combinations x 2 adhesives), were cut into 9 specimens each with
167 dimensions of 100 mm x 100 mm x 60 (or 62) mm. The 100 mm x 100 mm dimension corresponds to the
168 dimensions required for the CLT delamination test of EN 16351:2015 [22]. It has been chosen to keep the same
169 dimensions for the glulam specimens, although EN 14080:2013 [36] specify a specimen length in grain direction
170 of 75 ± 5 mm. The position of the specimens inside the panels is presented in Fig. 1. Wood bonding quality was
171 then assessed through the delamination test, measurement of wood failure percentage, and shear test after the
172 delamination cycle.

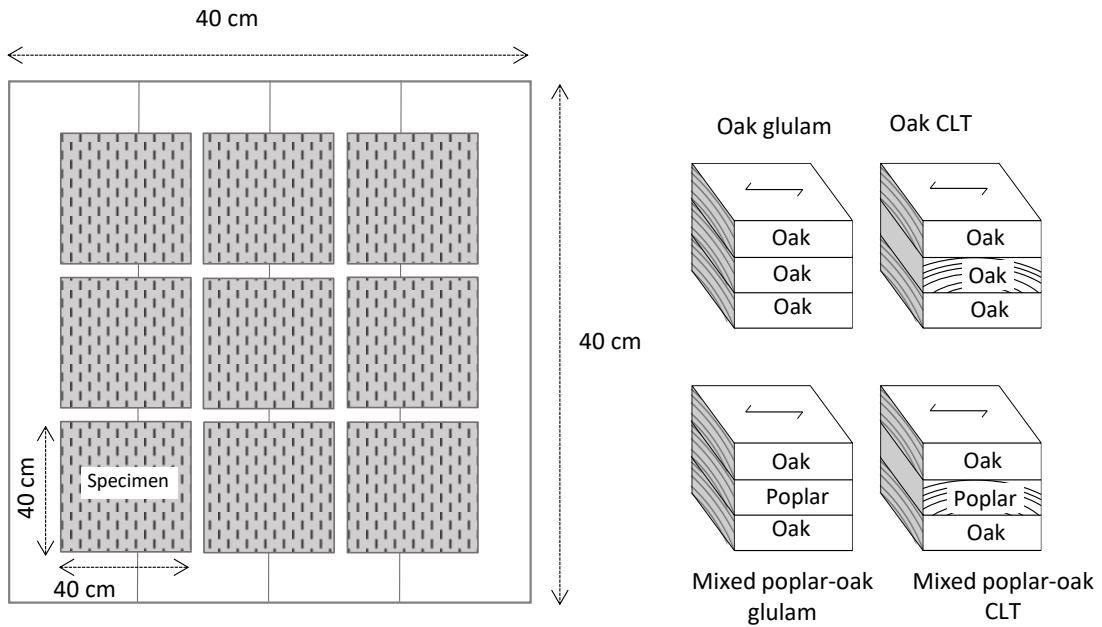


Fig. 1. Sampling position and configuration of oak and mix poplar oak specimen.

Delamination test

In this research study, the delamination test as defined in EN 16351:2015 [22] for CLT was applied for both CLT and glulam (it corresponds to method B of EN 14080:2013 [36] for glulam). The test was performed in one cycle. The specimens were placed in a vacuum pressure vessel with end grain surfaces exposed to water. A vacuum of 75 kPa was first drawn for 30 min. The vacuum was then released and pressure was applied around 550 kPa for 2 h. The test pieces were then dried at 70°C until the mass of the test pieces has returned to 110 % of the original mass. The specimen weight before and after the wetting and drying cycle was measured using an analytical scale Sauter RC-8021 with 0.1 g resolution. After reaching their target weight, the specimens were immediately removed from the oven for visual inspection.

As defined in EN 16351:2015 [22] for CLT the total delamination length (%) of a test piece has been calculated from Eq. (1):

$$D_{tot, CLT} = 100 \frac{l_{tot, delam}}{l_{tot, glue\ line}} \quad (1)$$

Where $l_{tot, delam}$ is the total delamination length, in mm; $l_{tot, glue\ line}$ is the sum of the perimeters of all glue lines in a delamination specimen, in mm. The EN 16351:2015 [22] standard requires that the total delamination length should not exceed 10% of the sum of all glue lines. The delamination length was measured using a ruler with a ± 1 mm precision.

The maximum delamination (%) for CLT was calculated using Eq. (2):

$$D_{max, CLT} = 100 \frac{l_{max, delam}}{l_{glue\ line}} \quad (2)$$

Where $l_{max, delam}$ is the maximum delamination length, in mm; $l_{glue\ line}$ is the perimeter of one glue line in a delamination specimen, in mm. The EN 16351:2015 [22] requires that the maximum delamination length of each specimen should not exceed 40% of the total length of a single glue line.

As defined in EN 14080:2013 [36] for glulam the total delamination length (%) of a test piece has been calculated from Eq. (3):

$$D_{tot, glulam} = 100 \frac{l_{end, tot, delam}}{l_{end, tot, glue\ line}} \quad (3)$$

Where $l_{end, tot, delam}$ is the total delamination length on both end-grain surfaces, in mm; $l_{end, tot, glue\ line}$ is the entire length of the glue lines on both end-grain surfaces, in mm. The EN 14080:2013 [36] standard requires that the

203 total delamination length on both end-grain surfaces should not exceed 4% of the entire length of the glue lines on
204 both end-grain surfaces.

205 The maximum delamination for glulam (%) was calculated based on Eq. (4):

206

$$D_{\max \text{ glulam}} = 100 \frac{l_{\text{end,max,delam}}}{2 \cdot l_{\text{end glue line}}} \quad (4)$$

208 Where $l_{\text{end,max,delam}}$ is the maximum delamination length, in mm; $l_{\text{end glue line}}$ is the length of one glue line on
209 the end-grain surface, in mm. The EN 14080:2013 [36] standard requires that the maximum delamination length
210 of each specimen should not exceed 30 %.


211 Shear test

212 The shear strength behavior was determined in a block shear test according to EN 16351:2015 [22] and EN
213 14080:2013 [36] as presented in Fig. 2. After the delamination procedure, the specimens were tested parallel to
214 the grain with the shear plane corresponding to the adhesive layer. The shear test was performed with a universal
215 testing machine (ZWICK) using a displacement rate of 2 mm/min. The shear strength f_v was calculated by means
216 of the load at failure F_u and the cross-section A of the respective specimen (Eq. 5):

217

$$f_v = \frac{F_u}{A} \quad (5)$$

218 F_u is the ultimate load, in N; $A = 100 \times 100 \text{ mm}^2$ is the sheared area.

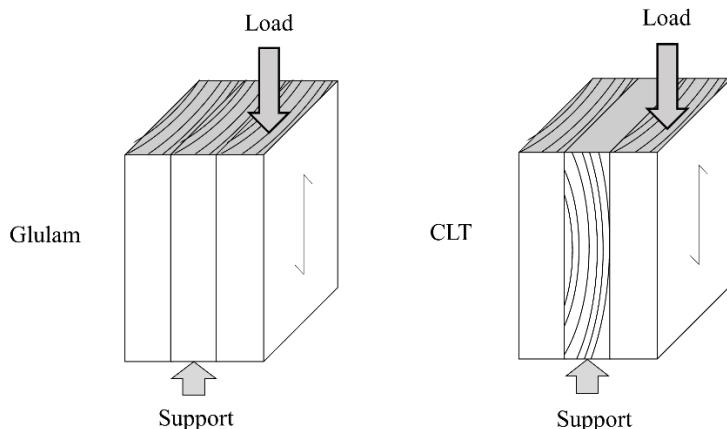


219
220 **Fig. 2.** Loading position in the shear test for glulam and CLT.

221 Measurement of WFP

222 The measurement of WFP was performed right after the shear test. For most specimens, the glued surfaces were
223 fully split. For the rest, which was not completely split, each glue line has been cut open with a chisel. For panels
224 made of MUF, the areas where the glue failed were white, smooth, and shiny while the areas of wood failure were
225 rough due to rip-off wood grain or extra fiber added to the surface. In contrast, for PU, the glue failure areas were
226 rough with a color often similar to the wood. These factors make it difficult to automate the measurement of WFP,
227 as it relies heavily on color contrast.

228 A contrast between the area with solid wood failures and non-solid wood failures was enhanced by applying black
229 ink on the plain area or area of non-solid wood failures (Fig. 3a). An image of each glued surface was then taken.
230 An image analysis system (ImageJ) was then used to calculate the wood failure percentage. The WFP of a split
231 glued area was calculated as the ratio of the area with solid wood failures and the glued area before splitting. WFP
232 total was defined as the ratio of the total area with solid wood failures to the total area of glue lines whereas WFP
233 minimum was determined as the ratio of the area where the solid wood failures are minimum to the glued area
234 before splitting. The colored image was first converted into 3 channels of grey level image (red, green, blue)
235 followed by the application of a common color threshold on the red channel image in order to select the designated
236 wood failure area. The particle analysis of image-J was then used to calculate the wood failure percentage as
237 presented in Fig. 3. The same procedure was performed to calculate WFP on the glulam samples.

238 For CLT, the EN 16351:2015 [22] standard allows to measure the WFP after the delamination test and splitting
239 the specimens, so that if the delamination lengths do not fulfill the requirements, the test can be passed if the
240 minimum WFP of a single bonding area is higher than 50% and the minimum WFP of the sum of all split bonding
241 areas in the sample is higher than 70%.

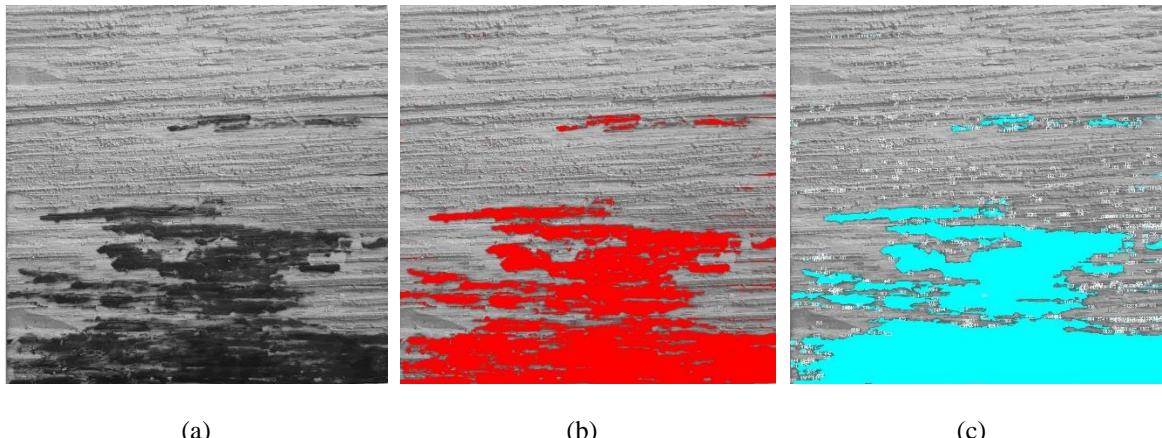

242

243
244

(a)

(b)

(c)

245 **Fig. 3.** Measurement of WFP using image analysis: a) red channel image, b) thresholded image (0,85), c) particle
246 analysis to calculate the area of non-joint failure.

247 **Data analysis**



248 An analysis of variance (ANOVA) was performed to evaluate the influence of each fabrication parameter and their
249 interaction. Therefore, delamination, WFP, and residual shear strength were used as the dependent variables while
250 pressure, adhesive, assembly type, species, and their interactions were used as the independent variables. A post
251 hoc analysis (Tukey's HSD test) was calculated for those that showed significant differences as a result of the
252 ANOVA. The Pearson correlation coefficients were also calculated to investigate the correlations between residual
253 shear strength, delamination, and WFP.

254 **3 Results and discussion**



255 **Delamination and WFP**

256 The average values and standard deviations for the different combinations of parameters and testing methods are
257 presented in Fig. 4 while the results of the analysis of variance are summarized in Table 2. The mean total
258 delamination length for all specimens was 23.18 % while the mean WFP was 69.89 %. The mean total delamination
259 length for oak CLT (41.02 %) was nearly two times the one found for mixed poplar-oak CLT (20.85 %).
260 Meanwhile, the total delamination length for oak glulam was five times higher than mixed poplar-oak glulam
261 (27.43% VS 4.41%). Consistent with the delamination, the mean WFP of mixed poplar-oak CLT (81.36%) was
262 two times higher than oak CLT (39.07%). The mean WFP of mixed poplar-oak glulam (92.93%) was also higher
263 than oak glulam (65.02%).

264

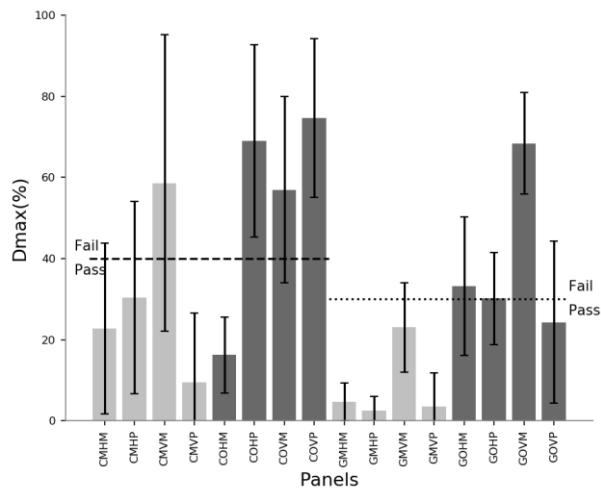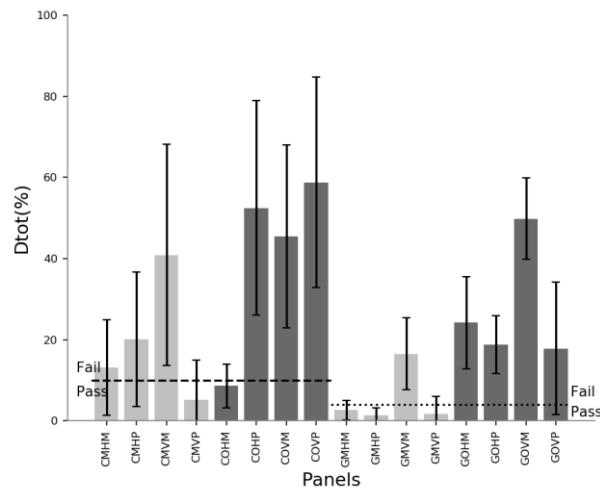

265

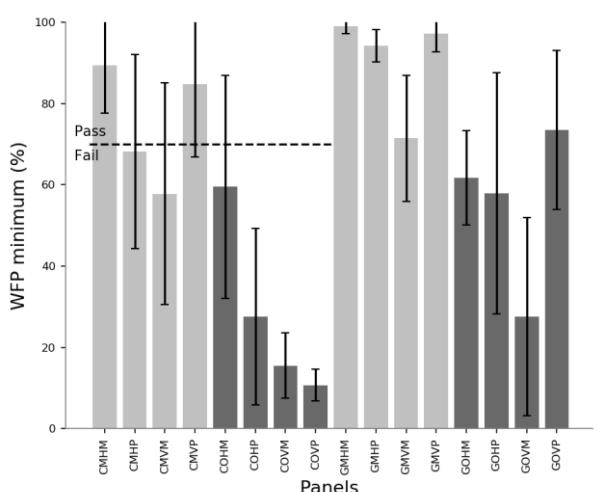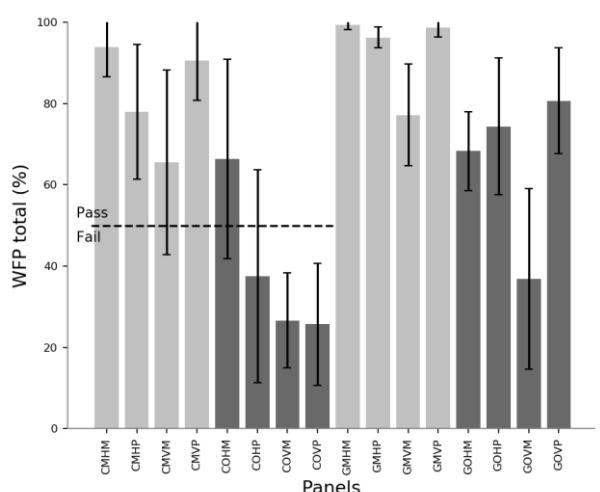

266

Fig. 4. Barplot of the percentage of total delamination, maximum delamination of the single glue line, WFP total, and minimum WFP in a single glue line along with the limit value required by EN 16351:2015. The error bar represents the standard deviation. The dashed line shows the threshold for CLT according to EN 16351:2015. The dotted line shows the threshold for glulam according to EN 14080:2013 [36].

Concerning the influence of the factors examined, the assembly type, wood species, and pressure were highly predictive and statistically significant factors influencing both total delamination length and WFP, while the glue used was much less predictive and statistically significant for WFP only (Table 2). Generally, specimens entirely made of oak exhibited more delamination than the mixed ones. Glulam and hydraulic press configurations also seem to produce lower delamination and higher WFP. Concerning the significant influence of interaction between glue and assembly type, it appears that glulam bonded with PUR generates the lowest delamination and highest WFP while CLT bonded with PUR produces the highest delamination. There was also a significant and high influence of the interaction between pressure and glue type: delamination results were better for MUF when the 0.8 N/mm^2 pressure in a hydraulic press was applied instead of the 0.085 N/mm^2 pressure in a vacuum press, whereas no clear conclusion can be drawn when PUR was used. For similar reasons, the interaction between species, glue, and assembly type appears to be highly significant.

282

283

284

285

286 **Table 2.** F values and significance as results of the four-way analysis of variance for the total delamination and
 287 WFP observed in the CLT and Glulam

| | D _{tot} | WFP |
|-------------------------------|------------------|-----------|
| pressure | 21.10*** | 29.88*** |
| species | 71.15*** | 189.78*** |
| glue | 1.44 | 5.39* |
| type | 29.25*** | 51.55*** |
| pressure * species | 3.90 | 4.06* |
| pressure *glue | 30.03*** | 40.84*** |
| species *glue | 9.74** | 0.13 |
| pressure *type | 0.67 | 1.16 |
| species *type | 0.01 | 8.65** |
| glue*type | 15.69*** | 18.64*** |
| pressure * species *glue | 0.00 | 0.00 |
| pressure * species *type | 0.93 | 2.21 |
| pressure *glue*type | 2.56 | 0.10 |
| species *glue*type | 26.96*** | 11.79*** |
| pressure * species *glue*type | 1.48 | 1.64 |

*Significant at 5% level; **significant at 1% level; ***significant at 0.1% level; ‘ ’ not significant.

288
 289 Table 3 presents the results of the Tukey test, which was performed to evaluate the influence of species, glue, and
 290 assembly type on the difference in mean total delamination and WFP. The glulam made from mixed poplar-oak
 291 bonded with PUR showed the lowest delamination and the highest WFP. For CLT configuration, mixed poplar-
 292 oak bonded with PUR seemed to produce the lowest delamination and highest WFP.

293 **Table 3.** Tukey test for all significant combinations. C, CLT; G, glulam; O, oak; M, mixed poplar-oak; P, PUR;
 294 M, MUF. Means that do not share a letter are significantly different at 5 % level based on the Tukey Post Hoc test

| type* species *glue | Number | Mean D _{tot} | Mean WFP |
|---------------------|--------|-----------------------|---------------------|
| C O P | 17 | 55.60 ^A | 31.60 ^A |
| G O M | 18 | 37.00 ^B | 52.50 ^B |
| C O M | 18 | 27 .00 ^{BC} | 46.40 ^{AB} |
| C M M | 19 | 27 .00 ^{BC} | 79.60 ^C |
| G O M | 18 | 18 .30 ^{CD} | 77.50 ^C |
| C M P | 16 | 12 .70 ^{CDE} | 84.30 ^{CD} |
| G M M | 18 | 9 .60 ^{DE} | 88.30 ^{CD} |
| G M P | 19 | 1 .67 ^E | 97.40 ^D |

295 The results of the pass and fail analysis for all treatment and test methods are reported in Table 4. Overall, only
 296 27.14 % of CLT specimens met the requirement of the standard EN 16351:2015 [22] for both total delamination
 297 and maximum delamination. Considering the second step of the evaluation, the percentage of specimens that
 298 reached the minimum WFP provided by the standard rose to 60.1 %. For glulam, 60.64 % of specimens pass the
 299 30 % threshold of maximum delamination and 49.31 % pass the total delamination required by standard EN
 300 14080:2013 [36]. Only two glulam configurations (GMHM and GMHP) had a 100% passing rate based on
 301 delamination while there was only one CLT configuration (CMHM) that passed the minimum requirement based
 302 on WFP. All of those three panels were constituted of mixed poplar-oak layers and were assembled using the
 303 hydraulic press. However, both of the vacuum-pressed mixed poplar-oak glulam and CLT bonded with PU (CMVP
 304 and GMVP) were close to reaching the requirements of the standard with more than 85% of the specimen that
 305 fulfilled the criteria.

306 None of the specimens entirely made of oak had a 100 % passing rate for both delamination and WFP. In addition,
 307 there were two configurations (COVP and GOVM) made from oak that had a 0 % passing rate for both
 308 delamination and WFP. Among all 4 criteria presented in Table 4, total delamination was found to be the most
 309 downgrading criteria for CLT (27.14 % of all CLT specimens) while WFP total is the one that gave the highest
 310 rate of success (49.13 % of all CLT specimens).

311 A previous study by Konnerth et al. [18] has shown that glulam made from oak glued with MUF passed the
 312 delamination minimum according to EN 301-2 unlike what we have found in the present work. Added to this, the
 313 pressure used by them was 40% higher than the pressure used in our study (1.4 N/mm² vs 1 N/mm²). Concerning
 314 the performance of oak CLT in the delamination test, the delamination resistance was still better compared to the

other major European hardwood species *i.e.* beech [15]. These results highlight how the minimum delamination rates required by EN 16351:2015 [22] are more difficult to achieve for CLT entirely made of hardwood such as oak or beech than for CLT made of softwood. A too harsh delamination test (which has been initially developed for softwood species and glulam type with the grain oriented in the same direction) or an inappropriate delamination limit for hardwood has been discussed in many reports [15,16,18,30].

Table 4. Percentage of the specimen that passes tests related to total delamination, maximum delamination of the single glue line, total solid wood failure, and minimum WFP in single glue line required by EN 16351:2015 [22]. C, CLT; G, glulam; O, oak; M, mixed poplar-oak; H, Hydraulic; V, Vacuum; P, PUR; M, MUF. NA: not applicable

| No | Code | Percentage of specimen passing the test by criteria | | | | |
|----|------|---|----------------------|---------|-------------|--------------|
| | | D _{tot} (%) | D _{max} (%) | WFP (%) | WFP min (%) | All criteria |
| 1 | CMHM | 44,44 | 66,67 | 100,00 | 100,00 | 100,00 |
| 2 | CMHP | 25,00 | 75,00 | 75,00 | 75,00 | 75,00 |
| 3 | CMVM | 20,00 | 20,00 | 50,00 | 50,00 | 50,00 |
| 4 | CMVP | 75,00 | 87,50 | 100,00 | 87,50 | 87,50 |
| 5 | COHM | 55,56 | 100,00 | 55,56 | 55,56 | 55,56 |
| 6 | COHP | 0,00 | 12,50 | 12,50 | 25,00 | 12,50 |
| 7 | COVM | 0,00 | 33,33 | 0,00 | 0,00 | 0,00 |
| 8 | COVP | 0,00 | 0,00 | 0,00 | 0,00 | 0,00 |
| 9 | GMHM | 100,00 | 100,00 | NA | NA | 100,00 |
| 10 | GMHP | 100,00 | 100,00 | NA | NA | 100,00 |
| 11 | GMVM | 22,22 | 55,56 | NA | NA | 22,22 |
| 12 | GMVP | 88,89 | 88,89 | NA | NA | 88,89 |
| 13 | GOHM | 11,11 | 33,33 | NA | NA | 11,11 |
| 14 | GOHP | 22,22 | 55,56 | NA | NA | 22,22 |
| 15 | GOVM | 0,00 | 0,00 | NA | NA | 0,00 |
| 16 | GOVP | 44,44 | 55,56 | NA | NA | 44,44 |

A higher passing rate with WFP criteria than with the delamination length criteria is in accordance with a previous study by Brunetti et al. [15]. However, measuring WFP is rather more subjective than measuring delamination length because it requires an operator to open the glue line in which each operator proceeds in his own way, and the WFP is measured visually by an operator and not by the image analysis used in the present work. Measurement of WFP by image analysis after a shear test seems to be more objective and repetitive.

Lower delamination for mixed poplar-oak CLT specimens in this study is also in accordance with the study of Brunetti et al. [15] on CLT constituted of beech and spruce. However, these authors did not explain the reason for this behavior. The proposed explanation is as follows. For these 3 plies specimens, the middle layer is the one subjected to the higher stresses because most of the outer layers are freer to swell, not having any boundary condition on their free faces. The inner layer of a CLT specimen is subjected to high compressive stresses because its swelling is blocked by the longitudinal outer layers which cannot stretch due to high wood anisotropy. The interface between inner and outer layers is thus subjected to shear stresses. Delamination should occur when specimens are swelling when the shear stresses in the glue line become greater than the shear strength of the glue line. If the middle lamella is made from poplar, the swelling is less important than for oak, thus the shear stresses in the glue line are less important. In addition, poplar having a low compressive strength, a plastification/damaging perpendicular to the grain phenomenon may occur in the poplar middle lamella, releasing some energy and thus limiting the shear stresses in the glue lines. Oak having a much greater perpendicular to the grain compressive strength in addition to a higher swelling, when the middle lamella is made from oak, the shear stresses induced are greater than when poplar is used, and they can be greater than glue line shear strength. Moreover, it should be noticed that the shear strength of the glue line may be different between an oak/poplar interface and an oak/oak interface.

Shear strength after delamination

347 The residual shear strength of specimens after the delamination cycle is presented in Fig. 5. In Table 5, the results
 348 of the analysis of variance are reported, with shear strength as the dependent variable and assembly type, species,
 349 pressure, glue, and their interaction as the independent factors included in the model. The type of assembly was
 350 the most important factor determining the residual shear strength, with glulam specimens demonstrating higher
 351 residual shear strength. There is only the wood species parameter that did not show a significant influence on the
 352 residual strength. However, for three-way interaction, it can be seen that the interaction of species, glue, and type
 353 of assembly have a significant influence on the shear strength.

354 **Table 5.** F-values and significance as results of the four-way analysis of variance for residual shear strength
 355 observed in the CLT and Glulam

| | F | P-value | significance |
|---------------------------------|--------|---------|--------------|
| pressure | 6.67 | 0.01 | * |
| species | 0.32 | 0.57 | |
| glue | 4.50 | 0.04 | * |
| type | 195.67 | 0.00 | *** |
| pressure * species | 0.27 | 0.60 | |
| pressure *glue | 19.81 | 0.00 | *** |
| species *glue | 0.15 | 0.70 | |
| pressure *type | 0.18 | 0.67 | |
| species *type | 0.90 | 0.34 | |
| glue*type | 21.76 | 0.00 | *** |
| pressure * species *glue | 0.51 | 0.48 | |
| pressure * species *type | 0.40 | 0.53 | |
| pressure *glue *type | 3.19 | 0.08 | |
| species *glue *type | 9.14 | 0.00 | ** |
| pressure * species * glue *type | 0.01 | 0.94 | |

356 *Significant at 5% level; **significant at 1% level; ***significant at 0.1% level; ' ' not significant.

357 The Tukey test was performed for the significant factors in the ANOVA and the outcomes (mean values and
 358 significance of the difference between means) for the glue, type of assembly, and species interaction are
 359 summarized in Table 6. It can be seen that glulam made from oak or mixed poplar-oak bonded with PUR provided
 360 the highest residual shear strength.

361 **Table 6.** Tukey test type*species* glue for the mean of residual shear strength. C, CLT; G, glulam; O, oak; M as
 362 a second character, mixed poplar-oak; P, PUR; M as a third character, MUF


| type* species* glue | Number | Mean | Grouping |
|---------------------|--------|------|----------|
| G O P | 18 | 6,50 | A |
| G M P | 19 | 5,93 | A |
| G M M | 18 | 4,88 | B |
| G O M | 18 | 4,11 | C |
| C O M | 18 | 2,76 | D |
| C M P | 16 | 1,73 | E |
| C M M | 19 | 1,51 | E |
| C O P | 17 | 1,24 | E |

363 Means that do not share a letter are significantly different at 5 % level based on the Tukey Post Hoc test.

364 The mean residual strength of all glulam specimens was higher (5.36 N/mm^2) than CLT specimens (1.81 N/mm^2).
 365 Performing block shear test after the delamination procedure is out of the standards: both the EN 16351:2015 [22]
 366 and EN 14080:2013 [36] propose to perform these tests on CLT of glulam without any pre-treatment. For
 367 reference, the standard for CLT production with softwood, EN 16351:2015 [22] sets as sufficient the characteristic
 368 value of 1.25 N/mm^2 for the bonding strength of glue lines between crosswise bonded layers, with no single value
 369 under 1 N/mm^2 (tests performed on dry specimens). Among all the CLT specimens, 71.42 % have shear strength
 370 higher than this reference value (80 % of mixed poplar-oak and 62.85 % of oak CLT). Considering all the CLT
 371 configurations, only one (CMVP) had 100 % specimens passing 1.25 N/mm^2 . However, CMHM, CMHP, and
 372 COHM configurations had all but one specimen above the limit of 1.25 N/mm^2 , which is very encouraging
 373 considering that these are residual shear strengths. The EN 14080:2013 [36] requires for glulam a shear strength
 374 of at least 6 N/mm^2 , or between 4 N/mm^2 and 6 N/mm^2 if wood failure percentage is 100 %. Among all glulam
 375 specimens, 43.83 % had residual shear strength above the 6 N/mm^2 limit required by EN 14080:2013 [36] for the

376 dry shear test. Among all glulam configurations, GOVP has the highest percentage of specimens with residual
377 shear strength higher than 6 N/mm² (77.78 %).

378

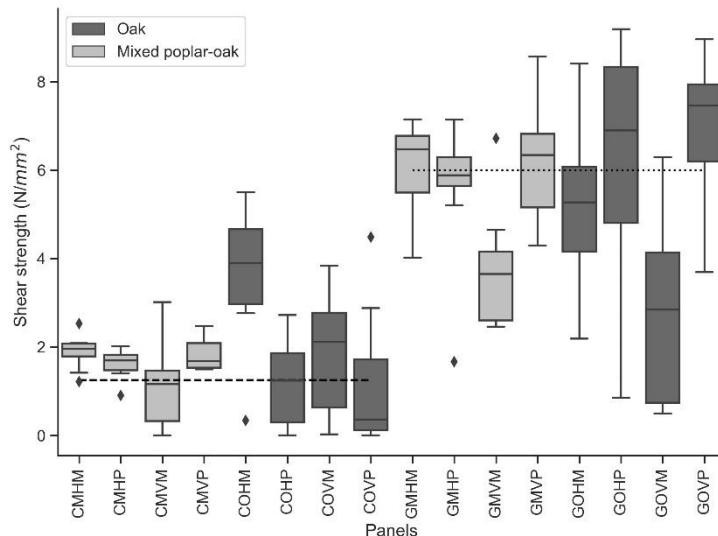

379

380 Fig. 5. Boxplot residual shear strength after delamination cycle

381 The mean shear strength for CLT made from oak specimens was 3.69 N/mm² and for mixed poplar-oak CLT it
382 was 3.56 N/mm². Thus, the residual shear strength of oak and mixed poplar-oak CLT was about equal. Indeed, the
383 trade-off between delamination and residual shear strength is visible here. The higher delamination of the oak
384 specimens results in low mean residual shear strength. However, since oak has superior mechanical properties to
385 poplar, the average residual shear strength of these heavily delaminated oak specimens was fairly high. It should
386 be remembered that some oak specimens were 100% delaminated, so the corresponding mean residual shear
387 strength can be computed with zero values. As a result, while a CLT specimen entirely made from oak is not 100%
388 split, it may still resist to the same shear stresses as a mixed poplar-oak CLT specimen exhibiting much lower
389 delamination.

390 The block shear test has been developed to test the laminations in shear parallel to the grain. Consequently, when
391 applied to CLT, it very often results in rolling shear failure which depends more on the wood mechanical properties
392 rather than the bonding strength [16]. Regarding the residual shear strength tested in our study, rolling shear failure
393 rarely happened. The oak specimens have generally shown shear failure in the glue line. For mixed poplar-oak
394 CLT, the specimens typically showed evidence of compression failure in the poplar lamella (before rolling shear
395 final failure), especially for specimens with practically no delamination. Fig. 6 shows the larger displacements
396 obtained for mixed poplar-oak CLT compared to oak CLT which is due to this compression failure. For specimens
397 with severe delamination, shear failure in the glue line was the primary type of failure. For CLT, the best residual
398 strength was achieved for specimens entirely made from oak bonded using MUF at 0.8 N/mm² pressure. This is
399 in accordance with the rather low delamination obtained for this configuration. The higher residual shear strength
400 than mixed poplar-oak CLT despite the lower delamination of these latter samples may be explained by the very
401 high rolling shear strength of oak and the observed compression failure in poplar lamella.

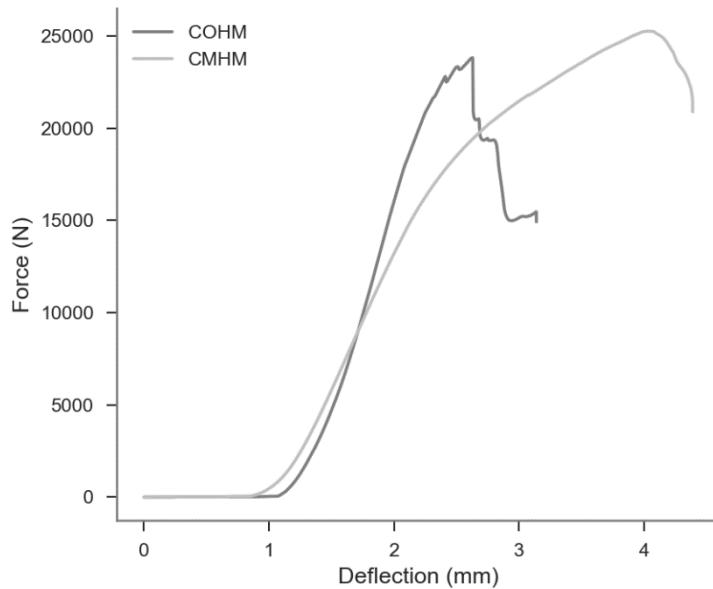


Fig. 6. A typical plot of force and displacements in the shear test for oak and mixed poplar-oak CLT specimens.

Correlations

The correlations among the percentage of total delamination, WFP, and residual shear strength of glulam are presented in Table 7 while for CLT, it is presented in table 8. For both oak and mixed poplar-oak glulam configurations, it can be seen that the WFP and total delamination were correlated with the residual shear strength. Indeed, the residual shear strength increased with the decrease of delamination and increase of WFP. For both oak and mixed poplar-oak configurations, residual shear strength seems to correlate better with WFP than with delamination length.

Table 7. Coefficient of correlation between WFP, delamination, and shear strength for glulam specimens made from oak (**upper triangle**) and mixed poplar-oak (lower triangle)

| | WFP | D _{tot} | Residual shear strength |
|-------------------------|----------|------------------|-------------------------|
| WFP | 1 | 0.74*** | 0.82*** |
| D _{tot} | -0.86*** | 1 | -0.64*** |
| Residual shear strength | 0.6*** | -0.59*** | 1 |

*Significant at 5% level; **significant at 1% level; ***significant at 0.1% level; " not significant.

A positive correlation between WFP and shear strength and a negative correlation between delamination and shear strength was also found for CLT configurations. It may be noticed that the coefficients of correlation between delamination length or WFP and residual shear strength were generally higher than for glulam.

Since all these possible criteria are rather well correlated, they may overlap and thus may seem unnecessary. However, the correlation is not perfect, and thus using both delamination length and WFP as criteria as in the EN 16351:2015 [22] standard allows avoiding to fail too easily to the delamination test. Post delamination shear test may be added to these criteria for the same reason.

Table 8. Coefficient of correlation between WFP, delamination, and shear strength for CLT specimens made from oak (**upper triangle**) and mixed oak-poplar (lower triangle)

| | WFP | D _{tot} | Residual shear strength |
|-------------------------|----------|------------------|-------------------------|
| WFP | 1 | -0.75*** | 0.51*** |
| D _{tot} | -0.82*** | 1 | -0.81*** |
| Residual shear strength | 0.78*** | -0.83*** | 1 |

*Significant at 5% level; **significant at 1% level; ***significant at 0.1% level; " not significant.

425 **4 Conclusion**

426 Bonding pressure and type of glue parameters appeared to have a significant influence on the bonding quality of
427 CLT or glulam, with also significant interactions with the kind of species bonded. Using a poplar middle lamella
428 in a 3-ply poplar-oak CLT or glulam induced less delamination than with specimens entirely made from oak
429 samples. Only mixed poplar-oak CLT and glulam bonded with a hydraulic press with 0.8 N/mm² bonding pressure
430 showed 100% passing rates for all the samples according to the EN 16351:2015 and EN 14080:2013 requirements.
431 If a high bonding pressure seemed to provide better results, vacuum-pressed (0.085 N/mm² bonding pressure)
432 mixed poplar-oak CLT or glulam bonded with PUR were very close to reaching the requirements of the standards,
433 only a few samples exhibiting too much delamination. As a result, it seems possible to use a vacuum press for
434 glulam or CLT bonding when a poplar middle layer is used with oak outer layers. It would be interesting to confirm
435 all these observations with 5-ply CLT or glulam with more plies. Moreover, other tests with more specimens and
436 variability would be needed to quantify more precisely the observed difference between configurations.

437 For CLT or glulam entirely made from oak, using MUF with 0.8 N/mm² bonding pressure provided the lowest
438 delamination and the highest residual shear strength. The shear strength was superior to what is obtained with
439 mixed poplar-oak specimens manufactured in the same conditions. Mixed poplar-oak CLT exhibited compression
440 failure in the poplar middle lamella, whereas CLT entirely made from oak exhibited shear failure in the glue line.
441 This highlights the very high transverse strength of oak, hence its interest as a middle layer when gluing is
442 performed efficiently. In particular, the CLT entirely made from oak glued with MUF at 0.8 N/mm² bonding
443 pressure exhibited significantly higher residual shear strength than other CLT configurations, but it did not pass
444 the delamination and WFP criteria of EN 16351:2015 on the contrary to mixed poplar-oak CLT. As a result, it
445 may be considered that either these criteria may be changed or the post-delamination shear test may be considered
446 as an additional test to qualify CLT resistance to delamination, especially for hardwood species that are very
447 resistant to rolling shear.

448 Delamination length, WFP, and residual shear strength were rather well correlated for both CLT and glulam.
449 However, allowing to use the WFP criterion if delamination length criterion is not fulfilled, then using residual
450 shear strength criterion if WFP criterion is not fulfilled looks like an interesting solution to avoid being too
451 restrictive in the assessment of bonding strength.

452 As a result of this research, mixing poplar and oak species in CLT or glulam manufacturing appears to provide
453 good bonding durability, with potentially other benefits like lighter structure and better thermal insulation. Further
454 research is needed to understand the mechanical properties of these hybrid products. In addition, this study only
455 presents the experimental results of bond durability with phenomenological explanations. Future studies would
456 require a strain field analysis and/or finite element modeling to understand what happens in the joint, and especially
457 what makes hybrid CLT or glulam perform better than CLT or glulam entirely made from oak.

458 **5 Acknowledgments**

459 The completion of this study was made possible thanks to the financial support of the Carnot Arts Institute and the
460 Bourgogne-Franche-Comté region. The authors would like to thank the BCB association (Bois Croisés de
461 Bourgogne) and Ducerf S.A. for providing the wood materials.

462 **Reference**

- 463 [1] A. Felton, M. Lindbladh, J. Brunet, Ö. Fritz, Replacing coniferous monocultures with mixed-species
464 production stands: an assessment of the potential benefits for forest biodiversity in northern Europe, *Forest
465 Ecology and Management*. 260 (2010) 939–947.
- 466 [2] M. Lindner, M. Maroscheck, S. Netherer, A. Kremer, A. Barbati, J. Garcia-Gonzalo, R. Seidl, S. Delzon, P.
467 Corona, M. Kolström, Climate change impacts, adaptive capacity, and vulnerability of European forest
468 ecosystems, *Forest Ecology and Management*. 259 (2010) 698–709.
- 469 [3] M. Hanewinkel, D.A. Cullmann, M.-J. Schelhaas, G.-J. Nabuurs, N.E. Zimmermann, Climate change may
470 cause severe loss in the economic value of European forest land, *Nature Climate Change*. 3 (2013) 203–207.
- 471 [4] IGN, Le memento inventaire forestier, (2020). [https://inventaire-
472 forestier.ign.fr/IMG/pdf/memento_2020.pdf](https://inventaire-forestier.ign.fr/IMG/pdf/memento_2020.pdf).
- 473 [5] K. Dolos, T. Mette, C. Wellstein, Silvicultural climatic turning point for European beech and sessile oak in
474 Western Europe derived from national forest inventories, *Forest Ecology and Management*. 373 (2016) 128–
475 137.

- 476 [6] G. Callegari, C. Cremonini, V.M. Rocco, A. Spinelli, R. Zanuttini, The production of hardwood X-Lam
 477 panels to valorise the forest-wood chain in piemonte (Italy), in: 11th World Conference on Timber
 478 Engineering-WCTE 2010, Ario Ceccotti and Jan-Willem Van de Kuilen., 2010: pp. 809–810.
- 479 [7] R.E. Thomas, U. Buehlmann, Using low-grade hardwoods for CLT production: a yield analysis, in: In:
 480 Möttönen, V.; Heinonen, E., Eds. Proceedings of the 6th International Scientific Conference on Hardwood
 481 Processing; 2017 September 25-28; Lahti, Finland. Helsinki, Finland: Natural Resources Institute of
 482 Finland: 199-206., 2017: pp. 199–206.
- 483 [8] S. Franke, Mechanical properties of beech CLT, in: Proceedings of the WCTE 2016 World Conference on
 484 Timber Engineering, Vienna, Austria, 2016: pp. 22–25.
- 485 [9] T. Ehrhart, R. Brandner, Rolling shear: Test configurations and properties of some European soft- and
 486 hardwood species, *Engineering Structures*. 172 (2018) 554–572.
 487 <https://doi.org/10.1016/j.engstruct.2018.05.118>.
- 488 [10] A.A. Marra, Technology of wood bonding, Van Nostrand Reinhold, 1992.
- 489 [11] K.S. Sikora, D.O. McPolin, A.M. Harte, Shear Strength and Durability Testing of Adhesive Bonds in Cross-
 490 laminated Timber, *The Journal of Adhesion*. 92 (2016) 758–777.
 491 <https://doi.org/10.1080/00218464.2015.1094391>.
- 492 [12] M. Prolle, An investigation into the edge gluing of green Eucalyptus grandis lumber using a one-component
 493 polyurethane adhesive, Stellenbosch: Stellenbosch University, 2017.
- 494 [13] M. Dugmore, M. Nocetti, M. Brunetti, Z. Naghizadeh, C.B. Wessels, Bonding quality of cross-laminated
 495 timber: Evaluation of test methods on Eucalyptus grandis panels, *Construction and Building Materials*. 211
 496 (2019) 217–227. <https://doi.org/10.1016/j.conbuildmat.2019.03.240>.
- 497 [14] C.G. Hunt, C.R. Frihart, M. Dunky, A. Rohumaa, Understanding wood bonds—going beyond what meets the
 498 eye: a critical review, *Reviews of Adhesion and Adhesives*. 6 (2018) 369–440.
- 499 [15] M. Brunetti, M. Nocetti, B. Pizzo, F. Negro, G. Aminti, P. Burato, C. Cremonini, R. Zanuttini, Comparison
 500 of different bonding parameters in the production of beech and combined beech-spruce CLT by standard
 501 and optimized tests methods, *Construction and Building Materials*. 265 (2020) 120168.
 502 <https://doi.org/10.1016/j.conbuildmat.2020.120168>.
- 503 [16] M. Betti, M. Brunetti, M.P. Lauriola, M. Nocetti, F. Ravalli, B. Pizzo, Comparison of newly proposed test
 504 methods to evaluate the bonding quality of Cross-Laminated Timber (CLT) panels by means of experimental
 505 data and finite element (FE) analysis, *Construction and Building Materials*. 125 (2016) 952–963.
 506 <https://doi.org/10.1016/j.conbuildmat.2016.08.113>.
- 507 [17] J. Luedtke, C. Amen, A. van Ofen, C. Lehringer, 1C-PUR-bonded hardwoods for engineered wood products:
 508 influence of selected processing parameters, *Eur. J. Wood Prod.* 73 (2015) 167–178.
 509 <https://doi.org/10.1007/s00107-014-0875-8>.
- 510 [18] J. Konnerth, M. Kluge, G. Schweizer, M. Miljković, W. Gindl-Altmutter, Survey of selected adhesive
 511 bonding properties of nine European softwood and hardwood species, *Eur. J. Wood Prod.* 74 (2016) 809–
 512 819. <https://doi.org/10.1007/s00107-016-1087-1>.
- 513 [19] S. Aicher, Z. Ahmad, M. Hirsch, Bondline shear strength and wood failure of European and tropical
 514 hardwood glulams, *European Journal of Wood and Wood Products*. 76 (2018) 1205–1222.
- 515 [20] P. Lavisci, D. Masson, X. Deglise, Quality of Turkey Oak (*Quercus cerris* L.) Wood. II. Analysis of some
 516 Physico-Chemical Parameters Related to its Gluability, 45 (1991) 415–418.
 517 <https://doi.org/10.1515/hfsg.1991.45.6.415>.
- 518 [21] D. Ohnesorge, K. Richter, G. Becker, Influence of wood properties and bonding parameters on bond
 519 durability of European Beech (*Fagus sylvatica* L.) glulams, *Ann. For. Sci.* 67 (2010) 601–601.
 520 <https://doi.org/10.1051/forest/2010002>.
- 521 [22] EN 16351:2015, Timber structures. Cross laminated timber. Requirements, (2015).
- 522 [23] G. Castro, F. Paganini, Mixed glued laminated timber of poplar and Eucalyptus grandis clones, *Holz Als
 523 Roh-Und Werkstoff*. 61 (2003) 291–298.
- 524 [24] M. Del Senno, F. Paganini, M. Piazza, R. Tomasi, Investigation on failure behavior of mixed-species glued
 525 laminated timber beams, in: *Architectural Engineering 2003: Building Integration Solutions*, 2003: pp. 1–4.
- 526 [25] S. Aicher, M. Hirsch, Z. Christian, Hybrid cross-laminated timber plates with beech wood cross-layers,
 527 *Construction and Building Materials*. 124 (2016) 1007–1018.
 528 <https://doi.org/10.1016/j.conbuildmat.2016.08.051>.
- 529 [26] Y. Ma, R. Si, M. Musah, Q. Dai, X. Xie, X. Wang, R.J. Ross, Mechanical Property Evaluation of Hybrid
 530 Mixed-Species CLT Panels with Sugar Maple and White Spruce, *Journal of Materials in Civil Engineering*.
 531 33 (2021) 04021171.
- 532 [27] Z. Wang, H. Fu, Y. Chui, M. Gong, Feasibility of using poplar as cross layer to fabricate cross-laminated
 533 timber, in: *Proceedings of the World Conference on Timber Engineering*, 2014.
- 534 [28] A. Kramer, A.R. Barbosa, A. Sinha, Viability of hybrid poplar in ANSI approved cross-laminated timber
 535 applications, *Journal of Materials in Civil Engineering*. 26 (2014) 06014009.

- 536 [29] G. Marko, L. Bejó, P. Takats, Cross-laminated timber made of Hungarian raw materials, in: IOP Conference
537 Series: Materials Science and Engineering, IOP Publishing, 2016: p. 012059.
- 538 [30] M. Knorz, M. Schmidt, S. Torno, J.-W. van de Kuilen, Structural bonding of ash (*Fraxinus excelsior L.*):
539 resistance to delamination and performance in shearing tests, European Journal of Wood and Wood
540 Products. 72 (2014) 297–309. <https://doi.org/10.1007/s00107-014-0778-8>.
- 541 [31] S. Ammann, S. Schlegel, M. Beyer, K. Aehlig, M. Lehmann, H. Jung, P. Niemz, Quality assessment of
542 glued ash wood for construction engineering, European Journal of Wood and Wood Products. 74 (2016)
543 67–74.
- 544 [32] A. Morin-Bernard, P. Blanchet, C. Dagenais, A. Achim, Use of northern hardwoods in glued-laminated
545 timber: a study of bondline shear strength and resistance to moisture, Eur. J. Wood Prod. 78 (2020) 891–
546 903. <https://doi.org/10.1007/s00107-020-01572-3>.
- 547 [33] M. Knorz, S. Torno, J.-W. van de Kuilen, Bonding quality of industrially produced cross-laminated timber
548 (CLT) as determined in delamination tests, Construction and Building Materials. 133 (2017) 219–225.
549 <https://doi.org/10.1016/j.conbuildmat.2016.12.057>.
- 550 [34] S. Aicher, Z. Christian, M. Hirsch, Rolling shear modulus and strength of beech wood laminations,
551 Holzforschung. 70 (2016) 773–781.
- 552 [35] EN 15425, Adhesives—One component polyurethane for load bearing timber structures—Classification and
553 performance requirements, (2008).
- 554 [36] NF EN 14080:2013, Timber structures - Glued laminated timber and glued solid timber - Requirements,
555 (2013).
- 556