



Science Arts & Métiers (SAM)

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>
Handle ID: <http://hdl.handle.net/10985/24973>



This document is available under CC BY license

To cite this version :

Lucie HEIM, Loic BRANCHERIAU, Rémy MARCHAL, Nabila BOUTAHAR, Louis DENAUD, Eric BADEL, Karima MEGHAR - NIR-hyperspectral camera analyses for differencing agroforestry and forestry poplar woods - Agroforestry Systems - Vol. 97, n°8, p.1557-1569 - 2023

Any correspondence concerning this service should be sent to the repository

Administrator : scienceouverte@ensam.eu



NIR-Hyperspectral camera Analyses for differencing Agroforestry and Forestry Poplar Woods.

Lucie Heim^{1,2,3,4}, Loïc Brancheriau^{1,2}, Remy Marchal³, Nabila Boutahar^{1,2}, Louis Denaud³, Eric Badel⁴, Karima Meghar^{5,6}, Kevin Candelier^{1,2*}

¹ CIRAD, UPR BioWooEB, Montpellier, France.

² BioWooEB, Univ. Montpellier, CIRAD, Montpellier, France.

³ Arts et Métiers Institute of Technology, LABOMAP, HESAM University, Cluny, France.

⁴ Université Clermont Auvergne, INRAE, PIAF, Clermont-Ferrand, France.

⁵ CIRAD, Research Unit QualiSud, Montpellier, France.

⁶ QualiSud, Univ. Montpellier, CIRAD, Montpellier, France.

*Corresponding author: kevin.candelier@cirad.fr

Lucie HEIM

PhD Student – LABOMAP

Address: Arts et Métiers Institute of Technology
LABOMAP, HESAM University F-71250, Cluny, France.

E-mail: lucie.heim@ensam.eu

ORCID: /

Telephone: +33 3 85 59 53 27

Loïc BRANCHERIAU

Dr. HdR – CIRAD, UR 114 BioWooEB

Address: CIRAD-Unité de Recherches BioWooEB, Montpellier, France
BioWooEB, Univ. Montpellier, CIRAD, Montpellier, France.

E-mail: loic.brancheriau@cirad.fr

ORCID: <https://orcid.org/0000-0002-9580-7696>

Telephone: +33 4 67 61 65 17

Rémy MARCHAL

Dr. HdR – LABOMAP

Address: Arts et Métiers Institute of Technology
LABOMAP, HESAM University F-71250, Cluny, France.

E-mail: Remy.marchal@ensam.eu

ORCID: /

Telephone: +33 3 85 59 53 27

Nabila BOUTAHAR

Tech. – CIRAD, UR 114 BioWooEB

Address: CIRAD-Unité de Recherches BioWooEB, Montpellier, France
BioWooEB, Univ. Montpellier, CIRAD, Montpellier, France.

E-mail: nabila.boutahar@cirad.fr

ORCID: /

Telephone: +33 4 67 61 65 68

Louis DENAUD

Dr. HdR – LABOMAP
Address: Arts et Métiers Institute of Technology
LABOMAP, HESAM University F-71250, Cluny, France.
E-mail: louis.denaud@ensam.eu
ORCID: <https://orcid.org/0000-0002-4370-6076>
Telephone: +33 3 85 59 53 27

Eric BADEL

Dr. HdR – PIAF
Address: Université Clermont Auvergne, INRAE, PIAF, F-63000 Clermont-Ferrand,
France.
E-mail: eric.badel@inrae.fr
ORCID: <https://orcid.org/0000-0003-2282-7554>
Telephone: +33 4 43 76 14 02

Karima MEGHAR

Eng. – CIRAD, UR 114 BioWooEB
Address: CIRAD-Unité de Recherches QualiSud, Montpellier, France
QualiSud, Univ. Montpellier, CIRAD, Montpellier, France
E-mail: karima.meghar@cirad.fr
ORCID: /
Telephone: +33 4 67 61 58 00

Kévin CANDELIER*

Dr. Eng. – CIRAD, UR 114 BioWooEB
Address: CIRAD-Unité de Recherches BioWooEB, Montpellier, France
BioWooEB, Univ. Montpellier, CIRAD, Montpellier, France.
E-mail: kevin.candelier@cirad.fr
ORCID: <https://orcid.org/0000-0002-9328-8511>
Telephone: +33 4 67 61 65 26

Short title: NIR-Hyperspectral camera analyses on agroforestry poplar woods

Keywords: Cellulose, Flexure wood, Growing conditions, Lignin, *Populus deltoïde x Populus nigra* -, “Koster”, Nir-hyperspectral imaging.

Total numbers of characters: 38807; Number of Tables: 2; Number of Figures: 7.

Statements and Declarations:

Conflict of interest: The authors declare no potential conflict of interest.

NIR-Hyperspectral camera Analyses for differencing Agroforestry and Forestry Poplar Woods.

Lucie Heim^{1,2,3,4}, Loïc Brancheriau^{1,2}, Remy Marchal³, Nabila Boutahar^{1,2}, Louis Denaud³, Eric Badel⁴, Karima Meghar^{5,6}, Kevin Candelier^{1,2*}

¹ CIRAD, UPR BioWooEB, Montpellier, France.

² BioWooEB, Univ. Montpellier, CIRAD, Montpellier, France.

³ Arts et Métiers Institute of Technology, LABOMAP, HESAM University, Cluny, France.

⁴ Université Clermont Auvergne, INRAE, PIAF, Clermont-Ferrand, France.

⁵ CIRAD, Research Unit QualiSud, Montpellier, France.

⁶ QualiSud, Univ. Montpellier, CIRAD, Montpellier, France.

*Corresponding author: kevin.candelier@cirad.fr

ABSTRACT

Wood characteristics of trees grown in agroforestry systems are still little studied, while their growth conditions are different from conventional stands. This work focused on the impact of the agroforestry system on the lignin/cellulose ratio of hybrid poplar trees. One disk sample was harvested on 6 agroforestry (AF) and 6 forest control (FC) poplar trees, at breast height ground level (1.30m). Every disk was analyzed by Near Infrared Hyperspectral imaging using a Specim FX17 (Specim, Spectral Imaging Ltd.). Images from hyperspectral camera analyses corresponding to absorbance spectra were collected at the wavelength of 1450 nm, attributed to first overtone O-H stretching vibration of lignin/extractives compounds, in order to clearly observe the chemical difference between AF and FC poplar woods. The results indicated significant difference between the chemical composition, based on estimated lignin content, of AF and FC poplar woods. According to the results from NIR- Hyperspectral images analyses, the lignin content appeared to be lower in AF poplar wood (9.8 ± 1.1 pixels/mm²) than in FC poplar wood (16.1 ± 3.8 pixels/mm²). These results could be explained by the different tree growing conditions between the both systems. AF poplar tended to produce more tension wood and more juvenile wood than FC poplar, which resulted in a lower concentration in lignin.

KEYWORDS: Cellulose, Flexure wood, Growing conditions, Lignin, *Populus deltoïde x Populus nigra* -, “Koster”, Nir-hyperspectral imaging.

1. INTRODUCTION

Agroforestry is a dynamic, ecologically based natural resources management system that, through the integration of trees on farms and in the agricultural landscape, diversifies and sustains production for increased social, economic and environmental benefits for land users at all levels. Today's agroforestry draws from traditional practices but has been adapted to modern farming constraints: specific maintenance techniques, low tree density per hectare, trees aligned and chosen for their compatibility with crops (most often for food use) and their economic or environmental value.

Poplar is a fast-growing tree species that has been extensively planted in many countries and provides industrial wood for paper pulp, light packaging industry, plywood or even furniture or construction ([Lieseback 2020](#)). In addition to growing in plantations for wood production, poplar is also planted in agroforestry systems especially as a fast-growing windbreak and/or an extra income stream for farmers. Poplar tree is considered as a good choice for agroforestry systems due to (i) its little shading effect on crops; (ii) its contribution to soil fertility through its leaf litter; (iii) its suitability with a wide variety of commonly planted inter-crops as wheat, oat, sorghum, maize ; (iv) its wood production that could generate additional income at the end of the rotation ([Chahal et al. 2012](#)).

Indeed, due to its short rotation cycle, generally between 10 and 15 years, poplar provides a quick additional income for plantation owners, compared to other species. In addition, this rotation period can be reduced to 3-5 years for small diameter pulpwood for paper production, 6-8 years for medium diameter poplar, and 10-15 years for large diameter poplar for plywood production, depending on the stand plantation density, genotype and site conditions ([Oliveira et al. 2020](#)).

Thus, poplar is a local asset worth preserving and its timber has unique qualities such as resistance and lightness. Poplars (*Populus spp.*) has a rapid juvenile growth, resulting in a high

volume production per hectare. Of course, the logs of the “high-value trees agroforestry system” are the most interesting for both veneer and sawmill processing, especially since these systems are becoming more prevalent.

Aboveground biomass in poplar plantations or forestry system (FS) and agroforestry systems (AF) has been widely studied around the world (Laureysens et al. 2004; Zabek and Prescott, 2006; Fang et al. 2007; Christersson 2010; Fortier et al. 2010; Truax et al. 2012). These previous works reported that associating poplar trees and crops is more productive than crop rotations separating crops on one side and trees on the other side. For example, a traditional agroforestry plot, associating poplars with cereals, showed that a 100 ha agroforestry farm produces as much biomass as a 140 ha farm separating its crops (Dupraz and Liagre 2008). Intercrops production seems to be modified year by year by the increase of canopy cover, while wood production is mostly related to site conditions and tree density regulated by periodic thinnings (Etienne and Rapey 1999). Moreover, forestry systems with low planting density require more care and pruning of trees to achieve a high-value clean trunk (Nerlich et al. 2013). Based on growth data after 5–8 years under temperate and Mediterranean conditions, Báder et al. (2022) showed that widely spaced deciduous trees in agroforestry areas have grown very satisfactorily compared to the same species in adjacent forest stands. Van Noordwijk and Lusiana (1999) found that the height of the trees was always greater in the classical forestry timber system compared to the agroforestry system because dense planting of trees underwent competition between trees. Usually, forestry trees are more slender than agroforestry trees. They invest less resources in canopy development and more resources for trunk growth. At the opposite, agroforestry trees seem to develop larger crowns (compared to planted forestry trees). They produce more assimilates and since they are generally more exposed to the wind, they produce a larger trunk diameter, which provides the stem resistance. In other words, agroforestry trees are less slender

than planted or control forest systems (Bonnesoeur et al. 2016). These differences could be explain by a difference in wood maturity (part of juvenile wood).

In spite of impacts of forestry conditions on tree growing and on woody biomass production, very little research has evaluated the quality of wood material coming from agroforestry systems and compared it to forestry systems. Moreover, the few results obtained in the literature are often in contrast to each other. Taghiyari and Sisi (2012) reported that 8 years old *Populus deltoids*, intercropped with maize, had larger wood volume compared to the trees from forestry plantations. They stated that the trunk diameter of *Populus nigra* intercropped with alfalfa was greater than in forestry plantations and the greatest difference in diameter growth occurred from age 3 to about age 7. Peszlen (1993) found that wood properties of poplars had no significant relationship with growth rate. In France, poplars (cultivar I-214) were found to have a nearly cylindrical shape in both agroforestry and forestry plantation systems. Through this study, Peszlen (1993) highlighted that the wood density, microbril angle and modulus of elasticity were reported very close in agroforestry and forestry trees. Thus, the wood quality of poplar from agroforestry was found to be very similar to wood quality produced in a forest (Kouakou et al. 2016). However, some researches have also emphasized that low stand density, pruning and a higher exposition to the wind within agroforestry systems could highly affect the tree growing kinetic, the wood anatomy and chemical composition, and finally the wood properties (Zobel and Van Buijtenen 1989; Uner et al. 2009; Novaes et al. 2010; Rocha et al. 2016).

NIR spectroscopy is also widely used in wood characterization, mostly to assess material properties based on chemical information (Leblon et al. 2013). The benefits of such a method reside in the lower time-consuming, labor-intensive, expensive and destructive conventional wet chemical analytical methods (Defoirdt et al. 2017). The NIR (Near-InfraRed) spectroscopy has been efficiently used for the assessment of chemical properties wood (Terrasse et al. 2021). Schimleck et al. (2003) showed that it is possible to accurately calibrate NIR models for a wide

range of species that represent different taxa, wood chemistry and physical properties. More recently, high-resolution near-infrared hyperspectral image acquisition, resulting in an infrared spectrum for each pixel of the image, has been developed. Defoirdt *et al.* (2017) highlighted the usability of NIR hyperspectral imagery as proxy for density and lignin content of poplar wood, where NIR spectra were used for 2D tension wood and lignin mapping. In addition, this technic has been showed as a valuable tool to estimate the difference in lignin content between agroforestry and forestry walnut tree (Heim *et al.* 2022). This study aims to improve the knowledge about the chemical composition, especially based on the lignin content of poplar wood formed in agroforestry context (AF) poplar trees and compared to standard forestry control plots (FC). All samples were analyzed by NIR-spectroscopy hyperspectral camera, in order to evaluate the impact of the two silvicultural practices.

2. MATERIALS AND METHODS

2.1. Experimental site

The experiment was carried out in Lent, located in east-middle France (46°05'11.1" N 5°10'22.7" E and elevation 255 m). Two plots composed by 19 years old poplar and 13 years old, respectively in forest control and agroforestry plots, are studied. The poplar cultivar was "Koster" (*Populus deltoïde x Populus nigra*), showing a great adaptability in the whole France area (Paillassa 2002). Koster cultivar is supposed to be a good candidate for agroforestry systems: it shows a low sensibility to the wind, a good resistance against pruning, low water requirements and good adaptation to stations located outside the valley (Paillassa 2002; CRPF 2016). In our systems, the tree stand densities were around 50 trees/ha and 200 trees/ha in AgroForestry plot (AF) and Forestry Control (FC) plot, respectively (Figure 1a). The planting lines of poplar trees were all Northwest - Southwest oriented, within the both plots (Figure 1a).

Trees were spaced by 5 x 5 m in FC plot and 10 x 20 m in AF plot (10 m within the planting line, 20 m between each planting line) (Figure 1b). In agroforestry system, fodder grass were annually harvested between each line on a 20 m wide strip for animal feedings. Both plots were exposed to a dominant wind coming from the Northwest direction (Figure 1c).

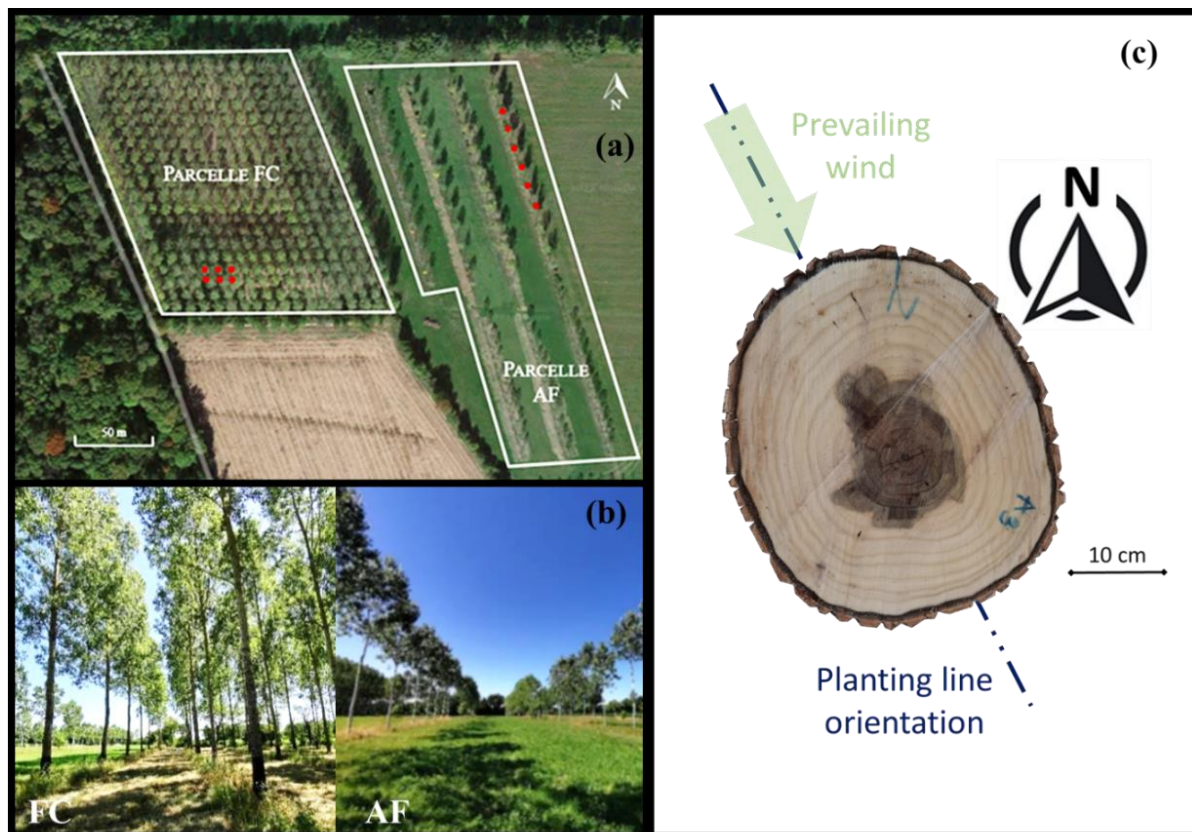


Figure 1. (a) Poplar trees selection (red bullets) in the agroforestry (AF) and forestry control (FC) plots, in Lent located in east-middle France southern France. (b) Pictures of poplar trees distribution in AF and FC plots. Schematic view of tree position according to the prevailing wind (North-Northwest) direction and the planting line orientation (from Northwest to Southwest).

2.2. Trees selection

As shown in Figure 1a, 12 ‘Koster’ poplar trees were selected in the two AF (6 trees) and FC (6 trees) plots. All of the selected poplar trees (AF and FC) were harvested in April 2022, limiting the seasonal impact on wood chemical composition (i.e., starch in sapwood). For each plot, the 6 trees were selected mainly according to constraints related the owner of the plots. However, FC trees were harvested at locations in the plot so that the wind effect would be

representative of the entire stand (Figure 1a). In addition, even if AF trees were collected at the periphery, these are exposed to the wind as the other trees from the plot because of the wide spacing between trees and planting line. The poplar trees issued from AF plot was marked with references from A3 to F3, and the poplar trees coming from FC plots were referred from G3 to L3.

2.3. Sampling

For each poplar tree, a 5 cm thick wooden disc was collected at 1.30 m from the ground. Each disc was lightly sanded in order to get a surface without irregularities limiting high variability in scattering effect during NIR-S measurements (Mancini et al. 2019). The machined face was then vacuum cleaned to avoid the accumulation of wood powder in the wood cells, which could impact the NIR-S measurements. Finally, the discs samples were cut in two equal parts, along the north-south direction, in order to obtain samples with a size adapted to the capacity of the Hyperspectral camera device (max: 20 x 40 cm). All the samples were placed in a conditioning chamber (regulated at 20 ± 2 °C, 65 ± 5 % Relative Humidity). NIR-Hyperspectral analysis were performed after mass stabilization. The process of wood sampling and preparation is illustrated in Figure 2.

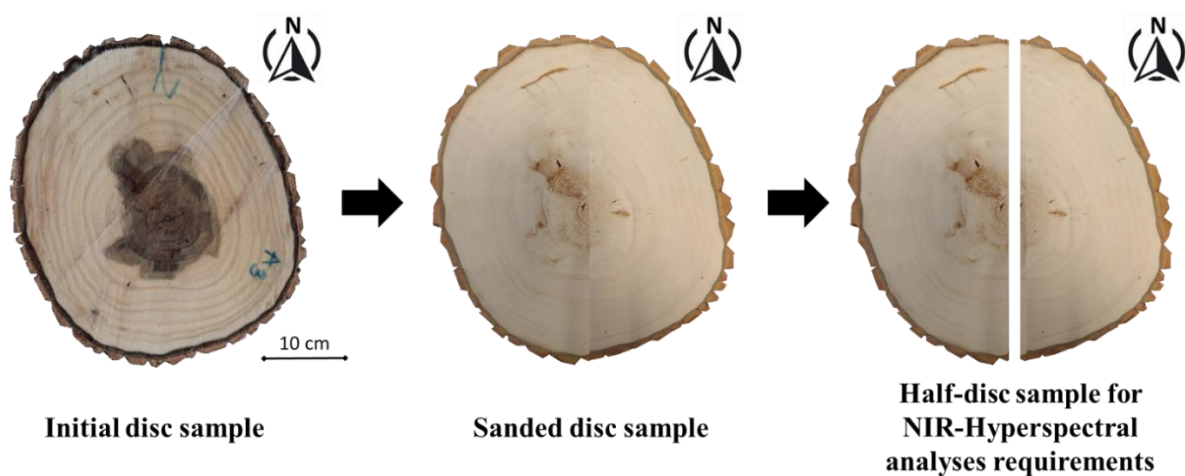


Figure 2. Process of wood sampling and preparation for NIR- Hyperspectral camera analyses.

2.4. NIR- Hyperspectral camera analyses

2.4.1. AgroForestry versus Forestry wood discs

Hyperspectral measurements were performed on the half-wooden discs using a Specim FX17 camera (Specim, Spectral Imaging Ltd.). The distance between the objective of the camera and the surface of the wood samples was fixed at 22 cm. The settings were a spectral range of 933-1721 nm and a 3.5 nm increments. Each NIR spectrum was digitized in 224 wavelengths. The spatial resolution was set to 0.27 mm/pixel. For each image, spectral data were collected as a 3D matrix of 640 x 1002 x 224 values. The dimensions 640 x 1002 were associated with the spatial dimensions of each disc. Images from hyperspectral camera analyses corresponding to absorbance spectra were collected at the wavelength of 1450 nm, attributed to first overtone O-H stretching vibration of lignin/extractives compounds. The both half-wooden discs images from the same tree were merged together. Then, these images were analyzed with Image J 1.53k software (Rasband 2018) in order to determine the values of pixels for each color in the RGB referential. The values of RGB pixels were analyzed on each AF and FC poplar wooden disc without taking the bark into consideration (Figure 3).

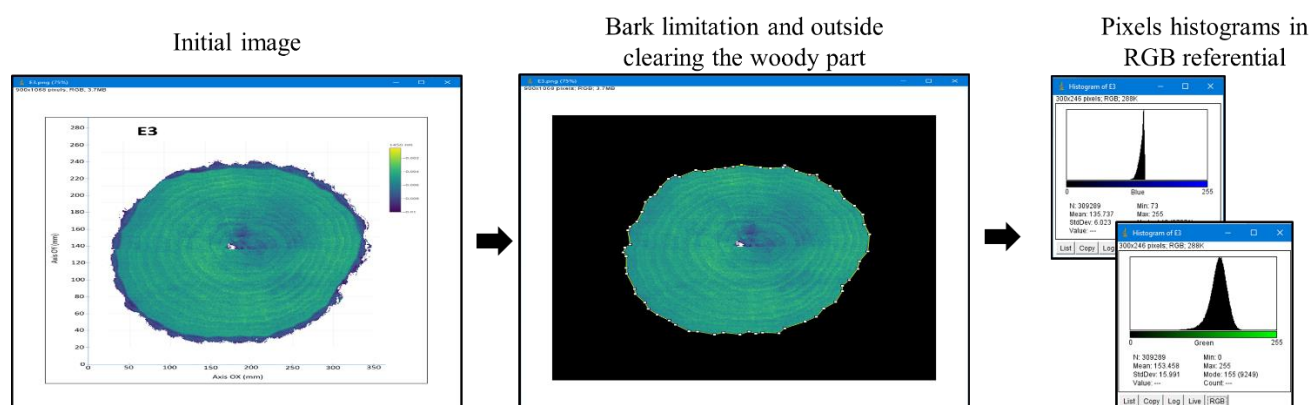


Figure 3. Process analyze concerning determination of RGB pixels on the images from hyperspectral camera (E3 for example), using Image J 1.53k software.

2.4.2. Flexure woods from AgroForestry and Forestry poplar trees

Similar image analyzes were performed on selected areas, representative of Tensile Flexure Wood (TFW) and Compression Flexure Wood (CFW). The TFW and CFW were studied by Roignant et al. (201), and they are represented in Figure 4. These two areas were analyzed for all AF and FC poplar discs, according to the same protocol previously described. The values of RGB pixels were then analyzed on each flexural wood and opposite wood areas. The bark portion was removed from the analyses (Figure 4).

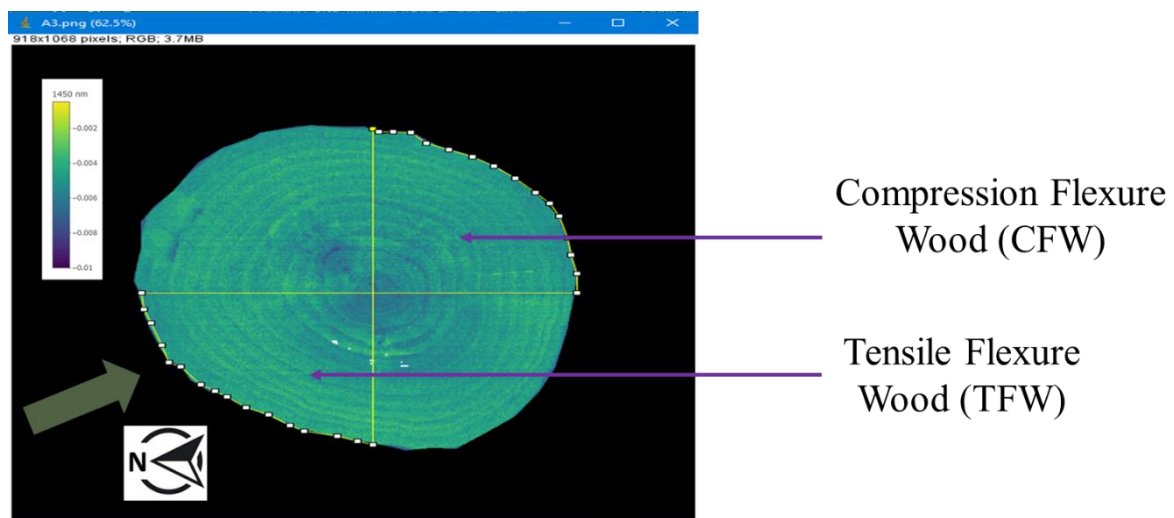


Figure 4. Selection of Tensile Flexure Wood (TFW) and Compression Flexure Wood (CFW) areas for the determination of RGB pixels on the images from hyperspectral camera (A3 for example), using Image J 1.53k software. The green arrow represents the direction of daily wind.

3. RESULTS AND DISCUSSIONS

Figure 5 shows the raw and average NIRS spectra of wood samples from poplar trees from FC and AF samples. Table 1 indicates the NIRS absorption bands associated with the main chemical components contained in the wood specimens. It is clear that the differences in chemical composition between AF and FC poplar wood depend mainly on differences in the content of celluloses (peak 7) and on the amount of lignin/extractives (peak 8). The highest difference between AF and FC poplar sample was observable for a wavelength of 1450 nm that is identified by peak number 8 in Figure 5.

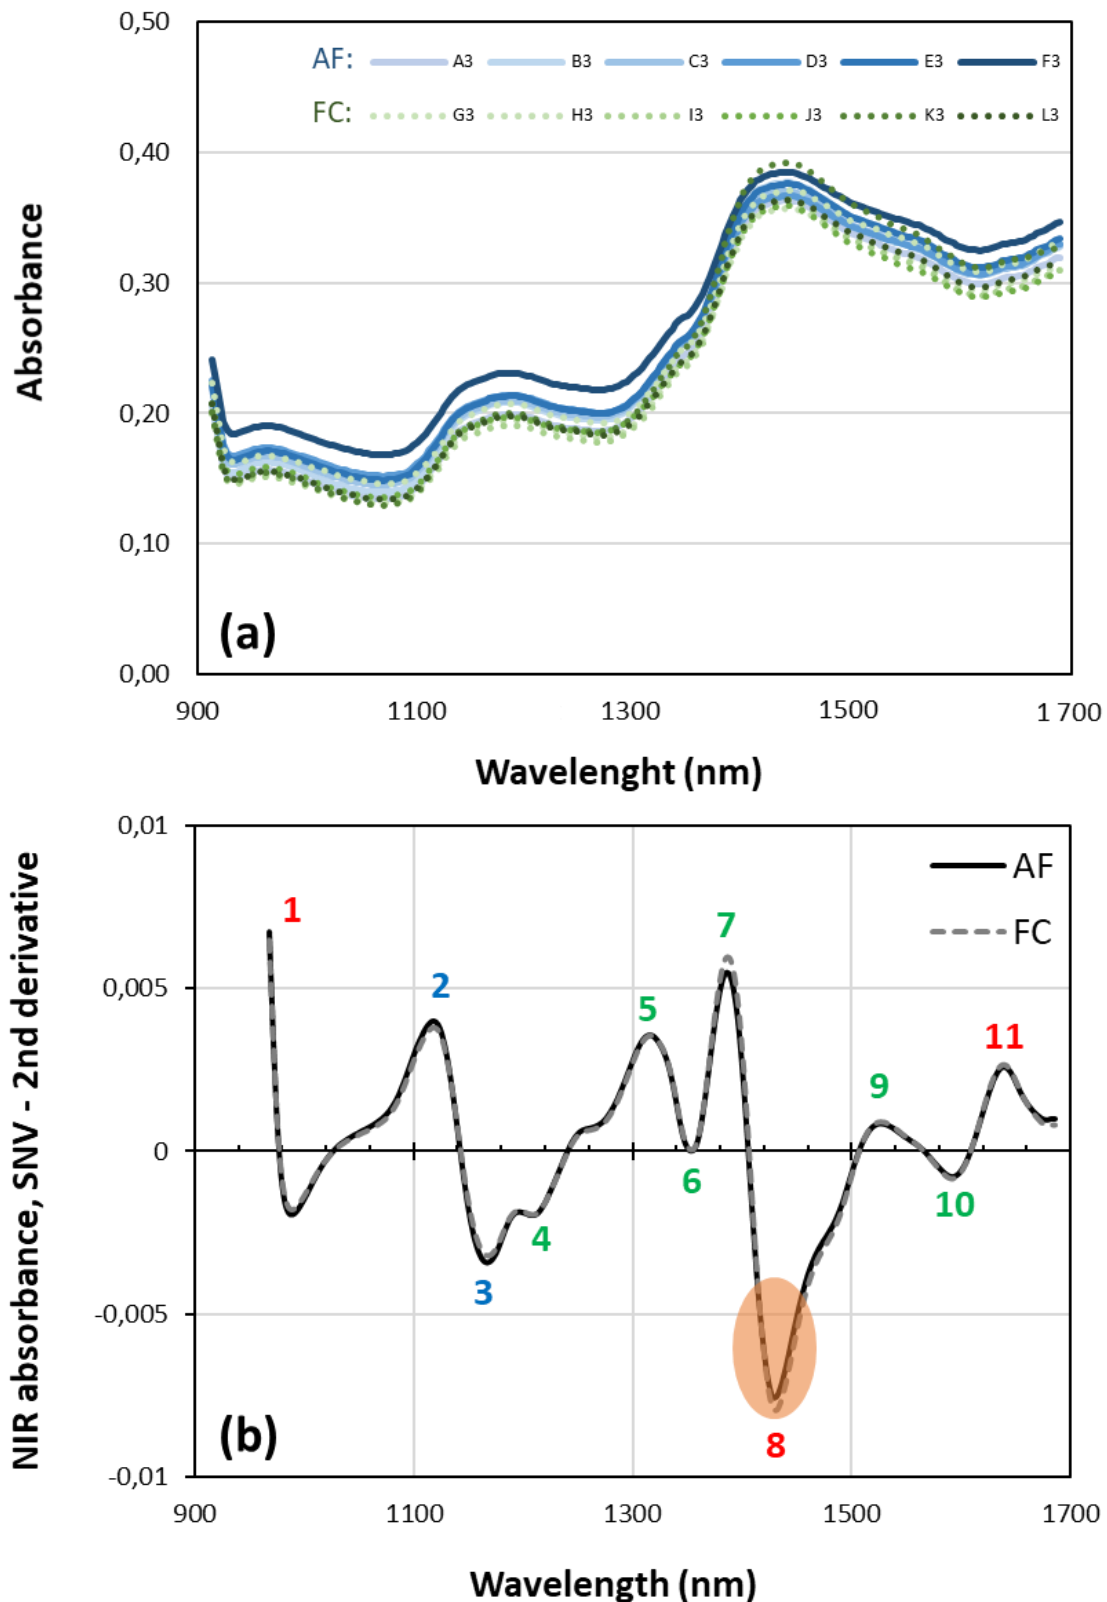


Figure 5. (a) Raw absorbance spectra and (b) average absorbance spectra after pretreatments (SNV correction – 2nd derivative) of AF and FC poplar trees. The area in orange specifies the wavenumber used for the NIR- Hyperspectral camera analyses. Peaks 5 and 6 refer to the hemicellulose. Peaks 4, 7, 9 and 10 refer to the cellulose. Peaks 2 and 3 and peak area delimited around peak 8 refer to lignin. Peaks 1 et 11 refer to extractives.

Table 1. NIRS absorption bands associated with the main wood components (cellulose, hemicelluloses, lignin and extractives) contained in the poplar wood specimens. Index numbers (in color) relate to the specific band in Figure 4.

Index	Wavelength Bands (nm)	Bond Vibration	Structure	Remarks	References
1	900-980		Lignin / Extractives	The major vibrations include the yellow-brown color of the wood that are primarily due to the presence of lignin and extractives.	Kelley <i>et al.</i> (2004) Yi <i>et al.</i> (2017)
2	1100-1150	Second overtone C-H stretching of CH ₃ groups	Lignin	CH ₃ groups and aromatic moieties	Workman & Weyer (2007) Schwanninger <i>et al.</i> (2011)
3	1150-1200	Second overtone asym. C-H, HC=CH stretchings	Lignin	/	Kelley <i>et al.</i> (2004) Schwanninger <i>et al.</i> (2011)
4	1200-1220	Second overtone C-H stretching	Cellulose	Two to three bands t.a. CH and CH ₂ groups, cellulose	Schwanninger <i>et al.</i> (2011)
5	1290-1310	First overtone C-H stretching + C-H deformation	Hemicelluloses / all	Tentative assignment to CH ₃ groups in acetyl ester groups in hemicelluloses and lignin and all wood components after acetylation	Schwanninger <i>et al.</i> (2011)
6	1310-1350	First overtone C-H stretching and C-H deformation	Hemicelluloses / all	Tentative assignment to CH ₃ groups in acetyl ester groups in hemicelluloses (normal wood) and all wood components after acetylation	Schwanninger <i>et al.</i> (2011)
7	1350-1380	First overtone O-H stretching	Cellulose	Amorphous regions in cellulose	Fujimoto T <i>et al.</i> (2007)
8	1420-1460	First overtone O-H stretching	Lignin / Extractives	Vibration of phenolic hydroxyl groups	Schwanninger <i>et al.</i> (2011)
9	1570 -1600	First overtone O-H stretching	Cellulose	Crystalline region of cellulose in C ₁ and C ₂	Tsuchikawa and Siesler (2003) Schwanninger <i>et al.</i> (2011)
10	1600 - 1610	First overtone O-H stretching	Cellulose	Strongly H-bonded O-H group in cellulose,	Schwanninger <i>et al.</i> (2011)
11	1610-1650	First overtone C-H stretching	Extractives	/	Schwanninger <i>et al.</i> (2011)

Images from hyperspectral camera analyses, presented on [Figure 6](#), show the absorbance spectra collected at the wavelength of 1450 nm (most discriminant wavelength between FC and AF), which is attributed to first overtone O-H stretching vibration of lignin/extractives compounds. The hyperspectral images associated to their respective blue and green color intensities, presented in [Figure 6](#), clearly highlight that AF discs samples contained less lignin/extractives components (low intensity in blue color) than those of FC samples.

In addition, Table 2 presented the average value and the associated standard deviation of the maximal value of the number of green and blue pixels, observed on FA and FC samples. These results show that the AF discs samples have a maximal value of the number of blue pixels $/\text{mm}^2$ of 9.8 ± 1.1 , whereas the AF discs samples have a maximal value of the number of green pixels $/\text{mm}^2$ of 16.1 ± 3.8 , showing that AF poplar contains lower lignin/extractives content (low number of blue pixels) than those of FC samples. Moreover, previous work conducted on AF and FC hybrid walnut (*Juglans regia* \times *nigra*) trees shown that the extractives fraction is not sufficient to explain the chemical differences between AF and FC trees and to classify these trees according to the silvicultural system ([Heim et al. 2022](#)). Moreover, poplar wood is well known to have a low extractives contents, so the chemical difference between AF and FC poplar is probably mainly due to their lignin contents. These differences in macromolecules chemical composition could be explain by the stand density. [Jiang et al. \(2007\)](#) highlighted that poplar tree growing in a stand with low planting density presented higher proportion of juvenile wood basal area at breast height, with higher fiber length, than those from plot with high stand density. The juvenile wood of poplar usually contains higher content of hollocelluloses than in mature wood ([Bao et al. 2001](#)). An inverse correlation was found concerning the lignin fraction ([Bao et al. 2001](#)). However, these statements need to be taken with precaution because the AF poplar are three years younger than FC poplar tree, which gives them probably more juvenile wood in relative value.

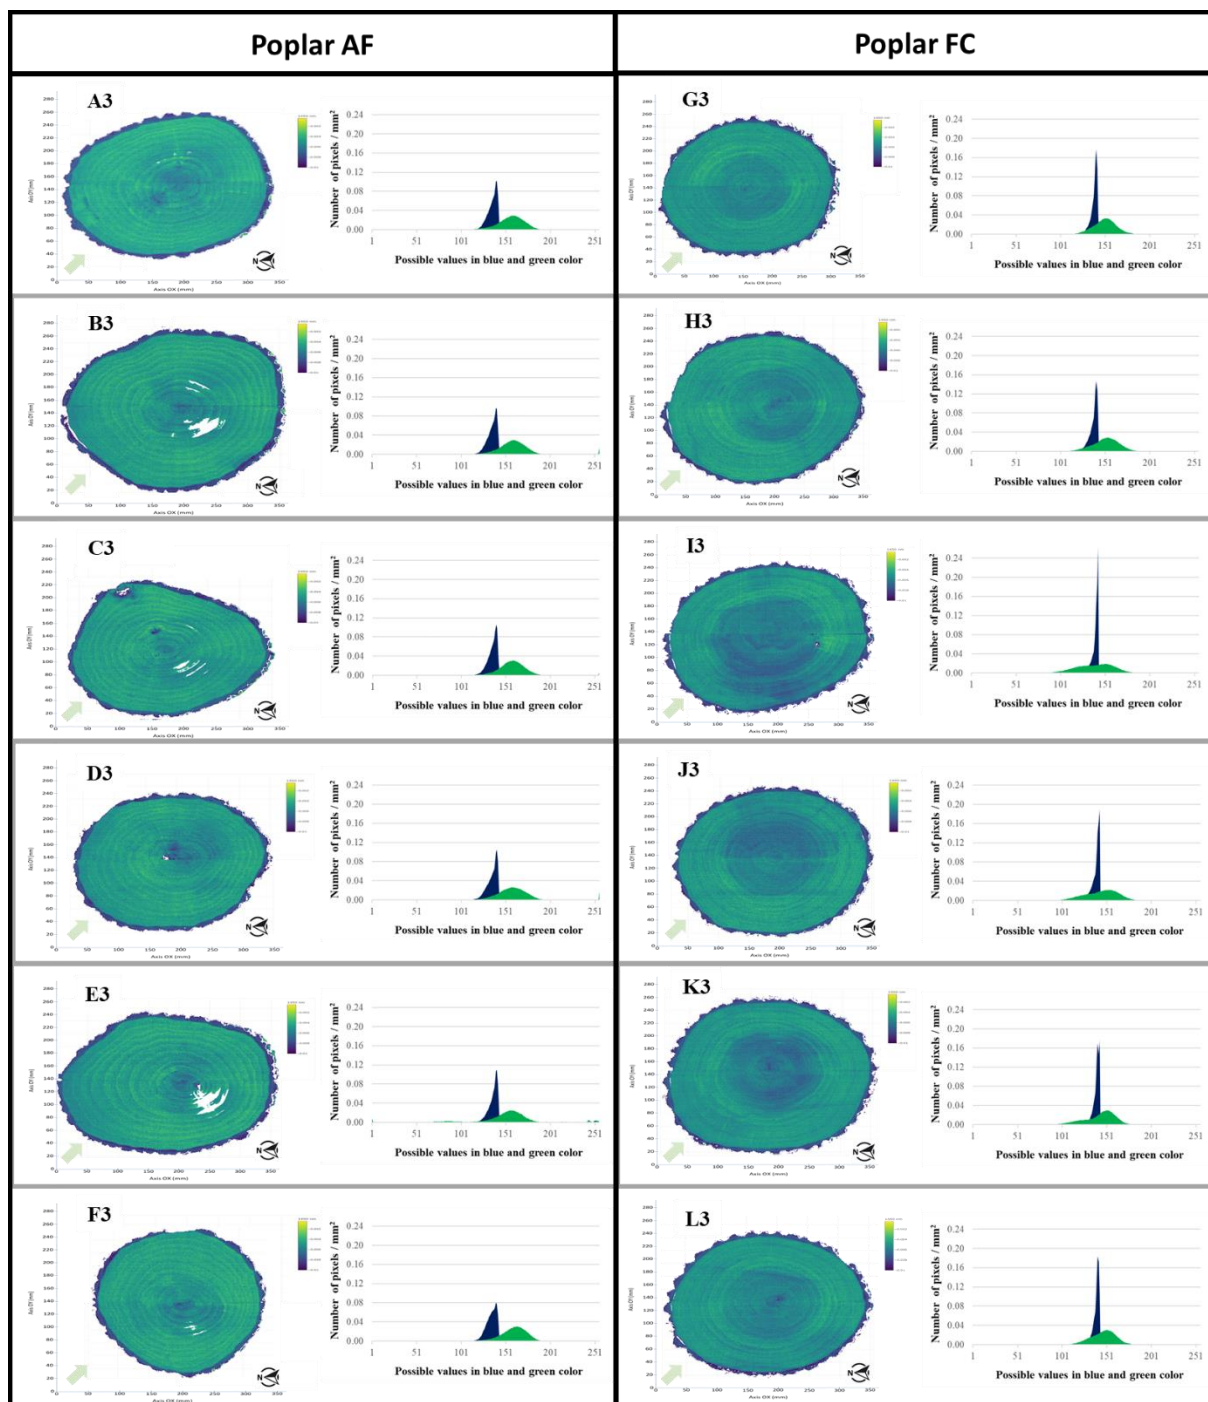


Figure 6. Illustrations of NIR absorbance after pretreatment (SNV correction – 2nd derivative) measured for the wavelength of 1450 nm. These images were acquired from agroforestry (AF) and forestry control (FC) slices of air-dried wooden discs. Images were associated to their histograms of pixels values in blue and grey color (based on RGB referential). On the left, the color scale ranges from yellow to dark blue and represents the intensity of NIR absorbance at the wavelength of 1450 nm, which is attributed to first overtone O-H stretching vibration of lignin/extractives compounds (Table 1). On the right, the histograms were constructed from the analyses of the wooden disc pictures recorded by hyperspectral camera. The blue pixels represent the lignin/extractives contents. The green arrow represents the main direction of wind.

Table 2. Maximum value [and associated standard deviation (SD)] of the numbers of green and blue pixels, observed on the images from AF and FC poplar discs, obtained by NIR hyperspectral Imagery at the wavelength of 1450 nm.

Pixels colors	Numbers of pixels /mm ²			
	AF		FC	
	Maximum value	SD	Maximum value	SD
Blue	9.8	± 1.1	16.1	± 3.8
Green	2.8	± 0.2	2.7	± 0.5

The results obtained by analyses carried out on tensile flexure wood (TFW) and compression wood (CFW) enlighten that TFW contains lower lignin content than CFW for Agroforestry poplar tree (Figure 7). The same results were observed for trees growing in forestry system.

The higher exposition toward dominant wind present within agroforestry plot could also affect the wood chemical composition of trees growing in such system compare to those from traditional forest area. Due to the higher wind exposure, poplar trend to produce flexure wood during its growing. This flexure wood was first defined by Telewski (1989) as the result of the regular mechanical deformations of the stem. In case of poplar, its anatomy was carefully analyzed by Roignant et al (2017) who enlightened several similarities between tension wood and flexure wood formed in the stretched zone, called Tensile Flexure Wood. Especially, it can contain a gelatinous G layer in the stretched cells. In many tree species including *Populus*, tension wood fibers form a distinctive gelatinous inner wall (GL). This G layer is then thick and is known to have a high cellulose content (Côté et al.1969; Mellerowicz and Sundberg 2008) and a microfibril angle close to zero, i.e. aligned to the cell axis (Prohdan et al. 1995), no lignin (Pilate et al. 2004), and a high mesoporosity (Chang et al. 2009). Our hyperspectral images (Figure 6 and 7) showed larger areas of tensile flexure wood (green arrow) in all AF samples than in FC samples. Roignant et al (2018) highlighted that tensile flexure wood is

characterized by lower vessel density, higher fiber diameter, thicker S layer, and the presence of G layer but no difference in lignin content; while [Pilate et al. \(2004\)](#) showed also lower lignin content in tension wood of poplar. These statements are in agreement with the results obtained with AF poplar trees.

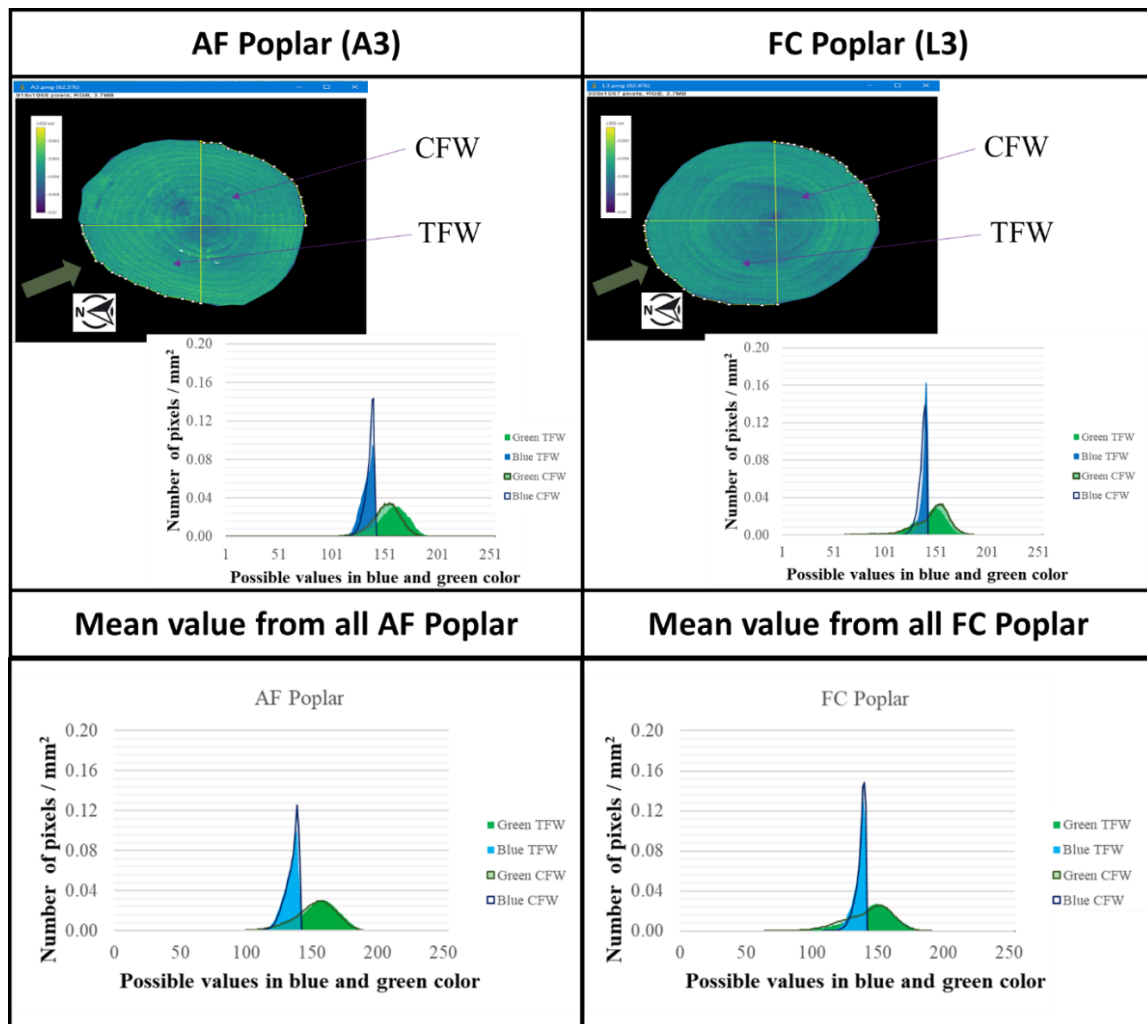


Figure 7. Focus on Tensile Flexure Wood (TFW) and Compression Flexure Wood (CFW) wood areas from agroforestry (AF) and forestry control (FC). NIRS Images were associated to their histograms of pixels values in blue and grey color (based on RGB referential). On the left, the color scale ranges from yellow to dark blue and represents the intensity of NIR absorbance at the wavelength of 1450 nm, which is attributed to first overtone O-H stretching vibration of lignin/extractives compounds (Table 1). On the right, the histograms were constructed from the analyses of the wooden disc pictures recorded by hyperspectral camera. The blue pixels represent the lignin/extractives contents. The green arrow represents the main direction of wind.

In addition, [Fang et al. \(2008\)](#) showed that the growing strength intensity (GSI), that is a good indicator of relative longitudinal growth stress magnitude within trees of the same species, affects the chemical composition of poplar wood. The higher the GSI values, the higher the cellulose content of the wood. Opposite trends for lignin and hemicelluloses contents were also observed in this previous study ([Fang et al. 2008](#)). With results support our findings concerning the lower amount of lignin content in tension wood compared to those of opposite wood in AF poplar, that are more submitted to wind than FC trees, whereas no difference were observed on FC Poplar.

However, the literature states sometimes that juvenile wood is slightly richer or similar in lignin than in cellulose ([Morais et al. 2017](#); [Lu et al. 2021](#)). This would suggest that the effect of flexure wood is dominant over the presence of juvenile wood in the chemical composition comparison between AF and FC poplar trees.

Even if the FC poplars were three years older than the AF poplars, this age differential does not seem to be a parameter that could explain such a difference in chemical composition of these two samples batches. In other words, three years of age difference between AF and FC trees on the average of all the measurements carried out does not seem to be affecting to alter the observed trend. In fact, [Krutul et al \(2019\)](#) compared several poplar clones and enlightened that their cellulose content did not depend from the species of tree age. Moreover, the lignin content increased slightly as a tree age, but its content in 7-year-old wood was already similar to the level found in 30 years-old wood ([Krutul et al. 2019](#)).

4. CONCLUSIONS

The hyperspectral methods, which used a camera, was quick and easy to use. It provided results with a new angle to understand the wood chemical composition of poplar trees allowing assessing the wood quality when trees grow under different growing conditions. In this article,

hyperspectral NIR imaging was used to analyze the quantitative distribution of lignin content in agroforestry and forestry poplar trees.

The use of the method for agroforestry systems allowed enlightening differences of chemical components between forestry poplars and poplar woods formed in agroforestry systems; which are still very under-studied by now. Hyperspectral imaging highlighted that AF poplar samples contained lower lignin/extractives compounds than FC samples. In addition, higher proportion in lignin content in the tensile flexure wood in comparison to the compression flexure wood were observed from all AF samples than those from FC samples. This suggests that AF poplar samples contain more cellulose than FC poplar trees. This is a typical pattern of trees that daily experience windy environments and who produce flexure wood in order to keep their straightness and verticality. However, the literature states sometimes that juvenile wood is slightly richer or similar in lignin than in cellulose, suggesting that the effect of flexure wood is dominant over the presence of juvenile wood in the chemical composition comparison between AF and FC poplar trees. In this sense, it could be interesting to be carried out, in the near future, micro-density and micro-fibril angle (MFA) analyses to determine the proportion of juvenile wood from AF and FC poplar trees.

5. ACKNOWLEDGMENTS

The authors gratefully acknowledge the “Fondation de France” association for its financial support attributed to Lucie Heim for her PhD thesis carried out at the “Arts et Métiers Institute of Technology”.

6. REFERENCES

Báder M, Németh, R, Vörös A, Tóth Z, Novotni A (2022) The effect of agroforestry farming on wood quality and timber industry and its supportation by Horizon 2020. Res Sq, pp. 20. <https://doi.org/10.21203/rs.3.rs-2049093/v1>

Bao FC, Jiang ZH, Jiang XM, Lu XX, Luo XG, Zhang SY (2001) Differences in wood properties between juvenile wood and mature wood in 10 species grown in china. Wood Sci Tech 35: 363-375. <https://doi.org/10.1007/s002260100099>

Bonnesoeur V, Constant T, Moulia B, Fournier M (2016) Forest trees filter chronic wind-signals to acclimate to high winds. New Phytol 210: 850–860. <https://doi.org/10.1111/nph.13836>

Chahal D, Ahmad A, Bhatia JN (2012) Assessment of agroforestry based two-tier-cropping system in Ambala district of Haryana. Agriculture Update 7 (3/4): 210-213. http://researchjournal.co.in/upload/assignments/7_210-213_1.pdf

Chang SS, Clair B, Ruelle J, Beauchêne J, Di Renzo F, Quignard F, Zhao GJ, Yamamoto H, Gril J (2009) Mesoporosity as a new parameter for understanding tension stress generation in trees. J Exp Bot 60: 3023-3030. <https://doi.org/10.1093/jxb/erp133>

Christersson L (2010) Wood production potential in poplar plantations in Sweden. Biomass Bioenerg 34(9): 1289-1299. <https://doi.org/10.1016/j.biombioe.2010.03.021>

Côté WA, Day AC, Timell TE (1969) A contribution to the ultrastructure of tension wood fibers. *Wood Sci Technol* 3: 257–271. <https://doi.org/10.1007/BF00352301>

CRPF. (2016). Le peuplier - un feuillu performant cultivé en Rhône-Alpes ». Centre Régional de la Propriété Forestière Rhône-Alpe, St-Didier-au-Mont-d’Or, France : 4 p.

https://pefcaura.com/sites/default/files/prgmaccompagnement/exe_fiche_essence_peuplier_09_2016_v2_1-1.pdf

Defoirdt N, Sen A, Dhaene J, De Mil T, Pereira H, Van Acker J, Van den Bulcke J (2017). A generic platform for hyperspectral mapping of wood. *Wood Sci Technol* 51: 887–907. <https://doi.org/10.1007/s00226-017-0903-z>

Dupraz C, Liagre F (2008) Agroforesterie – Des arbres et des cultures. Éditions France Agricole, Paris, France: 410 p.

Etienne M, Rapey H (1999) Simulating integration of agroforestry into livestock farmers' projects in France. *Agrofor Syst* 43: 257–272. <https://doi.org/10.1023/A:1026493811593>

Fang S, Xue J, Tang L (2007) Biomass production and carbon sequestration potential in poplar plantations with different management patterns. *J Environ Manage* 85: 672-679. <https://doi.org/10.1016/j.jenvman.2006.09.014>

Fang CH, Guibal D, Clair C, Gril J, Liu YM, Liu SQ (2008) Influence of growth stress level on wood properties in Poplar I-69 (*Populus deltoides* Bartr. cv. “Lux” ex I-69/55). *Ann For Sci* 65: 307-315. <https://doi.org/10.1051/forest:2008008>

Fortier J, Gagnon D, Truax B, Lambert F (2010) Biomass and volume yield after 6 years in multiclonal hybrid poplar riparian buffer strips. *Biomass Bioenerg* 34: 1028-1040. <https://doi.org/10.1016/j.biombioe.2010.02.011>

Heim L, Brancheriau L, Marchal R, Boutahar N, Lotte S, Denaud L, Badel E, Meghar K, Candelier K (2022) Variation analyses of extractive contents by NIR-spectroscopy bring out the differences between agroforestry and forestry walnut (*Juglans regia* × *nigra*) trees. *Holzforschung* 76 (9): 781-790. <https://doi.org/10.1515/hf-2022-0055>

Jiang ZH, Wang XQ, Fei BH, Ren HG, Xing-E Liu XE (2007) Effect of stand and tree attributes on growth and wood quality characteristics from a spacing trial with *Populus xiaohei*. *Ann For Sci* 64 (8): 807- 814. <https://doi.org/10.1051/forest:2007063>

Jourez B, Riboux A, Leclercq A (2001) Anatomical characteristics of tension wood ad opposite wood in young inclined stems of poplar (*populous euramericana* cv “ghoy”). *IAWA Journal* 22: 133-157. <https://doi.org/10.1163/22941932-90000274>

Kelley SS, Rials TG, Snell R, Groom LH, Sluiter A (2004) Use of near infrared spectroscopy to measure the chemical and mechanical properties of solid wood. *Wood Sci Technol* 38: 257–276. <https://doi.org/10.1007/s00226-003-0213-5>

Kouakou SS, Marchal R, Brancheriau L, Guyot A, Guibal D (2016) The quality of poplar wood from agroforestry: a comparison with forest plantation. 3rd European Agroforestry Conference, Montpellier, 23-25 May 2016, 273-276.

Krutul D, Antczak A, Radomski A, Drożdżek M, Klosińska T, Zawadzki J (2019) The chemical composition of poplar wood in relation to the species and the age of trees. *Annals of Warsaw University of Life Sciences – SGGW, Forestry and Wood Technology* No 107: 131-138.

Laureysens I, Bogaert J, Blust R, Ceulemans R (2004) Biomass production of 17 poplar clones in a short-rotation coppice culture on a waste disposal site and its relation to soil characteristics. *For Ecol Manag* 187(2-3): 295-309.

<https://doi.org/10.1016/j.foreco.2003.07.005>

Leblon B, Adedipe O, Hans G, Haddadi A, Tsuchikawa S, Burger J, Stirling R, Pirouz Z, Groves K, Nader J, LaRocque A (2013). A review of near-infrared spectroscopy for monitoring moisture content and density of solid wood. *The Forestry Chronicle* 89 (5): 595-606. - <https://doi.org/10.5558/tfc2013-111>

Liesebach M (2020) Poplars and other fast growing tree species in Germany: Report of the National Poplar Commission. 2016-2019, Thünen Working Paper, No. 141a, Johann Heinrich von Thünen-Institut, Braunschweig, <https://doi.org/10.3220/WP1585727785000>

Lu C, Wu J, Jiang Q, Liu Y, Zhou L, You Y, Cheng Y, Liu S (2021) Influence of juvenile and mature wood on anatomical and chemical properties of early and late wood from Chinese fir plantation. *J Wood Sci* 67: 72 (2021). <https://doi.org/10.1186/s10086-021-02005-2>

Mancini M, Toscano G, Rinnan A (2019) Study of the scattering effects on NIR data for the prediction of ash content using EMSC correction factors. *J Chemom* 33: e3111. <https://doi.org/10.1002/cem.3111>

Mellerowicz EJ, Sundberg B (2008) Wood cell walls: biosynthesis, developmental dynamics and their implications for wood properties. *Plant Biol* 11: 293–300. <https://doi.org/10.1016/j.pbi.2008.03.003>

Morais PHD de, Longue Júnior D, Colodette JL, Morais EH da C., Jardim, CM (2017). Influence of clone harvesting age of *eucalyptus grandis* and hybrids of *eucalyptus grandis* x *eucalyptus urophylla* in the wood chemical composition and in kraft pulpability. *Ciência Florestal* 27(1): 237-248. <https://doi.org/10.5902/1980509826462>

Nerlich K, Graeff-Hönninger S, Claupein W (2013) Agroforestry in Europe: a review of the disappearance of traditional systems and development of modern agroforestry practices, with emphasis on experiences in Germany. *Agrofor Syst* 87: 475–492. <https://doi.org/10.1007/s10457-012-9560-2>

Novaes E, Kirst M, Chiang V, Winter-Sederoff H, Sederoff R (2010) Lignin and biomass: a negative correlation for wood formation and lignin content in trees. *Physiol* 154: 555–561. <https://doi.org/10.1104/pp.110.161281>

Oliveira N, Pérez-Cruzado C, Cañellas I, Rodríguez-Soalleiro R, Sixto H (2020) Poplar Short Rotation Coppice Plantations under Mediterranean Conditions: The Case of Spain. *Forests* 11(12): 1352. <https://doi.org/10.3390/f11121352>

Paillassa E (2002) Fiche technique cultivar de peuplier : Koster ». *Forêt-entreprise*, n° 146.

Institut pour le développement forestier, Orléans, France.

https://www.peupliersdefrance.org/uploads/uploads-FR/fiches-cultivars/cultivarsREP_koster_1.pdf.

Peszlen L (1993) Influence of site, clone, age, and growth rate on wood properties of three *Populus x euramericana* clones. PhD Diss. in Forestry and Forest Products. VPI & SU Blacksburg, Virginia, 175 pp.

Pilate G, Chabbert B, Cathala B, Yoshinaga A, Leplé JC, Laurans F, Lapierre C, Ruel K (2004) Lignification and tension wood. *CR Biol* 327: 889–901.
<https://doi.org/10.1016/j.crv.2004.07.006>

Prodhan AKMA, Funada R, Ohtani J, Abe H, Fukazawa K (1995) Orientation of microfibrils and microtubules in developing tension-wood fibers of Japanese ash (*Fraxinus mandshurica* vat. *japonica*). *Planta* 196: 577-585.
<https://link.springer.com/content/pdf/10.1007/BF00203659.pdf>

Rasband WS (2018) ImageJ, U. S. National Institutes of Health, Bethesda, Maryland, USA, <https://imagej.nih.gov/ij/>, 1997-2018.

Rocha MFV, Vital BR, De Carneiro ACO, Carvalho AMML, Cardoso MT, Hein PRG (2016) Effects of plant spacing on the physical, chemical and energy properties of Eucalyptus wood and bark. *J Trop For Sci* 28: 243–248. <https://www.jstor.org/stable/43856528>

Roignant J, Badel E, Ruelle J, Leblanc-Fournier N, Brunel-Michac N, Moulia B, Decourteix M (2017) Feeling stretched or compressed? The multiple mechanosensitive responses of wood formation to bending. *Ann Bot* 121(6): 1151-1161.

<https://doi.org/10.1093/aob/mcx211>

Schimleck L, Evans R, Ilic J (2003). Application of near infrared spectroscopy to the extracted wood of a diverse range of species. *IAWA Journal* 24 (4): 429-438.
<https://doi.org/10.1163/22941932-900>

00347

Schwanninger M, Rodrigues JC, Fackler K (2011) A review of band assignments in near infrared spectra of wood and wood components. *J Near Infrared Spec* 19(5): 287-308.
<https://doi.org/10.1255/jnirs.955>

Telewski FW (1989) Structure and function of flexure wood in *Abies fraseri*. *Tree Physiol* 5: 113–121. <https://doi.org/10.1093/treephys/5.1.113>

Terrasse F, Brancheriau L, Marchal R, Boutahar N, Lotte S, Guibal D, Pignolet L, Candelier K (2021). Density, extractives and decay resistance variabilities within branch wood from four agroforestry hardwood species. *iForest - Biogeosciences and Forestry* 14 (3): 212-220. <https://doi.org/10.3832/ifor3693-014>

Truax B, Gagnon D, Fortier J, Lambert F (2012) Yield in 8 year-old hybrid poplar plantations on abandoned farmland along climatic and soil fertility gradients. *For Ecol Manag* 267: 228-239. <https://doi.org/10.1016/j.foreco.2011.12.012>

Tsuchikawa S, Siesler HW (2003) Near-infrared spectroscopic monitoring of the diffusion process of deuterium-labeled molecules in wood. Part I: softwood. *Appl Spectrosc* 57(6): 667-674. <https://opg.optica.org/as/abstract.cfm?URI=as-57-6-667>

Uner B, Oyar O, Var AA, Altnta OL (2009) Effect of thinning on density of *Pinus nigra* tree using X-ray computed tomography. *J Environ Biol* 30: 359–362. PMID: 20120459

Van Noordwijk M, Lusiana B (1999) WaNuLCAS, a model of water, nutrient and light capture in agroforestry systems. *Agrofor Syst* 43: 217–242. https://doi.org/10.1007/978-94-017-0679-7_14

Workman JJ, Weyer L (2007). Practical guide to interpretive near infrared spectroscopy. CRC Press, Boca Raton, USA: 344 pages.
<https://doi.org/10.1201/9781420018318>

Yi J, Sun Y, Zhu Z, Liu N, Lu J (2017) Near-infrared reflectance spectroscopy for the prediction of chemical composition in walnut kernel. *Int J Food Prop* 20(7): 1633-1642.
<https://doi.org/10.1080/10942912.2016.1217006>

Zabek L, Prescott C (2006) Biomass equations and carbon content of aboveground leafless biomass of hybrid poplar in Coastal British Columbia. *For Ecol Manag* 223: 291-302.
<https://doi.org/10.1016/j.foreco.2005.11.009>

Zobel JB, Van Buijtenen JP (1989) Wood variation: its causes and control. Springer, New York, USA, p. 363.

