



Science Arts & Métiers (SAM)

is an open access repository that collects the work of Arts et Métiers Institute of Technology researchers and makes it freely available over the web where possible.

This is an author-deposited version published in: <https://sam.ensam.eu>
Handle ID: <http://hdl.handle.net/10985/15999>

To cite this version :

D. P.R. QUEIROZ, Frédéric FRAÏSSE, Matthias KUNTZ, Jacques VERDU, Bruno FAYOLLE -
Radiochemical ageing of epoxy coating for nuclear plants - Radiation Physics and Chemistry -
Vol. Volume 79, Issue 3, p.Pages 362-364 - 2010

Any correspondence concerning this service should be sent to the repository

Administrator : scienceouverte@ensam.eu



Radiochemical ageing of epoxy coating for nuclear plants

D.P.R. Queiroz^a, F. Fraïsse^a, B. Fayolle^{a,*}, M. Kuntz^b, J. Verdu^a

^a Laboratoire d'Ingénierie des Matériaux (UMR 8006), Arts et Métiers Paristech, 151 Boulevard de l'Hôpital, 75013 Paris, France

^b EDF R&D, Département Matériaux et Mécanique des Composants, Avenue des Renardières, Ecuelles, 77250 Moret sur Loing, France

ARTICLE INFO

Keywords:

Epoxy network
Radiochemical ageing
Structure characterization

ABSTRACT

The degradation of an epoxy-amine network exposed to gamma irradiation in oxygen atmosphere has been studied by using a variety of analytical methods, including infrared spectroscopy (FTIR), differential scanning calorimetry (DSC), and sol-gel analysis. Results show that the oxidation of epoxy systems grows with the irradiation dose. Hydroperoxides, which are species resulting from oxidation, were identified and quantified by DSC. As indicated by the sol-gel analysis, the mechanism of degradation of chain scission seems to be predominant over crosslinking. The modifications induced by irradiation reflect in a greater capacity of water absorption.

1. Introduction

Networks based on poly(amidoamine) cured aromatic diepoxides are used as coatings, paints, etc. in wide variety of applications including nuclear plants (Park et al., 2004; Lee et al., 2006). In the latter case, indeed, durability is a key property. An important ageing component is, presumably, radiochemical ageing induced by low dose rate irradiation in the presence of oxygen. Several studies have been reported in the literature (Damian et al., 2001; Ngono-Ravache et al., 2001; Devanne et al., 2005; Longiéras et al., 2006; Longiéras et al., 2007) concerning the degradation of epoxy systems but this subject is not completely understood. In this work, we investigated the radio-oxidation of epoxy-amine network prepared from diglycidylether of bisphenol A (DGEBA) and a poly(amidoamine). This material was exposed to gamma irradiation under oxygen atmosphere. The characterization of the polymer oxidation was made using several methods ranging from molecular scale to macromolecular one such as sol-gel analysis, differential scanning calorimetry, IR spectrophotometry and density.

2. Experimental

2.1. Materials and methods

The studied epoxy network was based on a diglycidylether of bisphenol A (DGEBA), Araldite PZ 756/67, and a polyamidoamine,

Aradur 435. The structure of polyamidoamine is given in Fig. 1. The amine/epoxy functional ratios of this network are equal to 0.86 and the film thickness is close to 70 μm .

Irradiations were carried out in an atmosphere of oxygen at 50 °C with a dose rate of 200 Gy/h. Five doses in the range from 0 to 60 kGy were studied. Samples were stored at -10 °C in order to limit post-degradation.

Infrared spectrophotometric measurements were carried out on the films by using a Bruker IFS 28 spectrometer in the transmission mode.

Differential scanning calorimetry (DSC) was performed using a TA Q10-0553 equipment. The analysis was realized by heating the samples from 0 to 180 °C at 10 °C/min under nitrogen, followed by a cooling to 0 °C at 20 °C/min and a second heating under the same conditions as the first run. In aged samples, an exotherm appears close to 150 °C. Its enthalpy ΔH_{Tm} was directly determined by peak integration. The glass transition temperature (T_g) was obtained from the second run. All experiments are repeated twice.

Sulfur dioxide treatment was used to destroy hydroperoxides. SO_2 was generated by a solution of Na_2SO_3 and HCl. Treatments were performed for 5 h at 60 °C and their consequence on the exotherm at 150 °C was checked by DSC. The sol fraction of the films was determined by Soxhlet extraction using THF for 5 h. The sol content is provided by the difference in weight before and after the extraction operation.

The density of films was determined by a Mohr balance. The weights of the samples were measured in the air and after immersion in water bath. The density ρ is calculated by the following equation:

$$\rho = \frac{A}{|B - A|_*} \rho_{\text{water}}$$

* Corresponding author. Tel.: +33 0 144246149; fax: +33 0 142 1692 13.
E-mail address: bruno.fayolle@paris.ensam.fr (B. Fayolle).

where A and B are the weights of the films in dry state and immersed in the water, respectively, and ρ_{water} is the water density.

The sorption and desorption characteristics of epoxy films have been measured by dynamic vapour sorption, using the gravimetric DVS measurements surface systems, at 50 °C and relative humidity of 70%. Diffusion coefficient is calculated from mass changes assuming that the sorption mechanism follows a Fickian behaviour.

3. Results and discussion

The IR spectra of the carbonyl region for the epoxy films irradiated to different doses are shown in Fig. 2a. One can notice a band centered at 1730 cm^{-1} for all samples assigned to carbonyl stretching. The intensity of this band increases with the irradiation dose and it is associated with the formation of oxidation products, such as ketones, carboxylic acids, esters or formates. The absorbance at 1730 cm^{-1} was scaled according to an internal reference at 1886 cm^{-1} whose intensity is invariant throughout degradation (Fig. 2a). The carbonyl concentration was determined by using the Beer-Lambert law in which the molar absorptivity usual value is 300 $\text{L mol}^{-1} \text{cm}^{-1}$ for carbonyl group. The carbonyl concentrations are presented in Fig. 2b as a function of irradiation dose. One can see that carbonyl concentration increases linearly with the irradiation dose at a rate of $16 \times 10^{-6} \text{ mol Gy}^{-1}$. The DSC results and the thermograms (1st run) for the irradiated and non-irradiated epoxy films are shown in Table 1 and Fig. 3a, respectively. The second run, not included in figures, shows that the T_g of the samples exposed to different irradiation dose is almost dose independent close to 60 °C. The fact that irradiation does not induce a significant T_g change is not very surprising in such networks based on chains of relatively low stiffness. Endotherms close to T_g are observed only in the 1st run. They may indicate the existence of a structural relaxation process, associated to physical ageing, that is not surprising considering the proximity of the ageing temperature with T_g . But the most important feature is that the exothermic peak at around 150 °C that appears for the samples with irradiation dose up to 20 kGy. This exotherm increases with the irradiation dose.




Fig. 1. Chemical structure of the polyamidoamine.

The exothermic peak can be associated to hydroperoxide decomposition. As a matter of fact, SO_2 treatment, which is well known to destroy hydroperoxides by non-radical process, induces the disappearance of this peak (Carlsson et al., 1986; Gardette and Lemaire, 1986). The thermograms of a treated and a non-treated irradiated sample are shown in Fig. 3b: the exotherm at 150 °C disappears after the SO_2 treatment.

Richaud et al. (2006) have used the same technique, SO_2 treatment and DSC, for the hydroperoxide characterization to study polypropylene thermo-oxidation. They used the heat of the exothermic peak, appeared at around 150 °C, to calculate the hydroperoxide concentration. Mallégo et al. (2001) also have attributed an exotherm in alkyd resins to peroxide thermal decomposition. The temperature of this exotherm has changed from 121 to 171 °C with the oxidation time. Ouldmetidji et al. (2001) have used DSC for the quantification of peroxide concentration in polystyrene and elastomeric materials. For epoxy systems, the use of DSC method for the characterization of hydroperoxides has never been reported to our knowledge.

By assuming that proportionality between decomposition enthalpy (ΔH in J g^{-1}) and hydroperoxide concentration ($\Delta[\text{POOH}]$ in mol kg^{-1}) is the same as in the case of polypropylene, i.e. 325 kJ mol^{-1} of POOH, hydroperoxide concentration can be calculated by using the following equation (Richaud et al., 2006):

$$\Delta[\text{POOH}] = \Delta H / 325$$

This statement is based on the fact that the temperature of hydroperoxide decomposition found in our epoxy network and in polypropylene reported is similar, that may indicate some similarity in thermochemical characteristics.

The calculated hydroperoxide concentrations are shown in Fig. 4, as a function of the irradiation dose. This graph displays an induction period corresponding to a radiation dose of 17.5 kGy, or a period of 87 h of irradiation at a dose rate of 200 Gy/h. After the end of the induction period, the hydroperoxide concentration increases almost linearly with the dose. Using these values, one can assess a radiochemical yield for hydroperoxide. It appears that in our case this yield is close to 4 groups/100 eV, a usual order of magnitude in polymer radiochemistry.

Table 1
DSC results for epoxy films irradiated to different irradiation doses.

Irradiation dose (kGy)	T_g (°C)	T_{peak} (°C)	$\Delta H_{T_{\text{peak}}}$ (J/g)
0	57	–	–
10	57	–	–
20	58	157	0.3
40	58	151	2.7
60	60	149	5.3

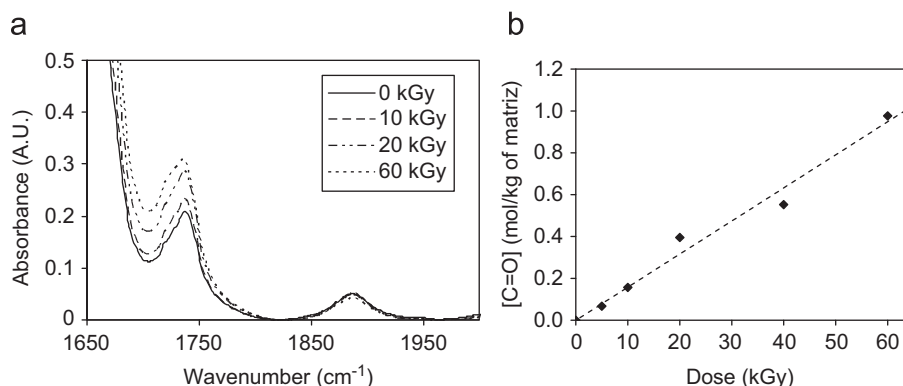


Fig. 2. (a) 2000–1650 cm^{-1} region of IR spectra of epoxy films irradiated at different doses and (b) increase in the concentration of carbonyl as a function of dose.

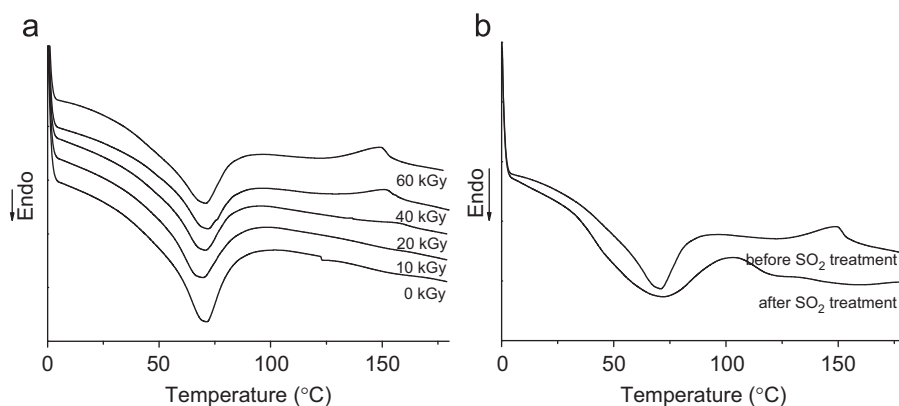


Fig. 3. (a) DSC thermograms of epoxy films irradiated to different doses and (b) thermograms of irradiated samples (60 kGy) before and after SO₂ treatment.

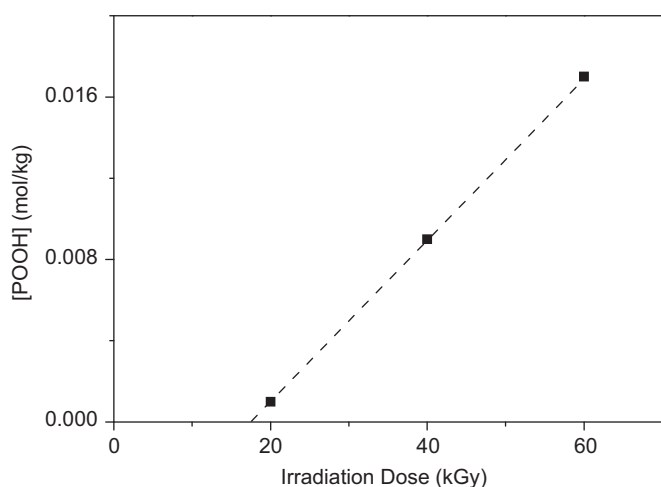


Fig. 4. Hydroperoxide concentration versus irradiation dose for irradiated epoxy films.

The sol fraction increases as a function of absorbed dose: a sol fraction value close to 13% is reached after 60 kGy irradiation whereas the initial value before irradiation was close to 7%. This significant increase seems to indicate that chain scission predominates over crosslinking in our case.

Water sorption tests reveal a small but significant increase of the equilibrium water uptake: 3.82% after 60 kGy exposure against 3.46% before ageing. This increase can be linked to the presence of highly hydrophilic carboxylic acids and amides among carbonyls observed by IR. More significant is the decrease in diffusivity from $2.06 \times 10^{-12} \text{ m}^2 \text{ s}^{-1}$ before ageing to $1.27 \times 10^{-12} \text{ m}^2 \text{ s}^{-1}$ after 60 kGy exposure. This would be consistent with the results of Thominette et al. (2006) showing that water diffusivity is a

decreasing function of hydrophilicity in many polymer families among which amine crosslinked epoxies.

References

- Carlsson, D.J., Brousseau, R., Wiles, D.W., 1986. Reactions of sulfur dioxide with oxidized polyolefins. *Polym. Degrad. Stab.* 15, 67–79.
- Damian, C., Espuche, E., Escoubes, M., 2001. Influence of three ageing types (thermal oxidation, radiochemical and hydrolytic ageing) on the structure and gas transport properties of epoxy-amine networks. *Polym. Degrad. Stab.* 72, 447–458.
- Devanne, T., Bry, A., Raguin, N., Sebban, M., Palmas, P., Audouin, L., Verdu, J., 2005. Radiochemical ageing of an amine cured epoxy network. Part II: kinetic modelling. *Polymer* 46, 237–242.
- Gardette, J.L., Lemaire, L., 1986. Advantages and limits of hydroperoxide titration methods in solid polymers. *Polym. Photochem.* 7, 409–416.
- Lee, J.R., Park, S.J., Seo, M.K., Baik, Y.K., Lee, S.K., 2006. A study on physicochemical properties of epoxy coating system for nuclear power plants. *Nucl. Eng. Des.* 236, 931–937.
- Longi eras, N., Sebban, M., Palmas, P., Rivaton, A., Gardette, J.L., 2007. Degradation of epoxy resins under high energy electron beam irradiation: radio-oxidation. *Polym. Degrad. Stab.* 92, 2190–2197.
- Longi eras, N., Sebban, M., Palmas, P., Rivaton, A., Gardette, J.L., 2006. Multiscale approach to investigate the radiochemical degradation of epoxy resins under high-energy electron-beam irradiation. *J. Polym. Sci.: Polym. Chem.* 44, 865–887.
- Mall egol, J., Gonon, L., Commereuc, S., Verney, V., 2001. Thermal (DSC) and chemical (iodometric titration) methods for peroxides measurements in order to monitor drying extent of alkyd resins. *Prog. Org. Coat.* 41, 171–176.
- Ngono-Ravache, Y., Foray, M.F., Bardet, M., 2001. High resolution solid-state ¹³C-NMR study of as-cured and irradiated epoxy resins. *Polym. Adv. Technol.* 12, 515–523.
- Ouldmetidji, Y., Gonon, L., Commereuc, S., Verney, V., 2001. A differential scanning calorimetry method to study polymer photoperoxidation. *Polym. Test.* 20, 765–768.
- Park, S.J., Seo, M.K., Lee, J.R., 2004. Effects of irradiation and design basis accident conditions on thermal properties of epoxy coating system for nuclear power plant. *Nucl. Eng. Des.* 228, 47–54.
- Richaud, E., Farcas, F., Fayolle, B., Audouin, L., Verdu, J., 2006. Hydroperoxide titration by DSC in thermally oxidized polypropylene. *Polym. Test.* 25, 829–838.
- Thominette, F., Gaudichet-Maurin, E., Verdu, J., 2006. Effect of structure on water diffusion in polymers. *Defect and Diffusion Forum* 258, 442–446.